

**STATE OF NEW MEXICO  
BEFORE THE WATER QUALITY CONTROL COMMISSION**

\_\_\_\_\_)  
**In the Matter of:** )  
 )  
 )  
**PROPOSED AMENDMENT** )  
**TO 20.6.2 NMAC (Copper Rule)** )  
\_\_\_\_\_)

**No. WQCC 12-01(R)**

**EXHIBIT FINLEY - 2**

## Chapter 6

# GEOCHEMISTRY OF ACID MINE WATERS

D. Kirk Nordstrom<sup>1</sup> and C.N. Alpers<sup>2</sup>

<sup>1</sup>*U.S. Geological Survey, 3215 Marine Street, Boulder, CO 80303-1066*

<sup>2</sup>*U.S. Geological Survey, Placer Hall, 6000 J Street, Sacramento, CA 95879-6129*

### INTRODUCTION

There are about a dozen major hydrogeochemical processes that can account for the chemical composition of most natural waters. One of these is the oxidation of pyrite, a process at least as important a source of sulfate in natural waters as seawater and sea spray, gypsum dissolution, and atmospheric emissions. The natural process of pyrite oxidation is fundamental to the supergene alteration of ore deposits, the formation of acid-sulfate soils, and the development of acidity and metal mobilization in natural waters. As mineral deposits continue to be mined, and inactive or abandoned mines with their associated waste-rock and tailings piles continue to be exposed to weathering, large concentrations of sulfate and heavy metals will continue to be found in both surface waters and ground waters. Nearly  $5 \times 10^{10}$  tons of mining and mineral processing wastes had been generated in the United States as of 1985 and about  $10^9$  tons continue to be generated each year (U.S. Environmental Protection Agency, 1985). A more recent estimate indicates that there may be more than 500,000 inactive or abandoned mine sites in the U.S. (Lyon et al., 1993). Hazardous mine sites in serious need of remediation are probably much fewer but may still range in the thousands. Inventories of mineral resources, mine sites, and their associated environmental hazards are being assembled at various scales by federal and state agencies to better assess the magnitude of the problem.

The water-quality hazard produced by pyrite oxidation is known as "acid rock drainage," or if from a mined area, "acid mine drainage." We use the terms "acid mine drainage" and "acid mine water" synonymously, reflecting popular usage. These waters drain from waste rock, tailings, open pits, and underground mines into surface streams, rivers, and lakes. Acid mine waters typically have pH values in the range of 2-4 and high concentrations of metals known to be toxic to living organisms (Ash et al., 1951; Martin and Mills, 1976; Nordstrom and Ball, 1985). Natural waters acidified by mine drainage have killed enormous numbers of fish and benthic organisms, harmed livestock, and destroyed crops and have made many rivers, streams, and lakes turbid, colored, and unfit for most beneficial purposes. In the United States,  $10^7$  fish were reported killed during 1961-1975 from the effects of mining activities (Biernacki, 1978), and this number can safely be considered a gross underestimate. For example, the eighth annual report of the Federal Water Pollution Control Administration (1968) states that of the  $11.59 \times 10^6$  fish reported killed in 1967 from all types of pollution only 16,413 were reported killed from the state of California. The California Department of Fish and Game (Nordstrom et al., 1977), however, recorded

47,100 fish killed from mine drainage at one site during a 7-day period in January of 1967. Many other mining-related fish kills may not be adequately recorded in federal or state archives.

Kleinmann (1989) has estimated that about 19,300 km of rivers and streams and more than 180,000 acres of lakes and reservoirs in the continental U.S. have been seriously damaged by acid mine drainage. Although a quantitative assessment of environmental damage from mining activities may be difficult or impossible, the volume of water bodies affected by acid mine drainage could be comparable to that affected by acid rain or other industrial sources of acidification.

It is important to note that pyrite oxidation also occurs in the absence of mining and there are numerous localities world-wide where naturally acidic waters containing high concentrations of metals are known (Runnells et al., 1992). The geochemical processes of weathering may be very similar in terms of mineral oxidation and dissolution but the hydrologic regime, the rates of reaction, and the environmental consequences can be quite different. Geochemical reactions in mined areas are more rapid because of:

- 1) greater accessibility of air through mine workings, wastes, and tailings,
- 2) greater surface areas for sulfides in mine workings, wastes, and especially tailings, and
- 3) different compositions of tailings as a result of mineral processing.

The presence of flues and flue dust piles (typically high in arsenic, zinc, and cadmium), slag piles, and soils and rocks contaminated by smelter fumes can be particularly detrimental to flora and fauna. Erosion of these materials by both aeolian and fluvial transport can contaminate drainage systems for very long distances (Moore and Luoma, 1990). The slower weathering of unmined mineral deposits occurs over longer time frames and tends to lead to more stable and insoluble mineral phases than those at mined deposits.


As an example of the extremes to which mine waters can develop acidity and high metal concentrations, the analyses of four of the most acidic mine waters ever reported are shown in Table 6.1. These waters were found in the Richmond mine workings at Iron Mountain, California (Nordstrom et al., 1991). Note that all samples have negative pH values and metal concentrations in grams per liter. These concentrations are some of the highest recorded metal and sulfate concentrations and the lowest pH values known. A survey of the literature indicates that only one known determination for copper, one for zinc, and one for arsenic have been found to be higher than those from the Richmond mine

waters (Table 6.1). Although these extreme values are rare, they do indicate the dramatic changes in water quality caused by natural processes and enhanced by mining activities.

**TABLE 6.1**—Comparison of four of the most acidic mine waters at Iron Mountain, California with the most acidic and metal-rich mine waters reported in the world (pH values in standard units, concentrations in grams per liter, Nordstrom et al., 1991; Nordstrom and Alpers, 1999).

	Iron Mountain				Other sites	References
pH	-0.7	-2.5	-2.6	-3.6	0.67	Goleva et al. (1970)
Cu	2.3	4.8	3.2	n.d.	48	Clarke (1916)
Zn	7.7	23.5	20	n.d.	50	Braeuning (1977)
Cd	0.048	0.21	0.17	n.d.	0.041	Lindgren (1928)
As	0.15	0.34	0.22	n.d.	0.40	Goleva (1977)
Fe (total)	86.2	111	101	16.3	48	Blowes et al. (1991)
Fe (II)	79.7	34.5	34.9	9.8	48	Blowes et al. (1991)
SO <sub>4</sub>	360	760	650	n.d.	209	Lindgren (1928)

The chemical reaction responsible for the formation of acid mine waters requires three basic ingredients: pyrite, oxygen, and water. The overall reaction is often written as:



where one mole of ferric hydroxide and 2 moles of sulfuric acid are produced for every mole of pyrite oxidized. For each mole of pyrite oxidized in equation [1], 1 electron is lost by oxidation of iron, 14 electrons are lost by oxidation of disulfide, and 15 electrons are gained by reduction of oxygen. Iron is also hydrolyzed and precipitated. All of these reactions cannot take place in a single step. Electron transfer reactions take place generally with only one or two electrons at a time (Basolo and Pearson, 1967). Hence, there could be 15 or more reactions with as many possible rate-determining steps to consider. To further complicate matters, several other oxidizing agents besides oxygen have been implicated in pyrite oxidation, e.g., ferric iron. Fortunately, all the intermediate reactions need not be determined to delineate the rate-controlling mechanisms involved with pyrite oxidation.

This chapter reviews the abiotic and microbial rates and mechanisms for sulfide mineral oxidation, the secondary minerals formed as a result of sulfide oxidation, and the major environmental factors that control the quality and quantity of acid water produced from mining activities.

## HISTORICAL BACKGROUND

The history of mining and its environmental consequences, like technology in general, goes back several thousands of years, well before recorded history. Theophrastus (ca. 315 B.C.) mentions the degradation of pyrite to acid and salts (see Agricola, 1556). By the time of Pliny (23–79 A.D.), it was already well known that oil of vitriol (sulfuric acid), vitriol (ferrous sulfate), and alum (aluminum sulfates) were produced by the natural lixiviation (leaching) of pyritiferous rocks. Oil of vitriol was used to make other acids and compounds, vitriol was primarily used to blacken leather, and alum was used to tan hides. The acid waters and their

associated efflorescent (or flowering) salts produced from pyrite oxidation were also known to be highly toxic. Georgius Agricola (1546) wrote "When moisture corrodes cupriferous and friable pyrite it produces an acid juice from which *atramentum sutorium* forms and also liquid alum.... Experiments show that when porous, friable pyrite is attacked by moisture such an acid juice is produced." *De Re Metallica* (Agricola, 1556), considered to be the first systematic book on mining and mineralogy, contains the following passage, "Since I have explained the nature of vitriol and its relatives which are attained from cupriferous pyrites I will next speak of an acid solidified juice...; it is hard and white and so acrid that it kills mice, crickets and every kind of animal." The "solidified juice" was later identified (by Herbert Hoover, translator) as goslarite, a hydrated zinc sulfate that likely contained some cadmium. With the dawn of the industrial revolution, acid mine drainage became a major source of water pollution on a large scale.

In the United States, occasional effort was directed towards the problem of acid mine drainage in the Appalachian coal mining region before 1900 (Vranesh, 1979). The State of Indiana has had a land reclamation act for coal-stripping since 1942 and a history of concern with the adverse effects of strip mining that can be traced back to 1917 (Wilber, 1969). Western mines were originally exempt from regulations on mine drainage or other environmental hazards because of the interest in attracting businesses and people to the West. Mining and metallurgical engineers occasionally investigated the problem (e.g., Burke and Downs, 1938), but primarily with an aim to alleviate coal mine drainage problems. From the 1920s through the 1940s, government agencies and the mining industry investigated acid mine drainage produced in the Appalachians from coal mines (Ash et al., 1951). Twenty years later the Appalachian Regional Commission reviewed the coal mine drainage problems (Appalachian Regional Commission, 1969). From the late 1960s through the late 1970s the National Coal Association and Bituminous Coal Research, Inc. sponsored a series of Coal Mine Drainage Research Symposia that resulted in several useful publications on the problem. About the same time, considerable research was supported by the Federal Water Pollution Control Federation and, later, the Environmental Protection Agency (EPA) on both the causes of acid mine drainage and its remediation. Even more attention has been given to the problem with the advent of the Comprehensive Environmental Response, Compensation and Liability Act (CERCLA or Superfund) in 1980. Several mining sites around the country were put on EPA's National Priority List for Superfund investigation and remediation.

## FORMATION OF ACID MINE WATERS

The general description of the weathering of pyrite will now be examined in more detail. Equation [1], the overall reaction for the breakdown of pyrite to ferric hydroxide and sulfuric acid, is a gross oversimplification. It gives the correct picture in that oxygen is the ultimate driving force for the oxidation of pyrite and the final products are an insoluble form of oxidized iron and an aqueous sulfuric acid solution. Some problems with equation [1] are that it does not explain geochemical mechanisms or rates, it does not explain that ferric hydroxide is a fictitious, idealized phase, and it does not reflect the slow oxidation of aqueous ferrous iron in acid solutions that often results in high ferrous iron concentrations in

acid mine waters. Furthermore, factors such as microbial catalysis, neutralization reactions, sorption reactions, and climatic effects have an important influence on pyrite weathering, but are not considered explicitly in equation [1].


Mine operators as well as reclamation and remediation teams would like to know the potential or actual production of acid waters from a mine or from waste materials at a mine or a mineral processing facility. There is no simple, single test to assess metal and acid mobility in these settings because of the numerous variables that affect contaminant transport. The problem is multifaceted and we must emphasize that acid mine drainage forms within a complex environmental system where several factors need to be considered within the five general categories as shown in Table 6.2. These five categories are traditional scientific disciplines that must be integrated to characterize a field site.

TABLE 6.2—Environmental factors affecting acid mine water formation.

	Traditional Scientific Disciplines				
	Inorganic chemistry	Organic chemistry	Geology/mineralogy	Hydrology	Microbiology
Sulfide oxidation	✓		✓	✓	✓
Fe <sup>(II)</sup> <sub>(aq)</sub> → Fe <sup>(III)</sup> <sub>(aq)</sub>	✓	✓		✓	✓
pH	✓	✓		✓	✓
Temperature	✓		✓	✓	✓
Gangue dissolution	✓		✓	✓	✓
Rock type/structure	✓		✓	✓	✓
Porosity			✓	✓	✓
Permeability			✓	✓	✓
Flow paths (recharge/discharge)	✓		✓	✓	✓
Climate	✓			✓	✓
Evapoconcentration/efflorescent salt formation	✓		✓	✓	✓
Efflorescent salt dissolution	✓		✓	✓	✓
Photochemistry	✓	✓		✓	✓

**Stoichiometry and kinetics of abiotic pyrite oxidation**

The voluminous literature on pyrite oxidation has been reviewed by Lowson (1982) with regard to abiotic chemical oxidation and by Nordstrom (1982a) with regard to biotic and abiotic geochemical oxidation. More recent contributions can be found in Goldhaber (1983), McKibben and Barnes (1986), Moses et al. (1987), Moses and Herman (1991), and Evangelou (1995). When pyrite oxidizes there are two species that can oxidize, the ferrous iron and the sulfidic sulfur. In studies on acid mine waters and pyrite oxidation, it has long been recognized that iron easily leaches out of pyrite but tends to stay in the ferrous state in acid solutions. Ancient history records the production of vitriol and oil of vitriol from washing pyritiferous ores and shales. During the last two centuries this vitriol was determined to be a mixture of ferrous sulfate and sulfuric acid. Hence, another common representation of the pyrite oxidation reaction is:



The sulfur moiety in pyrite oxidizes more quickly than the iron, but it must transfer a large number of electrons (14 times as many as iron per mole of pyrite). Consequently, there are several possible side reactions and sulfur intermediates that may occur during oxidation.

One side reaction is the formation of elemental sulfur during oxidation (Stokes, 1901; Bergholm, 1955; Clark, 1966). The yield is low and increases with higher temperatures, up to a maximum at about 100–150°C (Lowson, 1982). The lowest yield is at ambient temperatures but increases with increasing acidity. Field observations without laboratory identification are not reliable sources of information on elemental sulfur forming from pyrite oxidation because other minerals such as copiapite and jarosite may commonly be misidentified as elemental sulfur. Positive identification of elemental sulfur has been made at numerous inactive tailings impoundments (Blowes, 1995, written comm.). When acid waters react with minerals such as pyrrhotite and sphalerite they will produce H<sub>2</sub>S, which readily oxidizes to elemental sulfur. Elemental sulfur is found commonly in nature where sulfur-rich, near-surface, hydrothermal solutions with temperatures around 100–150°C have oxidized or where H<sub>2</sub>S-rich spring waters have oxidized on exposure to air.


Another side reaction, or group of reactions, is the formation of intermediate sulfoxyanions of lower oxidation state than that found in sulfate: i.e., thiosulfate (S<sub>2</sub>O<sub>3</sub><sup>2-</sup>), polythionates (S<sub>n</sub>O<sub>6</sub><sup>2-</sup>), and sulfite (SO<sub>3</sub><sup>2-</sup>). Steger and Desjardins (1978) reported a thiosulfate compound on the surface of oxidizing pyrite but their method did not distinguish between thiosulfate, polythionate, and sulfite. Goldhaber (1983) measured rates of reaction and reaction products for the pH range 6–9 and found that polythionates, thiosulfate, sulfite, and sulfate formed but only at high stirring rates. The proportions of intermediate sulfoxyanions were sensitive to pH in Goldhaber's (1983) experiments. Polythionates were found to be dominant at low pH and thiosulfate was dominant at high pH, with some sulfite formed at the highest pH values. Some ambiguity exists in his determination of polythionates and thiosulfate. He used the colorimetric method of Nor and Tabatai (1976), which assumes tetrathionate is the dominant polythionate and does not completely distinguish between thiosulfate and polythionate. The pyrite and sphalerite oxidation experiments of Moses et al. (1987) included more direct determination of sulfate, sulfite, polythionates, and thiosulfate by ion chromatography (Moses et al., 1984). Their results were similar to those of Goldhaber (1983) except that additional experiments carried out in the presence of Fe<sup>3+</sup><sub>(aq)</sub> did not produce any detectable intermediate sulfoxyanions. These results are also similar to those of aqueous H<sub>2</sub>S oxidation with oxygen (Chen and Morris, 1971, 1972; Zhang and Millero, 1994; Vairavamurthy et al., 1994).

Experiments documenting the formation of intermediate sulfoxyanions during pyrite oxidation should not be taken as evidence that the same oxyanions are to be found in natural waters during sulfide weathering. In experimental systems, these compounds can only be detected in solution when the aqueous layer next to the mineral surface is strongly sheared by high stirring rates so that these metastable products can not back-react by further electron exchange with the solid. Such strong shearing is not found generally in ground-water systems and even rapidly-moving surface waters rarely exhibit such shearing at the mineral surface. Luther (1987, 1990) has pointed out that species such as thiosul-


fate and sulfite would not be detected in solutions containing  $\text{Fe}^{3+}_{(\text{aq})}$  because they oxidize so rapidly; experiments by Williamson and Rimstidt (1993) and references therein confirmed that this reaction is rapid. Furthermore, intermediate sulfoxyanions are an excellent source of energy for chemoautotrophic bacteria of the *Thiobacillus* genus and may be quickly biodegraded before detectable concentrations can accumulate (Gould et al., 1994).

The experiments of Granger and Warren (1969) are often cited as evidence for the formation of sulfoxyanions from pyrite oxidation and the role of sulfoxyanions in the genesis of ore deposits. However, these authors admitted that the thiosulfate they found in their column experiments may have been formed by the oxidation of residual aqueous  $\text{Na}_2\text{S}$  solution. They had first added  $\text{H}_2\text{O}_2$  solution in an effort to sterilize the column and then added  $\text{Na}_2\text{S}$  solution to reduce the iron oxide stains that had formed from the peroxide treatment. After such a traumatic chemical treatment, significant quantities of thiosulfate would have formed from the aqueous sulfide solution and would have been difficult to remove completely from the column. The thiosulfate thus formed may have had nothing to do with pyrite oxidation.

It has long been known that ferric iron rapidly oxidizes pyrite (Stokes, 1901). Experiments carried out by Garrels and Thompson (1960) and McKibben and Barnes (1986) have confirmed the balanced reaction stoichiometry:



for the oxidation of pyrite by aqueous ferric ions. This reaction is considerably faster than the reaction with oxygen as the oxidant, but significant concentrations of oxidized iron only occur at low pH values because of the low solubility of hydrolyzed ferric iron at circumneutral pH values. Hence, it is thought that pyrite oxidation is initiated by oxygen at circumneutral pH (equation [2]) but as pH values reduce to about 4, the rate of oxidation becomes governed by equation [3]. Oxygen is still required to replenish the supply of ferric iron according to



but the oxygen does not have to diffuse all the way to the pyrite surfaces. It is quite possible for pyrite to oxidize in the absence of dissolved oxygen. Nevertheless, the overall rate of pyrite oxidation in a tailings pile, in a mine, or in a waste rock pile will largely be determined by the overall rate of oxygen transport (advection and diffusion).

Considerable speculation can be found in the literature on the question of the initiation and propagation of pyrite oxidation. Undoubtedly, during the initiation of pyrite oxidation, there are complex chemical and microbiological processes occurring in microenvironments (Williams et al., 1982), i.e., within a few tens of nanometers of the surface of a sulfide grain. These regions are inaccessible to normal sampling techniques and are not represented by the bulk aqueous phase. For example, when oxygen initially adsorbs to a pyrite surface and transfers electrons, an accumulation of protons will form at or near the surface. Acidophilic iron-oxidizing bacteria will begin to colonize and a film of acidic water will cover the mineral grain without affecting the bulk aqueous

phase. Even before some acidic water develops, neutrophilic *Thiobacilli* will catalyze the initial stage of pyrite oxidation (Blowes et al., 1995; Gould et al., 1994). The extent to which these microenvironmental gradients affect the bulk properties are dependent on many factors, not the least of which is the pyrite concentration in the rock, soil, or waste material. The existence and importance of these microenvironments is well illustrated by the formation of jarosite, a mineral that can only form under acid conditions and has been found in soil waters of circumneutral pH (Carson et al., 1982).

The oxidation of at least 18 different sulfide minerals has been investigated (Table 6.3). Most of these have been studied with and without microbial catalysis by *Thiobacillus ferrooxidans*. The microbial oxidation rate is usually greater than the abiotic rate, all other conditions being equal. Unfortunately, most of the microbial studies were done without measurement of surface area and without a consistent procedure for removing small particles or otherwise cleaning the samples before the experiment. The lack of these characteristics prevents any direct comparison of microbial oxidation rates except in a qualitative manner. The results for abiotic and biotic oxidation of pyrite, however, are of considerably better quality than for other sulfide minerals and some quantitative comparisons are possible.

It should be noted that arsenic-rich minerals such as arsenopyrite and orpiment are also subject to bacterially catalyzed oxidation (Ehrlich, 1963a, 1964). Indeed, the occurrence of arsenite-oxidizing bacteria in acid mine waters has been reported by Wakao et al. (1988) and one of the first reports of arsenite oxidation by heterotrophic bacteria was that of Turner (1949).

There are now numerous reports on the oxidation rates of pyrite and marcasite by oxygen (Bergholm, 1955; McKay and Halpern, 1958; Smith and Shumate, 1970; Mathews and Robins, 1974; Goldhaber, 1983; McKibben and Barnes, 1986; Moses et al., 1987; Nicholson et al., 1988; Moses and Herman, 1991), by ferric iron (Bergholm, 1955; Garrels and Thompson, 1960; Smith and Shumate, 1970; Mathews and Robins, 1972; Wiersma and Rimstidt, 1984; McKibben and Barnes, 1986; Moses et al., 1987; Brown and Jurinak, 1989; Moses and Herman, 1991), and by hydrogen peroxide (McKibben and Barnes, 1986). The oxidation rates of pyrrhotite in the presence of oxygen (Nicholson and Scharer, 1994) and marcasite, covellite, galena, sphalerite, chalcopyrite, and arsenopyrite in the presence of ferric iron (Rimstidt et al., 1994) have been measured. Pyrite oxidation rates from different studies are generally comparable, but differences in experimental design, initial pH values, temperatures, grain size, mineral preparation, method for data reduction and rate law expression make a quantitative comparison difficult. For this paper, we use the results of McKibben and Barnes (1986) on pyrite to compare with the biotic rates in the next section. Table 6.4 summarizes the reaction rates from several studies cited above for a pH close to 2,  $m_{\text{Fe(III)}} = 10^{-3}$ , temperatures close to 25°C, and oxygen in equilibrium with the atmosphere.

The rates in Table 6.4 show that the oxidation of pyrite by ferric iron (according to the reaction stoichiometries given in equations [2] and [3]) can be about 2–3 orders of magnitude faster than by oxygen, that some minerals oxidize more rapidly than pyrite and some more slowly, and that oxidation rates can range over three orders of magnitude. These rates are demonstrably faster than the dissolution rates for aluminosilicate minerals (White and Brantley, 1995) by one to several orders of magnitude.

TABLE 6.3—Sulfide oxidation studies (more references can be found in Nordstrom and Southam, 1997).

Mineral	Formula	Oxidant	pH	Reference
Pyrite	FeS <sub>2</sub>	O <sub>2</sub> , Fe <sup>3+</sup> , H <sub>2</sub> O <sub>2</sub>	0-10	See references in next sections
Marcasite	FeS <sub>2</sub>	O <sub>2</sub> , Fe <sup>3+</sup>	2-3	Wiersma and Rimstidt (1984); Silverman et al. (1961)
Pyrrhotite	Fe <sub>1-x</sub> S	O <sub>2</sub>	2-6	Nicholson and Scharer (1994)
Sphalerite	(Zn, Fe)S	O <sub>2</sub> , Fe <sup>3+</sup>	2-7	Rimstidt et al. (1994); Torma et al. (1972); Khalid and Ralph (1977)
Galena	PbS	O <sub>2</sub> , Fe <sup>3+</sup>	2	Rimstidt et al. (1994); Torma and Subramanian (1974)
Chalcopyrite	CuFeS <sub>2</sub>	O <sub>2</sub> , Fe <sup>3+</sup>	1.2-2.5	Rimstidt et al. (1994); Torma et al. (1976)
Arsenopyrite	FeAsS	O <sub>2</sub> , Fe <sup>3+</sup>	2	Rimstidt et al. (1994); Ehrlich (1964)
Covellite	CuS	O <sub>2</sub> , Fe <sup>3+</sup>	2	Walsh and Rimstidt (1986); Rickard and Vanselow (1978)
Chalcocite	Cu <sub>2</sub> S	O <sub>2</sub>	2-4.8	Beck (1977); Sakaguchi et al. (1976)
Greenockite	CdS	O <sub>2</sub>	2.3	Torma et al. (1974)
Millerite	NiS	O <sub>2</sub>	2.3	Torma et al. (1974)
Cobalt sulfide	CoS	O <sub>2</sub>	2.3	Torma et al. (1974)
Klockmannite	CuSe	O <sub>2</sub>	2.3	Torma and Habashi (1972)
Cinnabar	HgS	Fe <sup>3+</sup>	2	Burkstaller et al. (1975)
Enargite	Cu <sub>3</sub> AsS <sub>4</sub>	O <sub>2</sub>	3	Ehrlich (1964)
Orpiment	As <sub>2</sub> S <sub>3</sub>	O <sub>2</sub>		Ehrlich (1963a)
Bornite	Cu <sub>5</sub> FeS <sub>4</sub>	O <sub>2</sub>		Landesman et al. (1966)
Molybdenite	MoS <sub>2</sub>	O <sub>2</sub>	2.5	Brierley and Murr (1973)
Tetrahedrite	(Cu,Fe) <sub>12</sub> Sb <sub>4</sub> S <sub>13</sub>	O <sub>2</sub>		Yakhontova et al. (1980)
Stibnite	Sb <sub>2</sub> S <sub>3</sub>	O <sub>2</sub>		Torma et al. (1974)
Pentlandite	(Fe, Ni) <sub>9</sub> S <sub>8</sub>	O <sub>2</sub>		Brierley and Le Roux (1977)

TABLE 6.4—Abiotic reaction rates (mol m<sup>-2</sup> s<sup>-1</sup>) for sulfide mineral oxidation.

Mineral/Oxidant	MB86 <sup>1</sup>	BJ89 <sup>2</sup>	R94 <sup>3,7</sup>	N94 <sup>4</sup>	NS94 <sup>5</sup>
Pyrite/O <sub>2</sub>	3.1 x 10 <sup>-10</sup>			5.3 x 10 <sup>-10</sup>	1.1 x 10 <sup>-10</sup>
Pyrite/Fe <sup>3+</sup>	9.6 x 10 <sup>-9</sup>	1.8 x 10 <sup>-8</sup>	1.9 x 10 <sup>-8</sup>		
Pyrrhotite/O <sub>2</sub>				1.4 x 10 <sup>-8</sup>	
Marcasite/Fe <sup>3+</sup>			1.5 x 10 <sup>-7</sup>		
Arsenopyrite/Fe <sup>3+</sup>			1.7 x 10 <sup>-6</sup>		
Galena/Fe <sup>3+</sup>			1.6 x 10 <sup>-6</sup>		
Sphalerite/Fe <sup>3+</sup>			7.0 x 10 <sup>-8</sup>		
Blau. covellite <sup>6</sup> /Fe <sup>3+</sup>			7.1 x 10 <sup>-8</sup>		
Chalcopyrite/Fe <sup>3+</sup>			9.6 x 10 <sup>-9</sup>		
Covellite/Fe <sup>3+</sup>			9.1 x 10 <sup>-9</sup>		

<sup>1</sup> McKibben and Barnes (1986); because there appears to be an error in the stated value for pyrite oxidation by oxygen we have used the corrected value from Nicholson (1994).

<sup>2</sup> Brown and Jurinak (1989); average from oxidation rates measured in different electrolytes.

<sup>3</sup> Rimstidt et al. (1994).

<sup>4</sup> Nicholson (1994); the value for pyrite is an average from four studies covering a pH range of 1-8.

<sup>5</sup> Nicholson and Scharer (1994) and Tervari and Campbell (1976).

<sup>6</sup> "blau. covellite" is blaubleibender or "blue-remaining" covellite having slightly different optical and X-ray properties than ordinary covellite.

<sup>7</sup> The values listed for R94 are all given in terms of the amount of Fe(III) reduced except for pyrite. All values for pyrite are given in the same units, per mole of pyrite oxidized, for purposes of direct comparison.

Galvanic protection does occur during oxidative dissolution of coexisting sulfide minerals. This phenomenon is the same as that for galvanized iron. The more electroconductive metal sulfide (the one with the higher standard electrode reduction potential, see Sato, 1992) will oxidize at a slower rate and the less electroconductive sulfide will oxidize at a faster rate than either one would when not in contact. Sveshnikov and Dobyichin (1956) reported that rates of metal release from different sulfides are related to

their electrode potentials and that a mixture of sulfide minerals in contact releases more metals into solution and decreases the pH more than monomineralic samples. Sveshnikov and Ryss (1964) postulated that these electronic properties of co-existing conductive sulfides are important during the weathering of sulfide mineral deposits. Sato (1992) has used electrochemical data on metal sulfides, typical of heavy metal sulfide deposits, to explain the mineral assemblage that is found during supergene enrichment.


fate and sulfite would not be detected in solutions containing  $\text{Fe}_{(\text{aq})}^{3+}$  because they oxidize so rapidly; experiments by Williamson and Rimstidt (1993) and references therein confirmed that this reaction is rapid. Furthermore, intermediate sulfoxyanions are an excellent source of energy for chemoautotrophic bacteria of the *Thiobacillus* genus and may be quickly biodegraded before detectable concentrations can accumulate (Gould et al., 1994).

The experiments of Granger and Warren (1969) are often cited as evidence for the formation of sulfoxyanions from pyrite oxidation and the role of sulfoxyanions in the genesis of ore deposits. However, these authors admitted that the thiosulfate they found in their column experiments may have been formed by the oxidation of residual aqueous  $\text{Na}_2\text{S}$  solution. They had first added  $\text{H}_2\text{O}_2$  solution in an effort to sterilize the column and then added  $\text{Na}_2\text{S}$  solution to reduce the iron oxide stains that had formed from the peroxide treatment. After such a traumatic chemical treatment, significant quantities of thiosulfate would have formed from the aqueous sulfide solution and would have been difficult to remove completely from the column. The thiosulfate thus formed may have had nothing to do with pyrite oxidation.

It has long been known that ferric iron rapidly oxidizes pyrite (Stokes, 1901). Experiments carried out by Garrels and Thompson (1960) and McKibben and Barnes (1986) have confirmed the balanced reaction stoichiometry:



for the oxidation of pyrite by aqueous ferric ions. This reaction is considerably faster than the reaction with oxygen as the oxidant, but significant concentrations of oxidized iron only occur at low pH values because of the low solubility of hydrolyzed ferric iron at circumneutral pH values. Hence, it is thought that pyrite oxidation is initiated by oxygen at circumneutral pH (equation [2]) but as pH values reduce to about 4, the rate of oxidation becomes governed by equation [3]. Oxygen is still required to replenish the supply of ferric iron according to



but the oxygen does not have to diffuse all the way to the pyrite surfaces. It is quite possible for pyrite to oxidize in the absence of dissolved oxygen. Nevertheless, the overall rate of pyrite oxidation in a tailings pile, in a mine, or in a waste rock pile will largely be determined by the overall rate of oxygen transport (advection and diffusion).

Considerable speculation can be found in the literature on the question of the initiation and propagation of pyrite oxidation. Undoubtedly, during the initiation of pyrite oxidation, there are complex chemical and microbiological processes occurring in microenvironments (Williams et al., 1982), i.e., within a few tens of nanometers of the surface of a sulfide grain. These regions are inaccessible to normal sampling techniques and are not represented by the bulk aqueous phase. For example, when oxygen initially adsorbs to a pyrite surface and transfers electrons, an accumulation of protons will form at or near the surface. Acidophilic iron-oxidizing bacteria will begin to colonize and a film of acidic water will cover the mineral grain without affecting the bulk aqueous

phase. Even before some acidic water develops, neutrophilic *Thiobacilli* will catalyze the initial stage of pyrite oxidation (Blowes et al., 1995; Gould et al., 1994). The extent to which these microenvironmental gradients affect the bulk properties are dependent on many factors, not the least of which is the pyrite concentration in the rock, soil, or waste material. The existence and importance of these microenvironments is well illustrated by the formation of jarosite, a mineral that can only form under acid conditions and has been found in soil waters of circumneutral pH (Carson et al., 1982).

The oxidation of at least 18 different sulfide minerals has been investigated (Table 6.3). Most of these have been studied with and without microbial catalysis by *Thiobacillus ferrooxidans*. The microbial oxidation rate is usually greater than the abiotic rate, all other conditions being equal. Unfortunately, most of the microbial studies were done without measurement of surface area and without a consistent procedure for removing small particles or otherwise cleaning the samples before the experiment. The lack of these characteristics prevents any direct comparison of microbial oxidation rates except in a qualitative manner. The results for abiotic and biotic oxidation of pyrite, however, are of considerably better quality than for other sulfide minerals and some quantitative comparisons are possible.

It should be noted that arsenic-rich minerals such as arsenopyrite and orpiment are also subject to bacterially catalyzed oxidation (Ehrlich, 1963a, 1964). Indeed, the occurrence of arsenite-oxidizing bacteria in acid mine waters has been reported by Wakao et al. (1988) and one of the first reports of arsenite oxidation by heterotrophic bacteria was that of Turner (1949).

There are now numerous reports on the oxidation rates of pyrite and marcasite by oxygen (Bergholm, 1955; McKay and Halpern, 1958; Smith and Shumate, 1970; Mathews and Robins, 1974; Goldhaber, 1983; McKibben and Barnes, 1986; Moses et al., 1987; Nicholson et al., 1988; Moses and Herman, 1991), by ferric iron (Bergholm, 1955; Garrels and Thompson, 1960; Smith and Shumate, 1970; Mathews and Robins, 1972; Wiersma and Rimstidt, 1984; McKibben and Barnes, 1986; Moses et al., 1987; Brown and Jurinak, 1989; Moses and Herman, 1991), and by hydrogen peroxide (McKibben and Barnes, 1986). The oxidation rates of pyrrhotite in the presence of oxygen (Nicholson and Scharer, 1994) and marcasite, covellite, galena, sphalerite, chalcopyrite, and arsenopyrite in the presence of ferric iron (Rimstidt et al., 1994) have been measured. Pyrite oxidation rates from different studies are generally comparable, but differences in experimental design, initial pH values, temperatures, grain size, mineral preparation, method for data reduction and rate law expression make a quantitative comparison difficult. For this paper, we use the results of McKibben and Barnes (1986) on pyrite to compare with the biotic rates in the next section. Table 6.4 summarizes the reaction rates from several studies cited above for a pH close to 2,  $m_{\text{Fe(III)}} = 10^{-3}$ , temperatures close to 25°C, and oxygen in equilibrium with the atmosphere.

The rates in Table 6.4 show that the oxidation of pyrite by ferric iron (according to the reaction stoichiometries given in equations [2] and [3]) can be about 2–3 orders of magnitude faster than by oxygen, that some minerals oxidize more rapidly than pyrite and some more slowly, and that oxidation rates can range over three orders of magnitude. These rates are demonstrably faster than the dissolution rates for aluminosilicate minerals (White and Brantley, 1995) by one to several orders of magnitude.

## GEOCHEMISTRY OF ACID MINE WATERS

TABLE 6.3—Sulfide oxidation studies (more references can be found in Nordstrom and Southam, 1997).

Mineral	Formula	Oxidant	pH	Reference
Pyrite	FeS <sub>2</sub>	O <sub>2</sub> , Fe <sup>3+</sup> , H <sub>2</sub> O <sub>2</sub>	0-10	See references in next sections
Marcasite	FeS <sub>2</sub>	O <sub>2</sub> , Fe <sup>3+</sup>	2-3	Wiersma and Rimstidt (1984); Silverman et al. (1961)
Pyrrhotite	Fe <sub>1-x</sub> S	O <sub>2</sub>	2-6	Nicholson and Scharer (1994)
Sphalerite	(Zn, Fe)S	O <sub>2</sub> , Fe <sup>3+</sup>	2-7	Rimstidt et al. (1994); Torma et al. (1972); Khalid and Ralph (1977)
Galena	PbS	O <sub>2</sub> , Fe <sup>3+</sup>	2	Rimstidt et al. (1994); Torma and Subramanian (1974)
Chalcopyrite	CuFeS <sub>2</sub>	O <sub>2</sub> , Fe <sup>3+</sup>	1.2-2.5	Rimstidt et al. (1994); Torma et al. (1976)
Arsenopyrite	FeAsS	O <sub>2</sub> , Fe <sup>3+</sup>	2	Rimstidt et al. (1994); Ehrlich (1964)
Covellite	CuS	O <sub>2</sub> , Fe <sup>3+</sup>	2	Walsh and Rimstidt (1986); Rickard and Vanselow (1978)
Chalcocite	Cu <sub>2</sub> S	O <sub>2</sub>	2-4.8	Beck (1977); Sakaguchi et al. (1976)
Greenockite	CdS	O <sub>2</sub>	2.3	Torma et al. (1974)
Millerite	NiS	O <sub>2</sub>	2.3	Torma et al. (1974)
Cobalt sulfide	CoS	O <sub>2</sub>	2.3	Torma and Habashi (1972)
Klockmannite	CuSe	O <sub>2</sub>	2.3	Torma and Habashi (1972)
Cinnabar	HgS	Fe <sup>3+</sup>	2	Burkstaller et al. (1975)
Enargite	Cu <sub>3</sub> AsS <sub>4</sub>	O <sub>2</sub>	3	Ehrlich (1964)
Orpiment	As <sub>2</sub> S <sub>3</sub>	O <sub>2</sub>		Ehrlich (1963a)
Bornite	Cu <sub>5</sub> FeS <sub>4</sub>	O <sub>2</sub>		Landesman et al. (1966)
Molybdenite	MoS <sub>2</sub>	O <sub>2</sub>	2.5	Brierley and Murr (1973)
Tetrahedrite	(Cu,Fe) <sub>12</sub> Sb <sub>4</sub> S <sub>13</sub>	O <sub>2</sub>		Yakhontova et al. (1980)
Stibnite	Sb <sub>2</sub> S <sub>3</sub>	O <sub>2</sub>		Torma et al. (1974)
Pentlandite	(Fe, Ni) <sub>9</sub> S <sub>8</sub>	O <sub>2</sub>		Brierley and Le Roux (1977)

TABLE 6.4—Abiotic reaction rates (mol m<sup>-2</sup> s<sup>-1</sup>) for sulfide mineral oxidation.

Mineral/Oxidant	MB86 <sup>1</sup>	BJ89 <sup>2</sup>	R94 <sup>3,7</sup>	N94 <sup>4</sup>	NS94 <sup>5</sup>
Pyrite/O <sub>2</sub>	3.1 x 10 <sup>-10</sup>			5.3 x 10 <sup>-10</sup>	1.1 x 10 <sup>-10</sup>
Pyrite/Fe <sup>3+</sup>	9.6 x 10 <sup>-9</sup>	1.8 x 10 <sup>-8</sup>	1.9 x 10 <sup>-8</sup>	1.4 x 10 <sup>-8</sup>	
Pyrrhotite/O <sub>2</sub>			1.5 x 10 <sup>-7</sup>		
Marcasite/Fe <sup>3+</sup>			1.7 x 10 <sup>-6</sup>		
Arsenopyrite/Fe <sup>3+</sup>			1.6 x 10 <sup>-6</sup>		
Galena/Fe <sup>3+</sup>			7.0 x 10 <sup>-8</sup>		
Sphalerite/Fe <sup>3+</sup>			7.1 x 10 <sup>-8</sup>		
Blau. covellite <sup>6</sup> /Fe <sup>3+</sup>			9.6 x 10 <sup>-9</sup>		
Chalcopyrite/Fe <sup>3+</sup>			9.1 x 10 <sup>-9</sup>		
Covellite/Fe <sup>3+</sup>					

<sup>1</sup> McKibben and Barnes (1986); because there appears to be an error in the stated value for pyrite oxidation by oxygen we have used the corrected value from Nicholson (1994).

<sup>2</sup> Brown and Jurinak (1989); average from oxidation rates measured in different electrolytes.

<sup>3</sup> Rimstidt et al. (1994).

<sup>4</sup> Nicholson (1994); the value for pyrite is an average from four studies covering a pH range of 1-8.

<sup>5</sup> Nicholson and Scharer (1994) and Tervari and Campbell (1976).

<sup>6</sup> "blau. covellite" is blaubleibender or "blue-remaining" covellite having slightly different optical and X-ray properties than ordinary covellite.

<sup>7</sup> The values listed for R94 are all given in terms of the amount of Fe(III) reduced except for pyrite. All values for pyrite are given in the same units, per mole of pyrite oxidized, for purposes of direct comparison.

Galvanic protection does occur during oxidative dissolution of coexisting sulfide minerals. This phenomenon is the same as that for galvanized iron. The more electroconductive metal sulfide (the one with the higher standard electrode reduction potential, see Sato, 1992) will oxidize at a slower rate and the less electroconductive sulfide will oxidize at a faster rate than either one would when not in contact. Svshnikov and Dobychin (1956) reported that rates of metal release from different sulfides are related to

their electrode potentials and that a mixture of sulfide minerals in contact releases more metals into solution and decreases the pH more than monomineralic samples. Svshnikov and Ryss (1964) postulated that these electronic properties of co-existing conductive sulfides are important during the weathering of sulfide mineral deposits. Sato (1992) has used electrochemical data on metal sulfides, typical of heavy metal sulfide deposits, to explain the mineral assemblage that is found during supergene enrichment.

Nicholson and Scharer (1994) mixed pyrrhotite and pyrite in different proportions to see if there was any evidence for galvanic protection, but could not detect any such effect in their study. Kwong (1995) has done laboratory experiments to show the effect of galvanic protection during dissolution of multi-sulfide mineral assemblages. The relative rates of mineral dissolution follow the sequence indicated by standard electrode potentials as outlined by Sato (1992).

Because the oxidation rate for pyrite by  $\text{Fe}^{3+}_{(\text{aq})}$  is faster than that by oxygen, it is important to know the oxidation rate for ferrous to ferric iron according to equation [4]. Numerous studies on the ferrous iron oxidation rate show that, under acid conditions, the rate becomes very slow and independent of pH. Singer and Stumm (1968) reported an abiotic rate of  $2.7 \times 10^{-12} \text{ mol L}^{-1} \text{ s}^{-1}$  at pH values below 4. Similar rates have been reported elsewhere. Such rates are considerably slower than the rate of oxidation of pyrite by  $\text{Fe}^{3+}_{(\text{aq})}$ ; hence, equation [4] would be the rate-limiting step were it not for the catalytic effect of bacteria.

#### Microbial oxidation: Historical perspective

Microorganisms are abundant in natural waters containing acid mine drainage; indeed, they are often the *only* form of life under such conditions. Powell and Parr (1919) and later Carpenter and Herndon (1933) suggested that pyrite oxidation and the consequent acid mine drainage from coal deposits may be catalyzed by bacteria. Lackey (1938) observed flagellates, rhizopods, ciliates, and green algae in 62 West Virginia streams. Joseph (1953) found gram-positive and gram-negative bacilli and cocci, fungi, green algae, diatoms, and actinomyces in acidified surface waters and soils in West Virginia and Pennsylvania. Acid mine waters from a copper mine in the southwestern U.S. were found to contain yeasts, flagellates, protozoa, and amoebae (Ehrlich, 1963b). "Acid slime streamers" have often been observed in acid mine waters (Dugan et al., 1970; Dugan, 1972).

As long ago as 1888 it was recognized by S.N. Winogradsky that certain microbes could oxidize reduced inorganic compounds, such as sulfur, to gain energy for the reduction of carbon dioxide for metabolism and growth (see Sokolova and Karavaiko, 1968). Microorganisms that utilize reduced inorganic substances are known as chemolithotrophic (see Mills, 1999). Nathansohn (1902) first isolated a *Thiobacillus* species and the acidophilic bacterium, *Thiobacillus thiooxidans*, was isolated and identified by Waksman and Jaffe (1921, 1922) from soils containing free sulfur and phosphate. Colmer and Hinkle (1947), Colmer et al. (1950), Temple and Colmer (1951), and Temple and Delchamps (1953) isolated a new chemoautotrophic and acidophilic bacterium, *Thiobacillus ferrooxidans*, and showed that microbial degradation of pyrite was an important factor in the production of acid mine waters.

The nutritional requirements for *T. ferrooxidans* are ubiquitous. Nitrogen and carbon dioxide are available in the atmosphere. Sulfur is readily available in mined environments, and only small amounts of phosphorous are needed. *Thiobacilli* have several adaptive techniques that permit them to tolerate low pH and high metal concentrations (Tuovinen et al., 1971; Kushner, 1978). Some studies have shown that *T. ferrooxidans* can tolerate g/l concentrations of Zn, Ni, Cu, Co, Mn, and Al (Tuovinen et al., 1971). Scala et al. (1982) found consistent and roughly equal concentrations of *T. thiooxidans* and *T. ferrooxidans* in mine effluents of different compositions from quite different mines, in different geo-

logical and climatological environments, in different parts of the country (from California to Virginia). The diversity of microorganisms and their populations in mineral deposit and mine waste environments is complex and not well understood. Further investigations on the microbial ecology of mines and mine wastes are certainly needed.

*T. thiooxidans* oxidizes elemental sulfur but not iron, *T. ferrooxidans* oxidizes both iron and sulfur compounds, and a third species, *Leptospirillum ferrooxidans*, behaves metabolically like *T. ferrooxidans* but has a helical-rod morphology first described by Markosyan (1972). *L. ferrooxidans* is now thought to be equally important as the other two bacilli (Sand et al., 1992). Mixed cultures oxidize reduced iron and sulfur compounds faster than single-species cultures (Kelly et al., 1979; Wakao et al., 1982). Apparently, bacteria are preconditioned by the medium in which they are cultured and may have a synergistic association with other species. For example, *T. ferrooxidans* grown in ferrous-containing solutions exhibited different surface chemistry than those grown on minerals such as pyrite, elemental sulfur, and chalcopyrite (Devasia et al., 1993) as exhibited by hydrophobicity and electrophoretic mobility measurements. The bacilli grown on mineral sulfides developed a proteinaceous cell surface appendage that adhered to the solid surface whereas the cells grown in ferrous iron solutions contained no such characteristic. The importance of these features bears on the mechanism of microbial oxidation. Free-floating bacteria can catalyze the oxidation of iron from ferrous to ferric in aqueous solution, and then the ferric iron directly oxidizes the pyrite. Silverman (1967) calls this the indirect mechanism. The direct contact mechanism works by direct adhesion of the bacteria to the pyrite surface. There has been a long-standing debate over whether the direct or indirect mechanism is dominant. We contend that the indirect mechanism is the dominant one, but there is some evidence for enhancement of the pyrite oxidation rate by direct microbial contact. Surface-etch patterns may result from bacterial attachment (Bennett and Tributsch, 1978), and direct microbial growth on pyrite surfaces has been observed (Konishi et al., 1990).

#### Microbial oxidation: Kinetics

The catalytic effect of *T. ferrooxidans* on the aqueous oxidation of ferrous to ferric iron is well-established. Singer and Stumm (1968, 1970a, b) found that bacteria increased the ferrous iron oxidation rate by  $10^5$  over the abiotic rate, from about  $3 \times 10^{-12} \text{ mol L}^{-1} \text{ s}^{-1}$  to about  $3 \times 10^{-7} \text{ mol L}^{-1} \text{ s}^{-1}$ . Silverman and Lundgren (1959), Lundgren et al. (1964), and Lacey and Lawson (1977) grew *T. ferrooxidans* on culture media and typically measured oxidation rates of  $2.8\text{--}8.3 \times 10^{-7} \text{ mol L}^{-1} \text{ s}^{-1}$ . Wakao et al. (1977) measured field oxidation rates of ferrous iron oxidation in acid mine drainage and estimated  $3 \times 10^{-6} \text{ mol L}^{-1} \text{ s}^{-1}$  but the stream velocity was not measured. Nordstrom (1985) measured stream velocities and iron oxidation rates of  $2$  to  $8 \times 10^{-7} \text{ mol L}^{-1} \text{ s}^{-1}$  in a mountainous stream drainage containing acid mine waters, where the range of values depended on climatic conditions. From these studies we have chosen an average microbial oxidation rate for ferrous iron of  $5 \times 10^{-7} \text{ mol L}^{-1} \text{ s}^{-1}$  for the purpose of comparison with the abiotic rates.

Table 6.5 summarizes abiotic and microbial rates of oxidation for ferrous iron and pyrite under roughly comparable conditions (except for the field rates cited here and discussed later). The

microbial oxidation rate of pyrite by oxygen is very similar to the abiotic oxidation rates of pyrite by either oxygen or ferric iron. Studies by Wakao et al. (1984) showed that adsorption of bacterial cells on pyrite surfaces actually inhibited pyrite oxidation and that it was the growth of free-floating ferrous-iron-oxidizing bacteria that contributed to pyrite oxidation. These results help to clarify the reaction mechanism. Pyrite oxidation is primarily accomplished by microbial catalysis by the indirect mechanism, as defined earlier.

Estimates of field oxidation rates of pyritiferous waste rock or tailings cover a wide range of values, from three orders of magnitude less than the microbial rate to two orders of magnitude greater (Table 6.5). The field rates are primarily based on flux rates of oxygen depletion upon reaction with pyrite in waste rock or tailings. There may be complications with the assumptions made in translating temperature and oxygen profiles into flux rates. The relation between flux rates and actual *in situ* rates of pyrite oxidation may be more difficult to quantify than previously realized. The main problem is estimating the reactive surface area of the sulfides. Other problems may include the consumption of oxygen by processes other than pyrite oxidation, the dependence of temperature profiles on the moisture content, the salinity of the moisture, the temperature dependence of the oxygen consumption rate, climatic variability in pressure and temperature, site heterogeneities, and variations in thermal conductivities of the various waste materials. Averaging hydrologic properties over spatial and temporal intervals may cause inaccurate estimations of flux rates and oxidation rates at some sites.

A direct comparison of the rates of microbial oxidation of aqueous ferrous iron with rates of microbial oxidation of pyrite would be helpful in discerning the rate-controlling step of these processes, but it is difficult to accomplish. Aqueous iron oxidation is expressed as a molar concentration change with respect to time ( $\text{mol L}^{-1} \text{s}^{-1}$ ), whereas pyrite oxidation is a function of surface area and the ratio of pyrite mass to solution volume or porosity ( $\text{mol m}^{-2} \text{s}^{-1}$ ). Two investigations make such a comparison possible: Southam and Beveridge (1992) described bacterial cell densities on pyrite surfaces and Olson (1991) conducted an interlaboratory comparison of pyrite bioleaching rates. Neither study reported pyrite surface area but both reported grain size, so that surface areas may be estimated from the relationship between surface area and grain size for sulfide minerals.

Figure 6.1 depicts the dependence of surface area (in  $\text{cm}^2 \text{g}^{-1}$ ) on grain size for pyrite and other sulfide minerals. The solid line

represents the diameter-to-surface-area relationship for an ideal sphere or cube of pyrite with a density of  $5.0 \text{ g cm}^{-3}$  (see Parks, 1990; Nicholson, 1994). The dashed line is a best fit for cleaned quartz grains from Parks (1990). Two suggestions are evident from Figure 6.1. More recent determinations demonstrate the effect of more carefully sized and cleaned pyrite grains (compare museum pyrite of Braley, 1954, with any of the more recent non-diagenetic pyrite). Secondly, the diagenetic or framboidal pyrite has much more surface area for a given mass than coarse-grained pyrite. Several of the data points on Figure 6.1 lie close to the best fit of Parks (1990), which will be used as a lower limit and as an estimate of the relationship of surface area to grain diameter.

Southam and Beveridge (1992) determined values of  $10^7$  to  $10^9$  cells  $\text{g}^{-1}$  for *Thiobacilli* on surfaces of Lemoine tailings at Chibougamau, Quebec, Canada, by the most probable number method. Their tailings samples were in the size range of 200 mesh and higher, hence about 50 micrometers ( $\mu\text{m}$ ) in diameter or about  $500 \text{ cm}^2 \text{g}^{-1}$  in surface area. A cell count of  $10^8$  cells  $\text{g}^{-1}$  for a surface area of  $500 \text{ cm}^2 \text{g}^{-1}$  works out to  $2 \times 10^5$  cells  $\text{cm}^{-2}$  or  $2 \times 10^9$  cells  $\text{m}^{-2}$  on pyrite surfaces. For a tailings aquifer with 30% porosity and assuming only pure pyrite in the solids, the cell concentration in the slurry becomes  $(1 - \text{porosity})(\text{pyrite density})(\text{cell count}) = (0.7) \times (5 \text{ g ml}^{-1}) \times (10^8 \text{ cells g}^{-1}) = 3.5 \times 10^8$  cells  $\text{ml}^{-1}$ , which is the same concentration of cells in solution that would oxidize aqueous ferrous iron optimally at  $5 \times 10^{-7} \text{ mol L}^{-1} \text{s}^{-1}$  (Silverman and Lundgren, 1959). It is also in the same range of cell concentration found in acid mine waters in the environment (Scala et al., 1982). Therefore, it appears that the observed concentration of *Thiobacilli* on pyrite surfaces would produce aqueous  $\text{Fe}^{\text{III}}$  concentrations of the same order of magnitude as those formed by microbial oxidation of ferrous iron in aqueous solution by free-floating bacteria.

A preferable method of estimating the microbial rate of pyrite oxidation can be obtained from the interlaboratory comparison of pyrite bioleaching rates coordinated by the National Institute of Science and Technology (Olson, 1991). Eight laboratories participated in tests using a standardized method with 1 gram of pyrite from the same source. The pyrite was cleaned and sterilized after sizing to -165/+250 mesh (58 to 91  $\mu\text{m}$ ). Then sample was inoculated with a standard culture of *Thiobacillus ferrooxidans*. From Figure 6.1, the surface area would have been about  $350 \text{ cm}^2 \text{g}^{-1}$ . The reported oxidation rate ( $12.4 \text{ mg Fe L}^{-1} \text{h}^{-1}$  or about  $6 \times 10^{-8} \text{ mol L}^{-1} \text{s}^{-1}$ ) is about an order of magnitude lower than the microbial oxidation rate of aqueous ferrous iron (Table 6.5). Olson

TABLE 6.5—Comparison of abiotic, microbial, and field oxidation rates ( $\text{pH} \approx 2$ ,  $T \approx 25^\circ\text{C}$ ).

Reaction or Process (references)	Abiotic rate	Microbial rate	Field rate
Oxidation of aqueous ferrous iron (Singer and Stumm, 1968; Lacey and Lawson, 1977; Nordstrom, 1985)	$3 \times 10^{-12} \text{ mol L}^{-1} \text{s}^{-1}$	$5 \times 10^{-7} \text{ mol L}^{-1} \text{s}^{-1}$	$5 \times 10^{-7} \text{ mol L}^{-1} \text{s}^{-1}$
Oxidation of pyrite by ferric iron (McKibben and Barnes, 1986; Rimstidt et al., 1994)	$1 \text{ to } 2 \times 10^{-8} \text{ mol m}^{-2} \text{s}^{-1}$		
Oxidation of pyrite by oxygen (McKibben and Barnes, 1986; Olson, 1991)	$0.3 \text{ to } 3 \times 10^{-9} \text{ mol m}^{-2} \text{s}^{-1}$	$8.8 \times 10^{-8} \text{ mol m}^{-2} \text{s}^{-1}$	
Oxidation of waste dump (Ritchie, 1994a, b)			$0.03 \times 10^{-8} \text{ mol m}^{-2} \text{s}^{-1}$
Oxidation of tailings (Elberling et al., 1993)			$20 \text{ to } 60 \times 10^{-8} \text{ mol m}^{-2} \text{s}^{-1}$

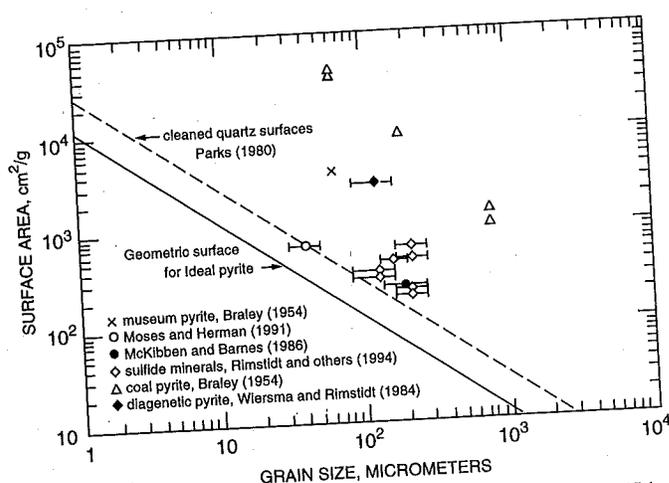


FIGURE 6.1—Surface area versus grain size for pyrite and other sulfide minerals.

(1991) used 1 g of pyrite in 50 ml of solution, so we can calculate the microbial oxidation rate of pyrite as

$$R = \frac{12.4 \text{ mg Fe L}^{-1}\text{h}^{-1}}{56 \text{ mg Fe mmol}^{-1}} \frac{50 \text{ ml}}{(1 \text{ g}) (350 \text{ cm}^2 \text{ g}^{-1})}$$

$$\frac{1 \text{ mol}}{10^3 \text{ mmol}} \frac{1 \text{ L}}{10^3 \text{ ml}} \frac{10^4 \text{ cm}^2}{\text{m}^2} \frac{1 \text{ h}}{3,600 \text{ s}}$$

$$= 8.8 \times 10^{-8} \text{ mol m}^{-2} \text{ s}^{-1} \quad [5]$$

This rate falls squarely between the abiotic oxidation of pyrite by ferric iron and the microbial oxidation of ferrous iron, i.e., within the uncertainty of the data, there is little difference between the oxidation rate of pyrite by ferric iron and the oxidation rate of ferrous iron by *T. ferrooxidans*. The lower rate of microbial pyrite oxidation compared to the oxidation rate of ferrous iron by *T. ferrooxidans* suggests that the heterogeneous reaction is the rate-determining step. We would suggest, however, that the uncertainties on the rates are large enough and the natural variation in the ferrous iron oxidation rate is large enough that there is not a significant difference. Hence, the rate of pyrite oxidation proceeds about as fast as the aqueous ferric iron can be produced from ferrous iron through microbial catalysis.

#### Field oxidation rates

What are the actual oxidation rates of pyritic mine waste in the field? What governs oxidation rates at field sites? Singer and Stumm (1970a) conceived of rates in the conventional sense of chemical kinetics. They described the abiotic oxidation of aqueous ferrous to ferric iron as the "rate-determining step" for the production of acid mine drainage because it is orders of magnitude slower than the oxidation of pyrite by ferric iron. This abiotic iron oxidation rate, however, has limited relevance because iron- and sulfur-oxidizing bacteria are ubiquitous in ground and surface waters, catalyzing aqueous iron and pyrite oxidation by orders of magnitude. Singer and Stumm (1970a, b) recognized

that microbial catalysis greatly speeds up the oxidation of aqueous ferrous iron and that either the complete elimination of oxygen or the use of bactericides would be necessary to eliminate microbial activity. The microbial oxidation of aqueous ferrous iron, under optimal conditions of temperature, oxygen supply, and nutrient availability, is the fastest rate known in the system. This rate provides an upper limit to the pyrite oxidation rate. The lower limit is zero (or negative if sulfate reduction is considered) in the absence of oxygen and water. These extremes of rate cover a wide range over which actual rates may occur in the field.

The effects of sulfide surface area, degree of crystallinity, and purity cannot be overstated. One has only to compare the spontaneous oxidation of "framboidal," "microcrystalline," or "cryptocrystalline" pyrite (see Pabst, 1940; Caruccio, 1970) with untarnished, large, euhedral pyrite cubes that have survived in museums for several centuries to notice the difference in oxidation rates. The signatures of kings, queens, and other dignitaries over the last century can still be seen clearly on an exposed surface of massive chalcopyrite in the Falun mine in Sweden. Caruccio (1970) and Caruccio et al. (1976) pointed out that the grain size and surface area of pyrite in coal deposits has a considerable influence on the production rate of acid mine drainage, with framboidal pyrite being the most reactive. Normalizing reaction rates to unit surface area is now routinely done when reporting dissolution rates of minerals but differences in degree of crystallinity and purity (solid solution substitutions) may also affect reaction rates. Furthermore, the "reactive surface area" may be significantly less than the total measured surface area as measured by standard techniques (Dzombak and Morel, 1990). Reactive surface area refers to those sites on the surface that are actively available to adsorb and chemically bond with aqueous species, and can be reduced by intergranular contact or inclusion within other minerals. Another complication in the field is that not all exposed surface sites are in the flow path of the water, thereby reducing further the reactive surface area.

Field oxidation rates for pyrite are complicated by air and water transport processes, microbial growth kinetics, microbial ecology, organic compounds, temperature gradients, secondary mineral formation, neutralization reactions, climatic patterns, and the site-specific design of mine workings, waste dumps, and tailings. The production rate of acid mine drainage is governed by rates of transport and attenuation processes, which tend to be slower than rates of pyrite oxidation. Some confusion exists in the literature because the distinction between oxidation rates and transport/attenuation rates has not been made clear. In this sense, an obvious parallel or analogy can be made with silicate mineral weathering rates and discrepancies between laboratory and field studies (see Alpers and Nordstrom, 1999, and White and Brantley, 1995).

Ritchie (1994a, b) has reviewed and analyzed the physical factors that pertain to the acid production rate from waste piles. He has shown that the limiting factor is the transport and reaction of oxygen in the waste. Three main processes are dominant in these systems: convection of oxygen, diffusion of oxygen, and the intrinsic oxidation rate which he has calculated for two sites and compared with results compiled from other sites. Ritchie (1994a, b) described the "global oxidation rate" as the overall flux rate of acid mine drainage from a waste dump and the "intrinsic oxidation rate" as the oxygen consumption rate, measured from oxygen profiles in units of  $\text{mol kg}^{-1} \text{ s}^{-1}$  or  $\text{mol m}^{-3} \text{ s}^{-1}$ . Several assumptions are involved in making these computations, including a stoichio-

metric relationship between oxygen consumed and pyrite oxidized (i.e., that oxygen is consumed only by pyrite).

The oxidation of pyrite is a highly exothermic reaction, which can cause thermal air convection in waste dumps and underground mines (Zverev et al., 1983). Air temperatures of 50 to 65°C are commonly achieved in waste-rock piles and copper heap-leach dumps (Cathles and Apps, 1975; Harries and Ritchie, 1981; Cathles, 1994; Ritchie, 1994a) and a water temperature of 47°C was reported from the Richmond Mine at Iron Mountain, California (Alpers and Nordstrom, 1991). Temperature and density gradients resulting from heat generation cause convective air transport, which can be a significant oxygen-supply mechanism (Ritchie, 1994a). Cathles (1994) indicated that convective gas flux driven by thermal gradients was dominant in the well-instrumented Midas Test Dump and other larger dumps at Kennecott's Bingham Canyon Mine (Cathles and Apps, 1975). However, Ritchie (1994a) asserted that the convective flux in a large dump generally applies over a much smaller area than the diffusive oxygen flux.

The relative importance of diffusion vs. convection depends primarily upon the range of air permeability. Ritchie (1994a) suggested a cutoff permeability value of  $10^{-9}$  m<sup>2</sup>. Above this value, convection should dominate and below this value, diffusion should dominate. Ritchie (1994a) also pointed out that he has found the global oxidation rate to be insensitive to changes in the intrinsic oxidation rate. Hence, for unsaturated waste rock, the dominant rate-limiting process should be oxygen diffusion, especially in a newly built waste-rock dump (Ritchie, 1994a). Parts of waste rock piles, usually located near the center, are typically dominated by diffusion whereas the outer edges may be dominated by convection. With time, convective gas transport will penetrate further into the dump as it ages (Ritchie 1994a).

Other factors that affect the ultimate release of acid drainage include the climate, hydrologic variables, mineralogy of the waste materials, physical structure of the waste and geological structure and setting of the mine site, historical evolution of mineral-processing practices, materials used and discarded in mineral processing, geomorphology of the terrain, and vegetation. Discussion of these subjects is beyond the scope of this chapter and can be found in other chapters of this volume or in other review papers. For example, Moore and Luoma (1990) have outlined the sources, transport mechanisms, and sinks for mining and mineral-processing wastes. They use the categories "primary," "secondary," and "tertiary" according to how many times the mining waste has been retransported. A comprehensive overview of tailings problems and their management has been published by Ritcey (1989).

## REDOX CHEMISTRY AND MINERAL SOLUBILITIES

### Eh-pH diagrams and redox chemistry

The traditional graphical method of delineating the stabilities of reduction-oxidation (or redox) species in geochemical systems (and in corrosion systems) has been through the use of Eh-pH (or pe-pH) diagrams. These are a type of master variable diagram where the independent or master variable is pH. Originally developed by Pourbaix (1945, 1966; also see Pourbaix and Pourbaix, 1992; Sato, 1992) to portray equilibrium relationships in metal corrosion systems, they were introduced and championed in the geochemical literature by Krumbein and Garrels (1952), Garrels

(1954) and Garrels and Christ (1965). Hem (1961, 1985), Krauskopf (1967), Krauskopf and Bird (1995) and many others have used the concepts of Eh and pH as a convenient means of representing redox relationships for ions and minerals. The reader is referred to these sources as well as discussions by Stumm and Morgan (1981) and Nordstrom and Munoz (1994) for an introduction to the construction of these diagrams from thermodynamic data.

A pe-pH diagram for the Fe-S-K-O<sub>2</sub>-H<sub>2</sub>O system is shown on Figure 6.2 with the thermodynamic stability fields of several major ions and minerals of iron. The formation and occurrence of jarosite, goethite, and other secondary iron minerals are discussed in the next section. The stability boundary between goethite and jarosite can vary over several units of pH depending on the crystallinity and particle size of these minerals. Metastable phases such as ferrihydrite may form more readily than the thermodynamically stable phase in some conditions, and thus can play an important role in controlling aqueous metal concentrations.

Figure 6.2 indicates that goethite is stable under mildly acidic to basic oxidizing conditions, jarosite is stable under acidic oxidizing conditions, and pyrite is stable under a large range of strongly reducing conditions. Acidity tends to promote dissolution of minerals under a range of redox conditions. Additional iron minerals can be shown on diagrams similar to Figure 6.2, if additional components such as carbonate, silica, phosphate, and uranium are included, but such multi-component diagrams can become very cluttered and most of these additional minerals are not particularly relevant to acid mine waters.

These pe-pH diagrams can be very useful in showing the general stability relations among redox-sensitive ions and minerals but their limitations must be clearly understood:

- 1) The redox chemistry of a solution or a natural water cannot be measured by a simple "Eh" parameter. There is no such thing as a single representative redox potential or an Eh of a water. A measurement of electromotive force (EMF) with a platinum

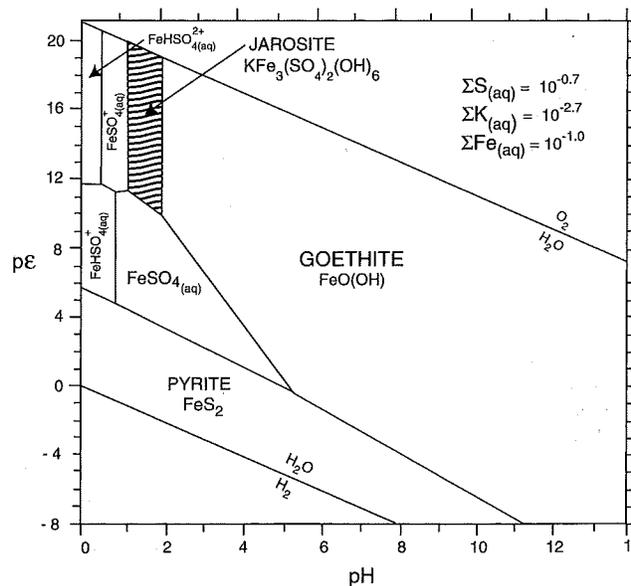


FIGURE 6.2—pe-pH diagram, showing stable solid phases in Fe-S-K-O-H system at 25°C (modified from Alpers et al., 1989).

electrode (converted to Eh by subtracting the reference electrode half-cell potential) for a water sample may or may not reflect an equilibrium potential for a single redox couple but there is no single Eh that represents the water (Thorstenson, 1984; Hostetler, 1984). Hence, Eh measurements may be quantitatively correlated to a specific redox couple such as Fe(II/III) but otherwise they are of little use.

- 2) Redox couples of different elements rarely, if ever, reach equilibrium at temperatures below 100°C. This fact is one of the reasons why a single Eh cannot be assigned to a water sample. Redox disequilibrium is the rule, not the exception. Lindberg and Runnells (1984) showed that when different redox couples are measured in the same water sample, none of them appear to be in equilibrium. The reasons for this are largely kinetic. Electrons transfer much more readily between redox-sensitive ions and surfaces such as electroconductive minerals (most sulfides) and bacteria than with other ions in solution.
- 3) Redox potential measurements respond to electroactive aqueous ions. To be electroactive an ion must have a sufficiently high exchange current density (Bricker, 1982) so that there is no kinetic hindrance to the transfer of electrons. This criterion requires both sufficiently high concentrations of the redox-sensitive ions as well as the lack of kinetic barriers to electron transfer. Only two common elements clearly meet this requirement: iron (II/III) and sulfur (sulfide). All other elements and ions found in natural waters (with the possible exception of uranium and cobalt under unusual circumstances) do not.
- 4) The redox conditions of a water sample are best characterized analytically by determining the concentrations of multiple redox species for each redox-active element in the sample. Acid mine waters are easily analyzed for Fe(II) and Fe(total) (with Fe(III) computed by difference or by direct determination, To et al., 1999) by visible spectrophotometry using a ferrous reagent such as bipyridine, orthophenanthroline, or ferrozine. The more precise and sensitive nature of methods using a colorimetric reagent such as ferrozine make them preferable to atomic absorption or inductively-coupled plasma atomic-emission spectroscopy (Ball and Nordstrom, 1994). Once the concentrations of redox species have been determined then the classification of Berner (1981) can be used to describe the redox chemistry. Berner suggests a practical lower limit of detection as  $10^{-6}$  molar for oxygen, iron, sulfide, and methane. The presence of oxygen classifies a water as "oxic," the absence of oxygen and presence of ferrous iron classifies it as "post-oxic," the presence of sulfide classifies it as "sulfidic," and the presence of methane classifies it as "methanic." This general classification works well for the typical ground water evolving into more reducing conditions with time and depth, but not for acid mine waters. Acid mine waters and other types of surface waters are usually of a mixed redox chemistry and only by determining relevant redox species can you interpret the redox chemistry of the water.

Nordstrom et al. (1979) showed that acid mine waters typically have sufficient iron concentrations to give an equilibrium potential at the platinum electrode for the Fe (II/III) redox couple but that the  $O_2/H_2O$  redox couple was far from equilibrium with respect to the iron couple. Careful analyses of acid mine waters from the Leviathan/Bryant Creek system demonstrate the limits of redox measurements for mine waters even more clearly (Ball and Nordstrom, 1989, 1994). Figures 6.3a and 6.3b compare platinum electrode Eh measurements with Eh values calculated from Fe

(II/III) determinations and speciated with the WATEQ4F code (Ball and Nordstrom, 1991; see Alpers and Nordstrom, 1999). The comparison of measured and calculated Eh on Figures 6.3a and 6.3b shows an excellent correlation for samples with total iron concentrations greater than  $10^{-5}$  m. Most of the deviations are found at the lowest Eh values where the iron concentrations are so low (less than  $10^{-6}$  m) that iron is no longer electroactive. Furthermore, these waters are saturated with atmospheric oxygen so that a mixed potential results from the oxygen competing with the low concentrations of iron. Poor comparisons of calculated and measured Eh are occasionally found at very high iron concentrations and low pH values because of inherent problems with the chemical model under these conditions (see Alpers and Nordstrom, 1999).

### Iron photoreduction

Iron (II) concentrations in oxygenated surface waters have not only been detected but have been found to vary from night to day. The concentrations of Fe (II) reach a peak during midday, at the peak of insolation. The solar radiation reduces both dissolved Fe (III) and colloidal ferric hydroxide in natural waters (Waite and

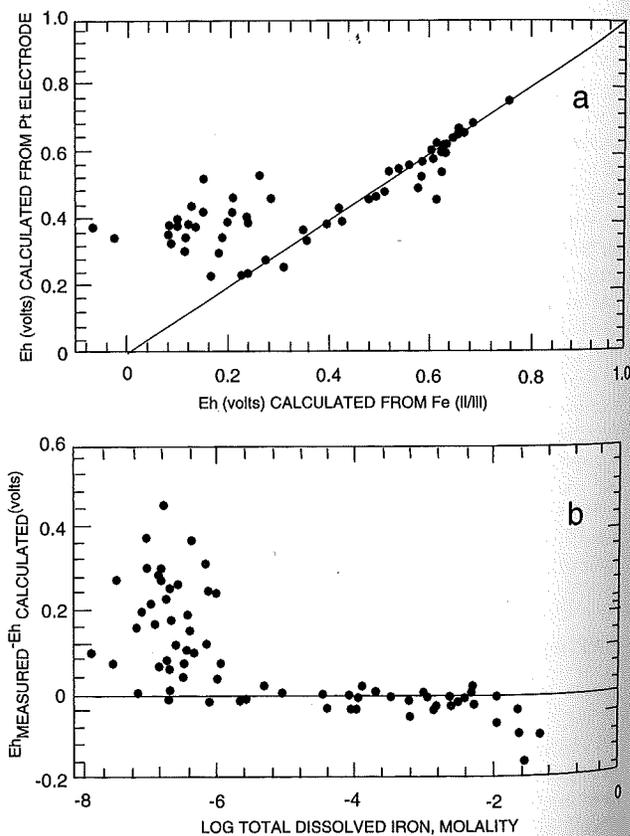


FIGURE 6.3—(a) Comparison of Eh calculated from the Fe (II/III) redox couple to Eh measured with a platinum electrode. (b) Difference between calculated and measured Eh plotted as function of total dissolved iron concentrations in molal units. Data from Leviathan/Bryant Creek watershed, California and Nevada (Ball and Nordstrom, 1989; 1994).

More water  
McK  
daytin  
night  
enhan  
(Le R  
mine v  
dissolv  
quence  
Ostwal  
hydrox  
Alterna  
colloid  
ty for  
1989).  
with re  
with me  
show th  
observed  
daylight  
generation

When  
able, a sp  
of satura  
thermody  
1999). Ni  
been sub  
interpret  
solubilitie  
approach  
Acid r  
aluminum  
sulfate con  
conditions  
erals and  
include jar  
ferric- and  
show two  
one for an  
exerts the  
elements, t  
trend close  
istry reflect  
reached eq  
plateau with  
erally in th  
explained b  
ubility prod  
crystallized  
substitution  
uration coul  
especially in  
sions.

The beha  
indices can t  
in the SI val

## GEOCHEMISTRY OF ACID MINE WATERS

Morel, 1984). The same effect has been found for acid mine waters that have dissolved iron <5 mg/l (McKnight et al., 1988; McKnight and Bencala, 1988). McKnight et al. (1988) found the daytime production of Fe(II) to be nearly 4 times faster than the nighttime oxidation of Fe(II). These results might also be enhanced by light inhibition of iron- and sulfur-oxidizing bacteria (Le Roux and Marshall, 1977). The continual exposure of acid mine waters to the sun promotes recycling of the iron between dissolved and particulate phases and may have important consequences on the sorption of metals. Solar radiation could lead to Ostwald ripening of iron colloids which would increase the iron hydroxide particle size and decrease the reactive surface area. Alternatively, recycling of iron hydroxides and recreation of fresh colloidal surfaces would promote surface area and the opportunity for increased adsorption of metals (McKnight and Bencala, 1989). These effects, however, may only be detectable in streams with relatively small concentrations of iron. Acid mine waters with more typical iron concentrations of 20–1000 mg/l may not show this effect. In wetlands, an opposite effect has been observed, where Fe (II) concentrations reach a minimum during daylight hours; this effect has been attributed to daytime oxygenation by algae (Wieder, 1994).

## Saturation indices (SI) and mineral solubilities

When complete water analyses for the major ions are available, a speciation computation can be done to determine the state of saturation with respect to any particular minerals for which thermodynamic data are available (see Alpers and Nordstrom, 1999). Numerous acid mine waters and tailings pore waters have been subject to these calculations to achieve more quantitative interpretations on the control of metal concentrations by mineral solubilities. Some brief examples of the usefulness of this approach are shown here.

Acid mine waters are characterized by low pH, high iron and aluminum concentrations, high metal concentrations, and high sulfate concentrations. Minerals that might be stable under these conditions should be hydrolyzed iron- and aluminum-sulfate minerals and insoluble metal-sulfate minerals. Prime candidates include jarosite, alunite, barite, anglesite, gypsum, and a suite of ferric- and aluminum-hydroxysulfate compounds. Figures 6.4a-d show two examples of SI values for barite, one for alunite, and one for anglesite. If equilibrium solubility is achieved and if it exerts the dominant control on the concentration of one or more elements, then the SI values should show a linear and horizontal trend close to zero. Such a pattern signifies that the water chemistry reflects the stoichiometry of the given mineral and may have reached equilibrium saturation. As expected, the values tend to plateau with the appropriate stoichiometry of the mineral but generally in the region of supersaturation. This effect might be explained by the particle size effect on solubility because the solubility product constant usually refers to a coarse-grained, well-crystallized material and it might also be due to solid solution substitution of trace components. Some of the apparent supersaturation could also be due to inadequacies in the chemical model, especially in the activity coefficient and stability constant expressions.


The behavior of aluminum and iron as reflected in saturation indices can be seen on Figures 6.5a-d. On Figure 6.5a, a plateau in the SI values for Al(OH)<sub>3</sub> is seen at pH values above about 4.5.

At pH values above 4.5, solubility equilibrium is apparently reached with respect to microcrystalline or amorphous Al(OH)<sub>3</sub> and seems to be maintained at all higher pH values. This phenomenon was pointed out by Nordstrom and Ball (1986) and can be more clearly seen on Figure 6.5b in which the activity of the free aluminum ion is plotted against pH. The rate of aluminum leaching from common minerals at low pH is not generally fast enough relative to the flow rate of surface and ground waters to reach equilibrium with gibbsite. Furthermore, gibbsite solubility is so high at very low pH that it becomes an unstable or metastable phase with respect to other aluminous minerals, especially in the presence of high sulfate concentrations (Nordstrom, 1982b).

When acid mine drainage is diluted by neutral surface waters, the pH and aluminum concentrations eventually reach the gibbsite solubility curve and aluminum concentrations become controlled by one of 3 possibilities: (1) solubility of a solid phase (such as gibbsite), (2) a surface coating control with a stoichiometry similar to gibbsite, or (3) a common aluminosilicate mineral with an exchange ratio of Al<sup>3+</sup> to H<sup>+</sup> of 1:3. A pH of 5 is also equal to the pK<sub>1</sub>, the negative logarithm of the first hydrolysis constant for aluminum, and without hydrolysis the precipitation of hydrolyzed aluminum would not be possible. Hem and Roberson (1990) have shown that the rate of aluminum hydrolysis increases as pH values rise to about 5 so that the hydrolysis kinetics for dissolved aluminum favors the tendency toward equilibrium. Nordstrom et al. (1984) have shown that, when rapid mixing causes precipitation of aluminum in acid mine waters, the solid produced is an amorphous aluminum-hydroxysulfate material that might best be described as an amorphous basaluminite.

Comparable diagrams for iron are shown on Figures 6.5c-d. Apparent supersaturation with respect to ferric hydroxide or ferrihydrite occurs at pH values above about 4. The supersaturation might be explained by substitution of sulfate for hydroxide ions in the ferrihydrite and the formation of a schwertmannite-like phase. Schwertmannite [Fe<sub>8</sub>O<sub>8</sub>(OH)<sub>6</sub>(SO<sub>4</sub>)] was described by Bigam et al. (1990) and Bigam (1994) and is discussed in more detail in a later section of this chapter. The apparent supersaturation with respect to ferric hydroxide might also be explained by the formation of colloidal iron particles that cannot be filtered out by 0.1 micrometer pore size membranes. This apparent supersaturation behavior for ferric hydroxide is commonly seen for both surface waters and ground waters.

In general, the stoichiometry of a phase controlling the solubility of an aqueous constituent can be derived from an appropriately-selected ion-activity plot. For example, if pure ferric hydroxide were controlling the solubility of ferric iron, the reaction



and its log equilibrium constant expression

$$\log K = \log a_{\text{Fe}^{3+}} - 3 \log a_{\text{H}^+} + 3 \log a_{\text{H}_2\text{O}} \quad [6b]$$

would indicate that a plot of Fe<sup>3+</sup> activity versus pH (= -log a<sub>H+</sub>) should have a slope of -3.

The observed slope of -2.4 on Figure 6.5d is clearly inconsistent with solubility control by pure ferric hydroxide having a molar Fe:OH ratio of 1:3 (Nordstrom, 1991). Similar results (a



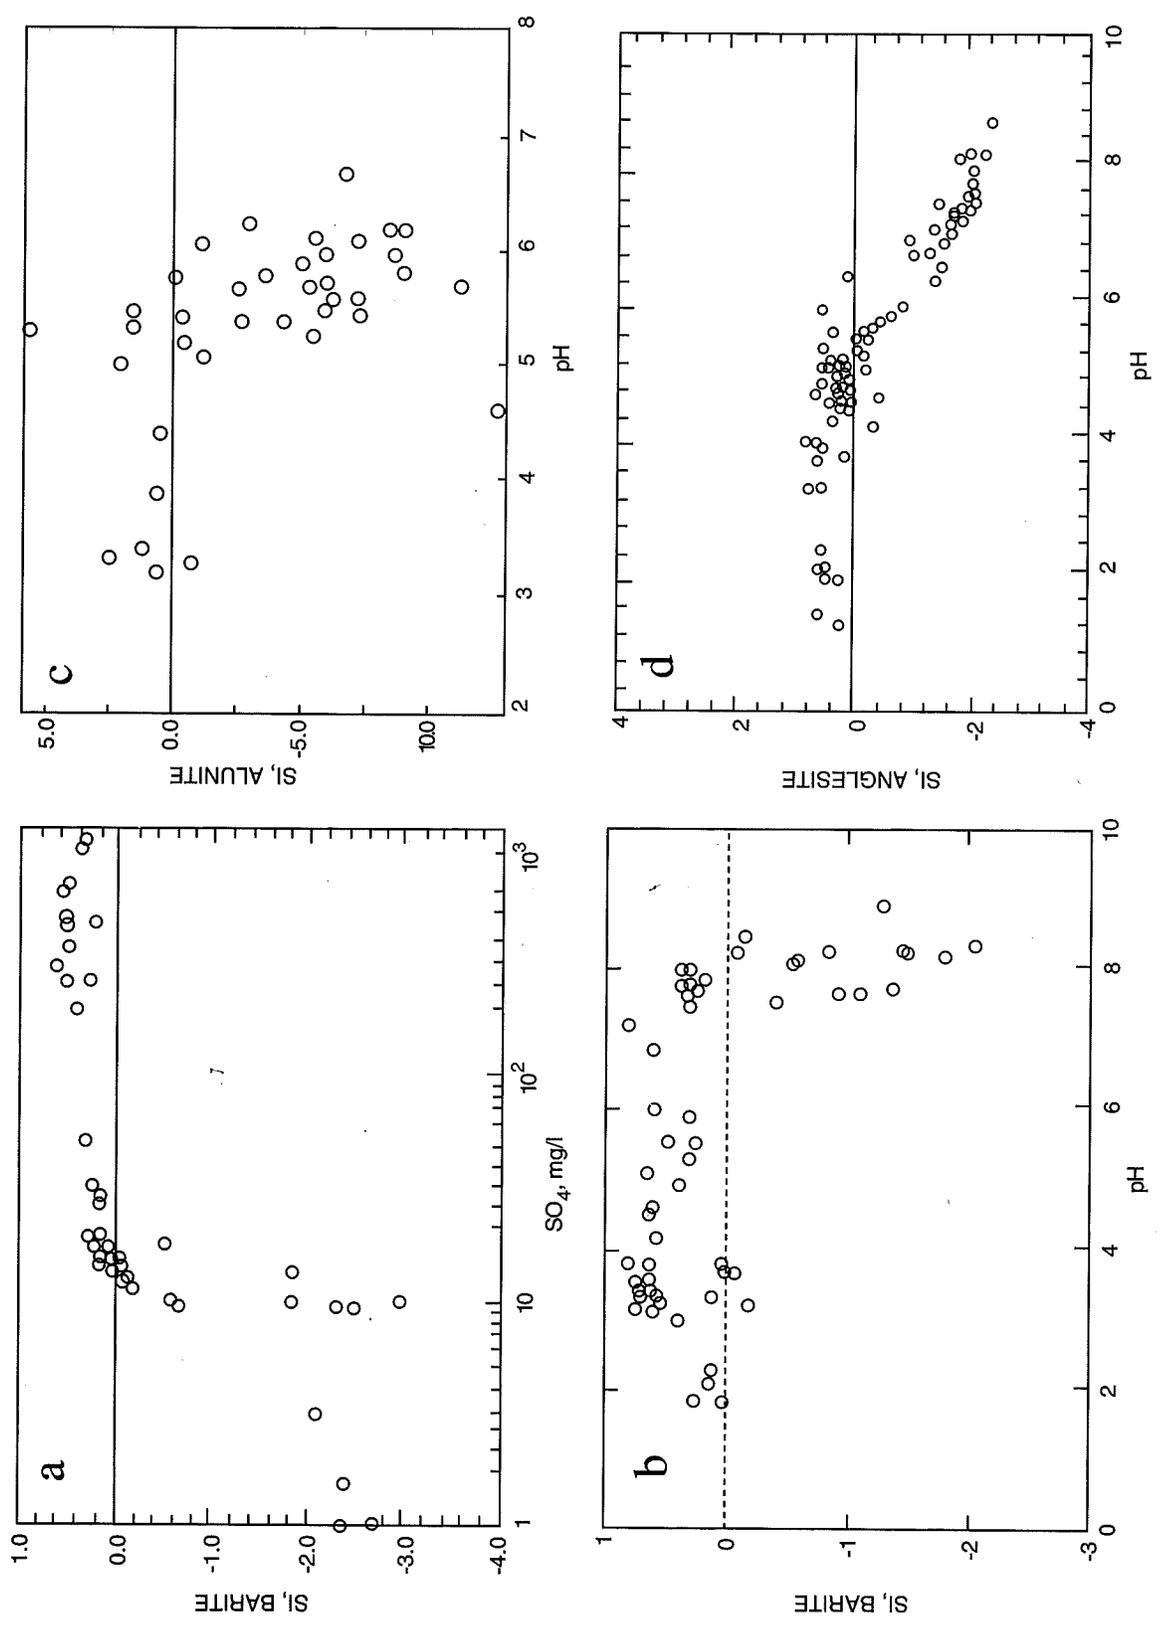


FIGURE 6.4—(a) Saturation indices for barite plotted as a function of sulfate concentration for data from the Osamu Utsumi mine site (Nordstrom et al., 1992). (b) Saturation indices for barite plotted as a function of pH for data from the Levathan mine site (Ball and Nordstrom, 1989, 1994). (c) Saturation indices for alunite plotted as a function of pH for data from the Osamu Utsumi mine site (Nordstrom et al., 1992). (d) Saturation indices for anglesite plotted as function of pH for mine tailings based on data from Blowes (1990).

5



amorphous Al(OH)<sub>3</sub>

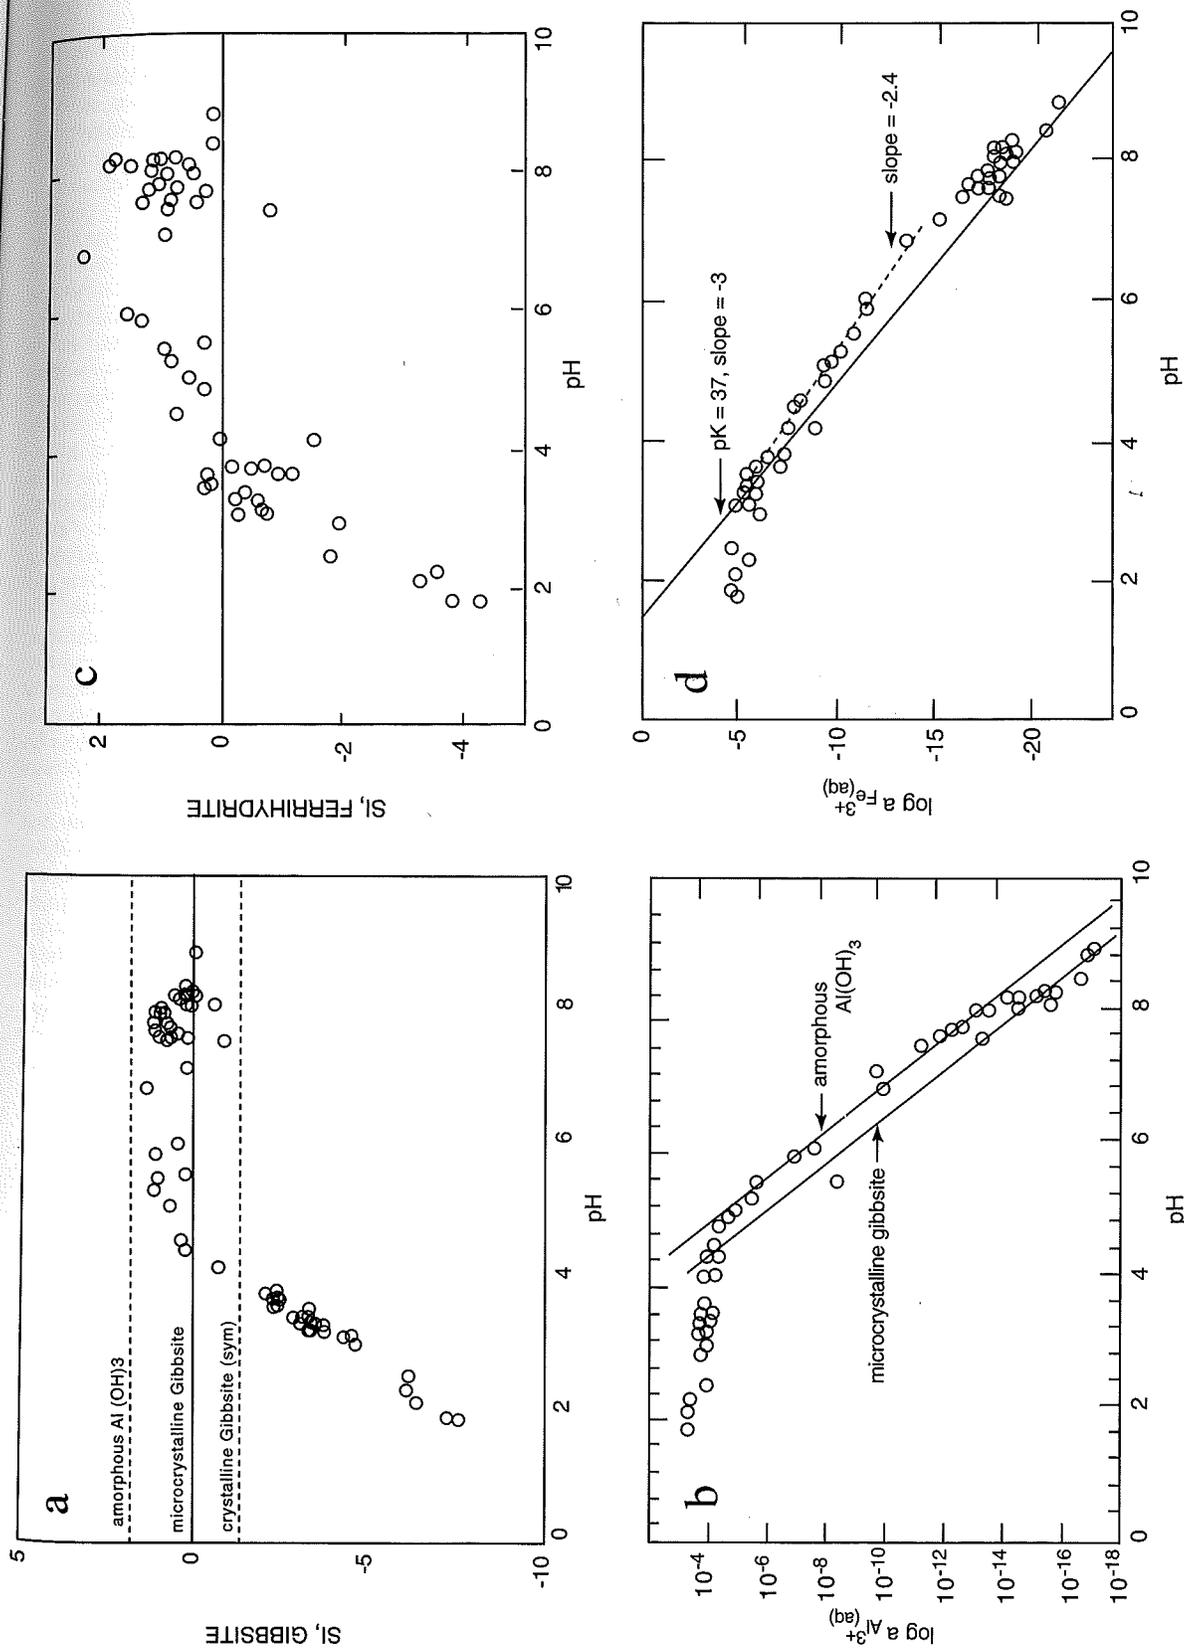

**FIGURE 6.5**—(a) Saturation indices for gibbsite as a function of pH for data from the Leviathan mine site (Ball and Nordstrom, 1989, 1994). (b) Logarithm of the activity of the aluminum ion plotted against pH with the equilibrium solubility lines for amorphous Al(OH)<sub>3</sub> and microcrystalline gibbsite shown (for 25°C). (c) Saturation indices for ferric ion plotted as a function of pH for data from the Leviathan mine site (Ball and Nordstrom, 1989, 1994). (d) Logarithm of the activity of the ferric ion plotted against pH with the equilibrium solubility for freshly precipitated ferric ion shown as a solid line and the best fit for data in the pH range of 3.5 to 7 shown as a dashed line (Nordstrom, 1991). The higher slope from the fitted line suggests non-stoichiometric substitution of sulfate for hydroxide in the precipitating ferric phase.

slope of -2.35) in other surface-water environments and in laboratory experiments were interpreted by Fox (1988) to represent a ferric hydroxide in which nitrate has partially substituted for hydroxide, i.e.,  $\text{Fe}(\text{OH})_{2.35}(\text{NO}_3)_{0.65}$ . Kimball et al. (1994) found a regressed slope of -2.23 from iron data on the acid mine waters of St. Kevin Gulch, Colorado during a neutralization experiment.


The relation on Figure 6.5d could be caused by a reaction involving a hypothetical sulfate-substituted ferric hydroxide such as



with its log equilibrium constant expression

$$\log K = \log a_{\text{Fe}^{3+}} - 2.4 \log a_{\text{H}^+} + 0.3 \log a_{\text{SO}_4^{2-}} + 2.4 \log a_{\text{H}_2\text{O}} \quad [7b]$$

The data on Figure 6.5d do not indicate solubility with schwertmannite of the composition reported by Bigham (1994). The expected slope on a plot of  $a_{\text{Fe}^{3+}}$  vs. pH showing schwertmannite solubility equilibrium would be -2.75, based on the reaction



and its log equilibrium constant expression

$$\log K = \log a_{\text{Fe}^{3+}} - 2.75 \log a_{\text{H}^+} + 0.125 \log a_{\text{SO}_4^{2-}} + 1.75 \log a_{\text{H}_2\text{O}} \quad [8b]$$

Bigham (1994) reported that schwertmannite is associated with mine drainage ranging in pH from about 2.5 to 6, and is most commonly associated with "typical" mine effluents with pH from 3 to 4. Bigham (1994) also noted that ferrihydrite is associated with mine drainage in the pH range of about 5 to 8. The data on Figure 6.5d with slope of -2.4 span from pH of about 4 to about 7. This suggests that the apparent stoichiometry is more likely to represent a sulfate-substituted ferrihydrite, schwertmannite, or other hydrous ferric oxide with a molar Fe:OH ratio of 1:2.4. It is also possible that mixtures of different iron mineral phases are precipitating from these waters over this pH range and the slope is not clearly resolvable into a particular reaction. This complex chemistry needs more detailed work to quantitatively relate water chemistry to iron colloids and other precipitates.

In his thesis work (Blowes, 1990) and in subsequent papers (Blowes and Jambor, 1990; Blowes et al., 1991; Blowes and Ptacek, 1994; Ptacek and Blowes, 1994), Dr. Blowes and his colleagues have mapped the saturation indices for siderite, calcite, goethite, ferrihydrite, gypsum, melanterite, and anglesite with depth in tailings piles at Heath Steele, New Brunswick, and Waite Amulet, Quebec. Similar detailed hydrogeochemical studies are being completed at Kidd Creek and Copper Cliff, Ontario. In some of these studies, two aqueous models are compared: the ion association model and the specific ion interaction (Pitzer) model. For some minerals, the comparisons of saturation indices computed by both models are nearly identical, but for others the Pitzer model gives SI values that are more consistently at equilibrium. The mineralogy at these sites has also been studied in detail and it fully sup-

ports the interpretations based on the Pitzer model saturation index computations, which are more appropriate for solutions of high ionic strength. The strengths and limitations of these aqueous models as applied to acid mine waters are discussed by Alpers and Nordstrom (1999).

## SECONDARY MINERALS

Acid mine waters are highly reactive solutions that can dissolve most primary minerals and form a wide variety of secondary minerals. The understanding of secondary mineral formation has important consequences for environmental management of mining wastes. Insoluble secondary minerals with large surface areas can effectively immobilize many of the major contaminants in acid mine waters, providing an important attenuation and detoxifying mechanism. Soluble secondary minerals also slow down toxic metal mobility but only temporarily until the next rainstorm or snowmelt event. Hence, the occurrence and properties of these minerals are equal in importance to the water chemistry and pyrite oxidation rates for the interpretation of chemical processes occurring in mine waste environments.

For the purpose of this discussion, secondary minerals are defined as those that form during weathering. A further distinction can be made between secondary minerals formed by natural processes prior to human disturbance and those formed after the commencement of mining, exploration, or other human activity. In this chapter we refer to these effects as pre-mining and post-mining.

There are clear similarities in the geochemistry of pre- and post-mining weathering processes, as well as in the nature of the associated aqueous solutions and secondary minerals; however, there are also some important differences. Mining tends to cause a dramatic increase in the rate of sulfide oxidation reactions because of rapid exposure of large volumes of reactive material to atmospheric oxygen. Blasting and crushing of ores and waste material leads to a considerable increase in the available surface area of reactive minerals. Hydrologic changes caused by mine dewatering in both underground and open-pit mines may expose large volumes of rock to atmospheric oxygen.

The type of secondary mineral formed depends on the composition of the water, the type and composition of the primary minerals, the temperature, and the moisture content. The initial minerals that precipitate in certain environments tend to be poorly crystalline, metastable phases that may transform to more stable phases over time. Therefore, those secondary minerals that are preserved in the geologic record in leached cappings, gossans, and zones of secondary enrichment may be quite different in their mineralogy compared with the secondary minerals that form over shorter time frames in mine drainage settings.

Four important processes lead to the formation of secondary minerals from acid mine waters: (1) iron oxidation and hydrolysis, (2) reaction of acid solutions with sulfides, gangue minerals, and country rock, (3) mixing of acid mine waters with more dilute waters, and (4) evaporation of acid mine waters.

A suite of Fe(III) minerals can form from iron oxidation and hydrolysis. Many of these phases have very low solubility, fall in the colloidal size range (less than 1.0 micrometer), and can adsorb or coprecipitate significant quantities of trace elements. Reaction of acid mine waters with country rock and some gangue minerals, such as calcite and dolomite, will cause neutralization and precip-

itation of metals. Evaporation concentrates the acid, sulfate, and metals found in acid mine waters until they reach mineral saturation, forming efflorescent sulfate salts, a common feature associated with oxidizing sulfide-bearing mine wastes.

This section describes five categories of secondary minerals:

(1) metal oxides, hydroxides, and hydroxysulfates, (2) soluble sulfates, (3) less-soluble sulfates, (4) carbonates, and (5) secondary sulfides. For each category, one or more lists of mineral formulas are provided (Tables 6.6–6.13). These lists are intended to include the more common secondary minerals in each category, but it should not be inferred that all minerals on the lists have been demonstrated to control metal concentrations in acid mine waters on a large scale. A discussion of the secondary minerals that are likely to control metal concentrations in acid mine waters is included as the final part of this section.

### Metal oxides, hydroxides, and hydroxysulfates

Most divalent and trivalent metals exhibit amphotericism, i.e., they produce a solubility minimum at circum-neutral pH values with enhanced solubilities under both acidic and basic conditions. Figure 6.6 shows both the amphoteric solubilities of ferrihydrite, gibbsite, and the hydroxides of Cu, Zn, Fe(II), and Cd at 25°C, as well as the importance of pH in controlling the dissolved concentration of these metals. Different metals reach their minimum solubility at different pH values. This phenomenon provides the basis for the removal of metals during rapid neutralization of acid mine drainage by alkaline treatment (lime, limestone, or sodium hydroxide). The pH-specific solubility minimum varies for each metal, causing a different efficiency of metal removal for neutralization to a given pH (Barton, 1978). At metal concentrations greater than  $10^{-6}$  molar, metal hydroxides should precipitate in the following sequence with increasing pH: Fe(III), Pb, Al, Cu, Zn, Fe(II), and Cd. This sequence is also very closely followed by the pH-dependent sequence of adsorption of metals on hydrated ferric oxide surfaces (Dzombak and Morel, 1990).

**Iron**—The minerals discussed in this section are ferrous ( $\text{Fe}^{\text{II}}$ ) and ferric ( $\text{Fe}^{\text{III}}$ ) oxides, hydroxides, and hydroxysulfates. The list of minerals in Table 6.6 includes some that are not observed to form readily during weathering, but are included for completeness and for analogy with other metals, especially aluminum (Table 6.7; discussed in a later subsection).

Ferrous hydroxide is considerably more soluble than its ferric equivalent at a given pH (Fig. 6.6) and the former appears only rarely in nature.  $\text{Fe}(\text{OH})_2$ , when slightly oxidized, takes on a green appearance and is also known as "green rust." It occurs when  $\text{Fe}^{\text{II}}$ -rich solutions are mixed with a highly alkaline solution and allowed to oxidize slightly. This material has been prepared in the laboratory and Ponnampetuma et al. (1967) have argued effectively for its occurrence in nature, but it is not credited as a mineral because it is unstable and poorly characterized.

Ferrihydrite is a poorly crystalline form of hydrous ferric oxide/hydroxide that seems to be the first phase to form upon neutralization of Fe(III)-bearing solutions at low temperature, surficial conditions. For many years, this phase was considered to be "amorphous  $\text{Fe}^{\text{III}}(\text{OH})_3$ ." However, careful examination by X-ray diffraction (XRD) and Mössbauer spectroscopy (e.g., Schwertmann, 1985a) has revealed that this material is commonly a poorly crystalline substance with a range of structural order, yielding an XRD pattern with two to six peaks (Carlson and

Schwertmann, 1981). Ferrihydrite formed in mining environments tends to have two to four XRD peaks, and is associated with waters having pH values of 5 to 8 (Bigham, 1994). The "two-line" ferrihydrite is also referred to as "proto-ferrihydrite" (Chukhrov et al., 1973), although this is not an approved mineral name. At least two formulas for ferrihydrite have been reported:  $\text{Fe}_5\text{HO}_8 \cdot 4\text{H}_2\text{O}$  (Towe and Bradley, 1967) and  $\text{Fe}_2\text{O}_3 \cdot 2\text{FeO}(\text{OH}) \cdot 2.6\text{H}_2\text{O}$ , a structural formula based on infrared spectroscopy (Russell, 1979). The latter formula can also be expressed as  $\text{Fe}_2\text{O}_3 \cdot 1.8\text{H}_2\text{O}$ .

Hematite ( $\text{Fe}_2\text{O}_3$ ) and goethite [ $\text{FeO}(\text{OH})$ ] are the most common and most stable forms of ferric oxide and oxyhydroxide, respectively. The solubility and stability of hematite and goethite are sufficiently close that grain size and surface Gibbs free energy have important influence on the phase relations. With regard to coarse-grained minerals, goethite appears to be stable relative to hematite at temperatures below about 80°C (Langmuir, 1969, 1971, 1972). However, fresh goethite nearly always occurs in a particle size less than 0.1 micrometers in soils and sediments, so it is unstable relative to coarser-grained hematite under the geologic conditions that form sedimentary rocks. This conclusion is supported by both laboratory (Berner, 1969, 1971) and field evidence (Walker, 1967, 1974, 1976). Both goethite and hematite have slow growth kinetics at surficial temperatures, so the initial solid products from the hydrolysis of  $\text{Fe}^{\text{III}}_{(\text{aq})}$  are poorly crystalline, metastable phases such as microcrystalline goethite or ferrihydrite. Thus, kinetic factors play an important role in determining the nature of the ferric precipitate(s) that may form as a result of ferrous iron oxidation and hydrolysis. Some progress has been made in understanding these factors and how they influence the distribution of hematite and goethite in soil profiles (Kämpf and Schwertmann, 1982; Schwertmann, 1985a, b). Ferrihydrite is known to convert to hematite if conditions are maintained between pH 5 and 9. Outside of this range, most of the ferrihydrite dissolves and reprecipitates as goethite (Schwertmann and Murad, 1983). Other factors may influence the formation of these phases, such as humidity, Al-content (Tardy and Nahon, 1985), grain size, and the presence of trace elements (Torrent and Guzman, 1982; Thornber, 1975). The preparation and characterization of iron oxides has been reviewed by Schwertmann and Cornell (1991).

Relatively little work has been done to understand the factors that influence the distribution of hematite and goethite in the weathered zone of mineral deposits. Leached cappings and gossans represent the *in situ* oxidized equivalents of porphyry copper and massive sulfide deposits, respectively. The mineralogy of iron in the oxidized zones of these deposits is dominated by hematite, goethite, and jarosite [ $(\text{K}, \text{Na}, \text{H}_3\text{O})\text{Fe}^{\text{III}}_3(\text{SO}_4)_2(\text{OH})_6$ ]. The early literature (e.g., Locke, 1926; Tunell, 1930) documented the observation that "deep maroon to seal brown" hematitic iron oxide tends to remain in rocks after oxidation of supergene chalcocite-bearing ores, which form as the enrichment product of copper-iron sulfide protodes. Increasing amounts of goethite and jarosite relative to hematite correlate with progressively higher ratios of pyrite to chalcocite at depth (Loghry, 1972; Alpers and Brimhall, 1989). The texture of the iron oxides (or "limonites") also reflects a systematic change from indigenous (in original sulfide cavities) to transported (outside sulfide cavities and in fractures) with increasing relative pyrite content prior to oxidation (Blanchard, 1968; Loghry, 1972).

Aluminum has been observed to substitute into goethite and

TABLE 6.6—Iron oxide, hydroxide, and hydroxysulfate minerals.

Mineral	Formula
Hematite	$\alpha\text{-Fe}_2\text{O}_3$
Maghemite	$\gamma\text{-Fe}_2\text{O}_3$
Magnetite	$\text{FeO}\cdot\text{Fe}_2\text{O}_3$
Goethite	$\alpha\text{-FeO(OH)}$
Akaganéite	$\beta\text{-FeO(OH,Cl)}$
Lepidocrocite	$\gamma\text{-FeO(OH)}$
Feroxyhyte	$\delta\text{-FeO(OH)}$
Ferrihydrite	$\text{Fe}_5\text{HO}_8\cdot 4\text{H}_2\text{O}$ or $\text{Fe}_2\text{O}_3\cdot 2\text{FeO(OH)}\cdot 2.6\text{H}_2\text{O}$
Schwertmannite	$\text{Fe}^{\text{III}}_8\text{O}_8(\text{SO}_4)(\text{OH})_6$
Fibroferrite	$\text{Fe}^{\text{III}}(\text{SO}_4)(\text{OH})\cdot 5\text{H}_2\text{O}$
Amarantite	$\text{Fe}^{\text{III}}(\text{SO}_4)(\text{OH})\cdot 3\text{H}_2\text{O}$
Jarosite	$\text{KFe}^{\text{III}}_3(\text{SO}_4)_2(\text{OH})_6$
Natrojarosite	$\text{NaFe}^{\text{III}}_3(\text{SO}_4)_2(\text{OH})_6$
Hydronium Jarosite	$(\text{H}_3\text{O})\text{Fe}^{\text{III}}_3(\text{SO}_4)_2(\text{OH})_6$
Ammonium Jarosite	$(\text{NH}_4)\text{Fe}^{\text{III}}_3(\text{SO}_4)_2(\text{OH})_6$
Argentojarosite	$\text{AgFe}^{\text{III}}_3(\text{SO}_4)_2(\text{OH})_6$
Plumbojarosite	$\text{Pb}_{0.5}\text{Fe}^{\text{III}}_3(\text{SO}_4)_2(\text{OH})_6$
Beaverite	$\text{PbCuFe}^{\text{III}}_2(\text{SO}_4)_2(\text{OH})_6$
Chromate jarosite	$\text{KFe}^{\text{III}}_3(\text{CrO}_4)_2(\text{OH})_6$

TABLE 6.7—Aluminum oxide, hydroxide, and hydroxysulfate<sup>1</sup> minerals.

Mineral	Formula
Corundum	$\alpha\text{-Al}_2\text{O}_3$
[ $\gamma$ -Alumina] <sup>1</sup>	$\gamma\text{-Al}_2\text{O}_3$
Diaspore	$\alpha\text{-AlO(OH)}$
Boehmite	$\gamma\text{-AlO(OH)}$
Gibbsite	$\gamma\text{-Al(OH)}_3$
Bayерite	$\alpha\text{-Al(OH)}_3$
Doyleite	$\text{Al(OH)}_3$
Nordstrandite	$\text{Al(OH)}_3$
Alunite	$\text{KAl}_3(\text{SO}_4)_2(\text{OH})_6$
Natroalunite	$\text{NaAl}_3(\text{SO}_4)_2(\text{OH})_6$
[Hydronium Alunite] <sup>2</sup>	$(\text{H}_3\text{O})\text{Al}_3(\text{SO}_4)_2(\text{OH})_6$
Ammonium Alunite	$(\text{NH}_4)\text{Al}_3(\text{SO}_4)_2(\text{OH})_6$
Osarizawaite	$\text{PbCuAl}_2(\text{SO}_4)_2(\text{OH})_6$
Jurbanite	$\text{Al}(\text{SO}_4)(\text{OH})\cdot 5\text{H}_2\text{O}$
Basaluminitite	$\text{Al}_4(\text{SO}_4)(\text{OH})_{10}\cdot 5\text{H}_2\text{O}$
Hydro-basaluminite	$\text{Al}_4(\text{SO}_4)(\text{OH})_{10}\cdot 12\text{-}36\text{H}_2\text{O}$

<sup>1</sup>  $\gamma$ -Alumina is a synthetic compound, used as a catalyst in industry. Surface properties are reviewed by Goldberg et al. (1995).  
<sup>2</sup> Hydronium alunite has not been found in nature and therefore is not considered a mineral.

TABLE 6.8—Some other oxide and hydroxide minerals and native metals.

Mineral	Formula
Pyrolusite	$\text{MnO}_2$
Hausmannite	$\text{Mn}_3\text{O}_4$
Manganite	$\gamma\text{-MnO(OH)}$
Pyrochroite	$\text{Mn(OH)}_2$
Todorokite	$(\text{Mn}^{\text{II}},\text{Ca},\text{Mg})\text{Mn}^{\text{IV}}_3\text{O}_7\cdot \text{H}_2\text{O}$
Takanelite	$(\text{Mn}^{\text{II}},\text{Ca})\text{Mn}^{\text{IV}}_4\text{O}_9\cdot \text{H}_2\text{O}$
Rancieite	$(\text{Ca},\text{Mn}^{\text{II}})\text{Mn}^{\text{IV}}_4\text{O}_9\cdot 3\text{H}_2\text{O}$
Native copper	$\text{Cu}$
Tenorite	$\text{CuO}$
Cuprite	$\text{Cu}_2\text{O}$
Delafossite	$\text{CuFeO}_2$
Bunsenite	$\text{NiO}$
Theophrastite	$\text{Ni(OH)}_2$
Jamborite	$(\text{Ni}^{\text{II}},\text{Ni}^{\text{III}},\text{Fe})(\text{OH})^2(\text{OH,S,H}_2\text{O})$
Native silver	$\text{Ag}$
Native gold	$\text{Au}$
Native mercury	$\text{Hg}$
Montroydite	$\text{HgO}$
Massicot litharge	$\text{PbO}$
Plattnerite	$\text{PbO}_2$

TABLE 6.9—Selected soluble iron-sulfate minerals.

Mineral	Formula
Melanterite	$\text{Fe}^{\text{II}}\text{SO}_4\cdot 7\text{H}_2\text{O}$
Siderotil	$\text{Fe}^{\text{II}}\text{SO}_4\cdot 5\text{H}_2\text{O}$
Rozenite	$\text{Fe}^{\text{II}}\text{SO}_4\cdot 4\text{H}_2\text{O}$
Szomolnokite	$\text{Fe}^{\text{II}}\text{SO}_4\cdot \text{H}_2\text{O}$
Halotrichite	$\text{Fe}^{\text{II}}\text{Al}_2(\text{SO}_4)_4\cdot 22\text{H}_2\text{O}$
Roemerite	$\text{Fe}^{\text{II}}\text{Fe}^{\text{III}}_2(\text{SO}_4)_4\cdot 14\text{H}_2\text{O}$
Coquimbite	$\text{Fe}^{\text{III}}_2(\text{SO}_4)_3\cdot 9\text{H}_2\text{O}$
Kornelite	$\text{Fe}^{\text{III}}_2(\text{SO}_4)_3\cdot 7\text{H}_2\text{O}$
Rhomboclase	$(\text{H}_3\text{O})\text{Fe}^{\text{III}}(\text{SO}_4)_2\cdot 3\text{H}_2\text{O}$
Ferricopiapite	$\text{Fe}^{\text{III}}_5(\text{SO}_4)_6\text{O(OH)}\cdot 20\text{H}_2\text{O}$
Copiapite	$\text{Fe}^{\text{II}}\text{Fe}^{\text{III}}_4(\text{SO}_4)_6(\text{OH})_2\cdot 20\text{H}_2\text{O}$
Voltaite	$\text{K}_2\text{Fe}^{\text{II}}_5\text{Fe}^{\text{III}}_4(\text{SO}_4)_{12}\cdot 18\text{H}_2\text{O}$

## GEOCHEMISTRY OF ACID MINE WATERS

TABLE 6.10—Some other soluble sulfate minerals.

Mineral	Formula
Epsomite	$MgSO_4 \cdot 7H_2O$
Hexahydrate	$MgSO_4 \cdot 6H_2O$
Goslarite	$ZnSO_4 \cdot 7H_2O$
Bianchite	$ZnSO_4 \cdot 6H_2O$
Gunningite	$ZnSO_4 \cdot H_2O$
Zincosite	$ZnSO_4$
Gypsum	$CaSO_4 \cdot 2H_2O$
Anhydrite	$CaSO_4$
Morenosite	$NiSO_4 \cdot 7H_2O$
Retgersite	$NiSO_4 \cdot 6H_2O$
Boothite	$CuSO_4 \cdot 7H_2O$
Chalcanthite	$CuSO_4 \cdot 5H_2O$
Chalcocyanite	$CuSO_4$
Alunogen	$Al_2(SO_4)_3 \cdot 17H_2O$
Mirabilite	$Na_2SO_4 \cdot 10H_2O$
Thenardite	$Na_2SO_4$

TABLE 6.11—Some less-soluble sulfate and hydroxysulfate minerals.

Mineral	Formula
Celestite	$SrSO_4$
Anglesite	$PbSO_4$
Barite	$BaSO_4$
Radium sulfate	$RaSO_4$
Antlerite	$Cu_3(SO_4)(OH)_4$
Brochantite	$Cu_4(SO_4)(OH)_6$
Langite, Wroewolfeite	$Cu_4(SO_4)(OH)_6 \cdot 2H_2O$
Posnjakite	$Cu_4(SO_4)(OH)_6 \cdot H_2O$

TABLE 6.12—Some carbonate minerals.

Mineral	Formula
Rhombohedral	
Calcite	$CaCO_3$
Magnesite	$MgCO_3$
Siderite	$FeII CO_3$
Rhodochrosite	$MnCO_3$
Smithsonite	$ZnCO_3$
Otavite	$CdCO_3$
Gaspéite	$NiCO_3$
Sphaerocobaltite	$CoCO_3$
Orthorhombic	
Aragonite	$CaCO_3$
Strontianite	$SrCO_3$
Witherite	$BaCO_3$
Cerrusite	$PbCO_3$
Double	
Dolomite	$CaMg(CO_3)_2$
Kutnahorite	$Ca(Mn, Mg)(CO_3)_2$
Ankerite	$Ca(Fe^{II}, Mg, Mn)(CO_3)_2$
Minrecordite	$CaZn(CO_3)_2$
Hydroxyl	
Malachite	$Cu_2(CO_3)(OH)_2$
Azurite	$Cu_3(CO_3)_2(OH)_2$
Hydrocerussite	$Pb_3(CO_3)_2(OH)_2$
Hydrozincite	$Zn_5(CO_3)_2(OH)_6$
Aurichalcite	$(Zn, Cu)_5(CO_3)_2(OH)_6$

TABLE 6.13—Supergene and diagenetic sulfide minerals.

Mineral	Formula
Supergene sulfide minerals	
Chalcocite	$Cu_2S$
Djurleite-I	$Cu_{1.965}S$
Djurleite-II	$Cu_{1.934}S$
Digenite	$(Cu, Fe)_9S_5$
Anilite	$Cu_7S_4$
Geerite	$Cu_8S_5$
Spionkopite	$Cu_{39}S_{28}$
Yarrowite	$Cu_9S_8$
Blue-remaining covellite	$Cu_{(1+x)}S$
Covellite	$CuS$
Violarite	$Ni_2FeS_4$
Millerite	$NiS$
Diagenetic sulfide minerals	
Amorphous FeS	FeS with coprecipitated Zn, Cd, Mn, Cu, Ni, As)
Mackinawite	$(Fe, Ni)_9S_8$
Smythite	$(Fe, Ni)_9S_{11}$
Greigite	$Fe^{II}Fe^{III}_2S_4$
Pyrite, marcasite	$FeS_2$

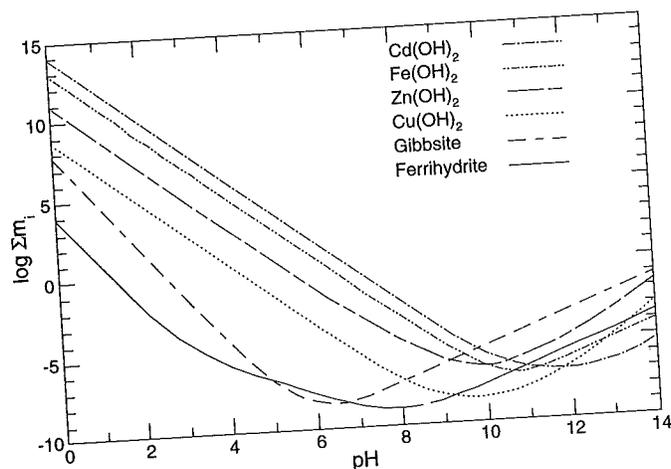


FIGURE 6.6—Solubility curves for gibbsite, ferrihydrite, and the hydroxides of Cu, Zn, Fe (II), and Cd shown as a function of pH.

hematite in certain soils, to maximum concentrations of 33 mole %  $\text{AlO}(\text{OH})$  and 14 mole %  $\text{Al}_2\text{O}_3$ , respectively (Yapp, 1983; Tardy and Nahon, 1985; Schwertmann, 1985a). Although both iron and aluminum are highly soluble in acid mine waters, we are unaware of any data showing significant aluminum substitution in iron oxide minerals formed in mine drainage settings. Adsorption and precipitation of hydrolyzable metal ions tends to take place at pH values near the first hydrolysis pK for that metal. The first pK of hydrolysis for  $\text{Fe}^{\text{III}}$  is 2.2, and for Al is 5.0, so the coprecipitation of Al in hydrous  $\text{Fe}^{\text{III}}$  oxides formed at pH values less than about 4.5 is unlikely. This fundamental difference between iron and aluminum chemistry leads to spatial and temporal separation of precipitating phases of hydrolyzed iron and aluminum in oxidizing mineral deposits and mine waters.

Schwertmannite is a poorly crystalline iron-hydroxysulfate mineral that has recently been discovered to be a fairly common phase in ochres formed in mine drainage environments (Bigham et al., 1990; Bigham, 1994; Murad et al., 1994). The structure of schwertmannite appears to be related to that of akaganéite, an iron oxyhydroxide with essential chloride (Bigham, 1994; Murad et al., 1994). A combination of powder XRD and Mössbauer spectroscopy is necessary for definitive identification of schwertmannite (Murad et al., 1994). Schwertmannite or other sulfate-substituted, hydrous ferric oxides are most likely to control ferric iron solubility in acid mine drainage, as discussed previously (Fig. 6.5d).

**Jarosite-alunite**—The jarosite-alunite group of minerals shares a common crystal structure and stoichiometry, with many possible compositional substitutions. The general jarosite-alunite formula is  $\text{AB}_3(\text{SO}_4)_2(\text{OH})_6$  where the B sites are occupied by  $\text{Fe}^{\text{III}}$  to form jarosites and by Al to form alunites. Endmember formulas for some of the more common jarosite group minerals are given in Table 6.6, and the more common alunite endmember formulas in Table 6.7. The A site is occupied either by a monovalent cation or by a divalent cation alternating with a vacancy to maintain charge balance. The most common occupants of the A site in order of abundance in natural alunites and jarosites are  $\text{K}^+ > \text{Na}^+ > \text{H}_3\text{O}^+$  (Kubisz, 1960, 1961, 1964; Brophy and Sheridan, 1965; Scott, 1987). The pure potassium-iron endmember is jarosite and the pure potassium-aluminum endmember is alunite. Pure end-

members are rare; jarosites and alunites formed during weathering and those synthesized at temperatures below  $100^\circ\text{C}$  tend to contain considerable hydronium ion in the A site (Dutrizac and Kaiman, 1976; Dutrizac, 1983; Alpers et al., 1989, 1992; Stoffregen and Alpers, 1992). Hydronium jarosite has been reported as a naturally occurring mineral (Kubisz, 1970), whereas hydronium alunite has not yet been found in nature. The hydronium endmembers can be synthesized readily (Ripmeester et al., 1986). Solid solutions between alunite and jarosite have also been synthesized (Parker, 1962; Brophy et al., 1962), but thermodynamic relations for iron-aluminum substitution have not been established and mineral compositions intermediate to alunite and jarosite are not commonly observed. This effect is probably caused by the different first hydrolysis constants for  $\text{Fe}^{\text{III}}$  ( $\text{p}K_1 = 2.2$ ) and Al ( $\text{p}K_1 = 5.0$ ), as discussed earlier regarding hematite and goethite. Further summaries on substitutional properties of the alunite-jarosite group were presented by Scott (1987), Stoffregen and Alpers (1987, 1992), and Alpers et al. (1989). Information on the relation between the crystallographic, chemical, and isotopic properties of alunite and jarosite was reported by Alpers et al. (1992) and by Stoffregen and Alpers (1992).

**Aluminum**—A list of some aluminum oxide, hydroxide, and hydroxysulfate minerals and their formulas is provided in Table 6.7. Thermodynamic properties of aluminous minerals have been reviewed, evaluated, and tabulated by Hemingway and Sposito (1996). Properties of aqueous aluminum ions and polymers have been reviewed and evaluated by Nordstrom and May (1996) and Bertsch and Parker (1996), respectively.

Solubility and stability relations among gibbsite, alunite, basaluminite, jurbanite, and alunogen were delineated by Nordstrom (1982b). In acid mine waters, aluminum-sulfate and -hydroxysulfate minerals become more stable than common soil minerals such as gibbsite and kaolinite. At pH values less than about 5.5 (depending on sulfate and potassium activities) gibbsite becomes unstable relative to alunite (Nordstrom, 1982b). Below pH values of about 4, jurbanite becomes most stable. Alunogen becomes stable only at pH values below 0 (i.e., hydrogen ion activities greater than 1.0). Some of these stability relationships need to be revised in light of the work by Reardon (1988), who applied the Pitzer approach to aluminum-sulfate solutions, and the recent revisions on thermodynamic properties of aluminum minerals and aqueous species (Hemingway and Sposito, 1996; Nordstrom and May, 1996). Despite its apparent thermodynamic stability, jurbanite tends to occur only rarely as a post-mining efflorescence (Anthony and MacLean, 1976), and has not been found commonly as a mineral precipitate from acid mine waters. We suspect that jurbanite has little significance as a solubility control in spite of the near-zero SI values commonly found, for three reasons:

- 1) recalculation of the solubility field is needed, based on revised thermodynamic properties for auxiliary species that may show the stability field of jurbanite to be at lower pH values,
- 2) jurbanite appears to be an efflorescent salt and most efflorescent salts in mine wastes form at pH values much less than 4,
- 3) other factors seem to govern aluminum and sulfate concentrations in acid mine waters (Nordstrom and Ball, 1986).

The behavior of aluminum in acid mine waters (and stream waters affected by acid rain) has been described by Nordstrom and Ball (1986). For waters with pH values less than 4.5 to 5.0, dissolved aluminum tends to behave as a conservative ion in surface waters, whereas for waters with pH values above 5.0, solubility control of dissolved aluminum by microcrystalline to amorphous

$\text{Al}(\text{OH})_3$  is apparent, as described previously (Figs. 6.5a and 6.5b). Such control may be caused by equilibrium solubility or by a surface reaction involving the exchange of  $\text{Al}^{3+}$  for  $3\text{H}^+$  on an aluminous surface. May and Nordstrom (1991) showed that a characteristic change of behavior for aluminum from conservative to non-conservative is common for a wide variety of sulfate-acidified waters. When the pH in an acid mine water increases to 5 or higher because of rapid mixing with circumneutral, dilute water, an aluminum-hydroxysulfate compound precipitates immediately. This precipitate is usually white, and is most commonly amorphous to XRD, electron diffraction, transmission electron microscopy, and scanning electron microscopy (Nordstrom et al., 1984). It seems to be of fairly constant composition, similar to the amorphous basaluminite reported by Adams and Rawajfih (1977). It has been observed many times by people working on acid mine waters and mine wastes. The occurrence of the white, aluminous precipitate at pH values of 5 or above is so consistent that one can frequently use its presence to predict the pH of the water when a pH electrode and meter are unavailable. A classic example is the caved portal at the Gem Mine (often called the Paradise portal), in the San Juan Mountains of southwestern Colorado, which has been discharging mine water continuously with a pH of  $5.5 \pm 0.3$  for more than 30 years. This site has a striking white precipitate, affectionately known as "white death," that consists primarily of aluminum, sulfate, and water (Nordstrom et al., 1984); anomalous concentrations of lanthanide elements have been found in this precipitate (Carlson-Fosch, 1991; Nordstrom et al., 1995).

As with the iron minerals, thermodynamic stability relations among the aluminum minerals and their kinetic rates of formation can vary greatly, depending upon sulfate concentration, salinity, pH, particle size, and temperature. Precipitation rates for some of these aluminous minerals may be sluggish so that the equilibrium conditions are not often reached in surface waters. In soil and ground waters, longer residence times favor solubility control by mineral-solution equilibria.

**Other metals**—Native metals, oxides, and hydroxides of several other metals such as copper, nickel, manganese, silver, gold, and mercury may occur from the weathering and oxidation of primary sulfide minerals (Table 6.8). These minerals tend to occur as residual products in oxidized zones (gossans and leached cap-pings), where many pore volumes of water have reacted with the formerly mineralized rocks. It is unlikely that these phases exert solubility control on large volumes of water, but rather they are likely to form during dry periods when isolated microenvironments may reach saturation with a given native metal, oxide or hydroxide. The absence of discrete trace-metal-bearing oxides and hydroxides in most oxidized mine wastes suggests that other mechanisms, such as adsorption or coprecipitation with hydrous iron oxides, limit the concentrations of dissolved trace metals in mining environments (see Smith, 1999).

The behavior of nickel in tailings impoundments and acid-mine-drainage precipitates illustrates that the fate of trace metals in mine drainage settings is generally tied to that of the major elements, particularly iron. Mineralogical analysis and microanalysis by Jambor and co-workers as part of a study on the Copper Cliff tailings area at Sudbury, Ontario, has indicated that nickel tends to occur dispersed in hydrous iron oxides forming alteration rims on pentlandite and nickeliferous pyrrhotite, rather than as discrete nickel oxide or hydroxide phases (Alpers et al., 1994b). Overall,

the bulk of the nickel liberated by oxidation of these sulfides ends up in goethite, a part of the nickel remains in solution and is transported from the site of oxidation, a small amount is taken up by vermiculite and associated mixed-layer silicates that replace biotite, and some may occur as secondary violarite (see Supergene and Diagenetic Sulfides section, below), which is expected to occur but has not yet been found in the Copper Cliff tailings (Alpers et al., 1994b).

Copper oxides, particularly tenorite and cuprite, are known to form in the oxidized zone of sulfide deposits and are indicative of low pyrite content and/or a high wallrock neutralization capacity (Loghry, 1972; Anderson, 1982). The behavior of copper in tailings impoundments and waste-rock piles is similar to that of nickel; in that discrete secondary copper oxides are rarely formed; rather the copper is either transported away from the oxidized zone in solution, is fixed in other secondary phases such as sulfates, carbonates, or silicates, or is coprecipitated and/or adsorbed to hydrous iron oxides.


Manganese oxides and hydroxides are known to form from acid mine drainage, often at considerable distance from the source(s) of sulfide oxidation and acid formation. Krauskopf (1957) pointed out that the redox and hydrolysis properties of iron and manganese are such that they sometimes behave differently under changing conditions of oxidation and reduction. Hem (1978, 1980) considered the effects of manganese oxidation and disproportionation on the coprecipitation of other trace metals with manganese oxides. He demonstrated the effect of manganese on the coprecipitation of  $\text{CoO}(\text{OH})$  (Hem et al., 1985) and on the precipitation of zinc as hetaerolite,  $\text{ZnMn}_2\text{O}_4$ , at  $25^\circ\text{C}$  (Hem et al., 1987). He further discussed the possibility that low-temperature "ferrite" compounds may be responsible for the low concentrations of trace metals found in uncontaminated natural waters. Hem also made many other significant contributions to our understanding of the hydrolysis and precipitation of trace metals (Hem, 1985).

Manganese oxides are actively precipitating at Pinal Creek, Arizona, in the Globe-Miami mining district, and so provide an opportunity for study of geochemical processes controlling manganese solubility in a mine drainage setting. At Pinal Creek, an alluvial ground-water aquifer was contaminated by acidic recharge (pH about 2.7) from copper mining and smelting activities (Eychaner, 1991). After neutralization by interaction with the alluvial material, the contaminated ground-water emerges at near-neutral pH in a perennial reach of Pinal Creek, about 15 km down-gradient from the acid source, at which point manganese-rich crusts have developed in the streambed. Chemical and XRD analyses (Lind, 1991) suggest that the manganese occurs as a mixture of two related hydrous oxides, takanelite and rancieite (see Table 6.8), plus an Mn-bearing carbonate, probably kutnohorite (see Table 6.12). The overall oxidation state of the manganese in the less-than-75 micrometer size fraction of the Pinal Creek precipitates was 3.65 (Lind, 1991). To test the hypothesis that neutralization of acidic Mn-bearing water would lead to formation of similar Mn-bearing minerals, titrations were made of Mn-rich ground waters from the Pinal Creek area with a 0.1 molar NaOH solution with and without  $\text{CO}_2$  present; these experiments yielded hausmannite (which aged to manganite), kutnohorite, and a mixed Ca-Mn species similar to todorokite (Hem and Lind, 1993).

### Soluble sulfates

Soluble sulfate minerals, often occurring as efflorescent salts, are common in mines, on mine tailings and waste rock, and on sulfide mineralization exposed to the air. These phases store metals and sulfate during dry periods and dissolve readily during flushing events, a process that has an important influence on temporal variations of metals in surface waters affected by mine wastes.

**Iron sulfates**—The most common efflorescent minerals are hydrated iron sulfate salts (Table 6.9). Based both on laboratory experiments of evaporating acid mine waters as well as field observations, the hydrated iron sulfate minerals seem to follow a paragenetic sequence as shown below (Buurman, 1975; Nordstrom, 1982a; C. Maenz, written commun., 1995).

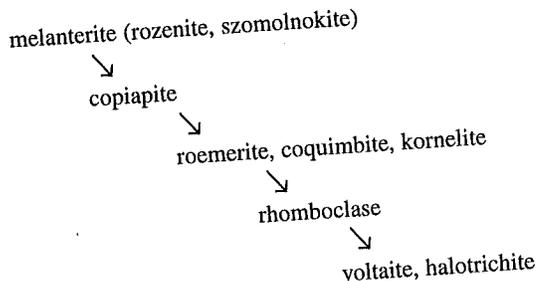

The formation of melanterite as the first phase to precipitate from the evaporation of many acid mine waters is consistent with the preponderance of aqueous ferrous iron in these waters. Reactions (2) and (3) indicate that aqueous ferrous iron and sulfate are the initial products of pyrite oxidation, and it is these ions that combine to form melanterite. The remaining iron sulfates in the generalized paragenetic sequence form as the solutions evaporate and the ferrous iron oxidizes to ferric; however, a simple progression from ferrous to ferric salts is not observed because of differences in solubility among the various salts and the influence of other major elements which substitute to a variable degree for divalent and trivalent iron, such as copper and zinc for ferrous iron and aluminum for ferric iron.

Copper tends to partition into melanterite in preference to zinc (Alpers et al., 1994a). The result of this partitioning is a tendency toward higher ratios of zinc/copper in residual solutions as melanterite and related phases form in the dry season, and then lower ratios of zinc/copper as the salts are flushed in the wet season (Alpers et al., 1994a).

Another important role of the soluble iron sulfates is to store acidity and oxidation potential in the form of hydronium and ferric ions. The mineral rhomboclase is essentially a solid form of sulfuric acid plus ferric sulfate. Although generally considered rare, large quantities of rhomboclase and other iron sulfate salts were found at Iron Mountain, California, in inactive underground mine workings within a volcanogenic massive sulfide deposit (Alpers and Nordstrom, 1991). The salts were observed to be actively forming from waters with pH values from 1 to less than -3 (Nordstrom et al., 1991; Alpers et al., 1991; Nordstrom and Alpers, 1999). Rhomboclase may be present in trace amounts in other settings where acid waters evaporate to dryness, providing a storage mechanism for hydronium ions. Other ferric-sulfate and mixed ferrous-ferric-sulfate salts have been found associated with mine wastes and spoils in numerous localities including coal and metal mines (e.g., Zdrov and McCandlish, 1978a, b; Zdrov et

al., 1979; Cravotta, 1994; Plumlee et al., 1995).

Dissolution of these salts can create large quantities of very acid mine waters. Flooding of underground mines and mine wastes as a remedial measure may not result in short-term improvements in water quality because the ferric salts will dissolve and the ferric iron will hydrolyze (if pH is above 2.2), providing an oxidant that will cause continued sulfide oxidation (e.g., Cravotta, 1994).

**Other metal sulfates**—There are a large number of additional metal sulfates that occur as efflorescent minerals in weathered mineral deposits and mining environments. Some of the more common ones are listed in Table 6.10. One of the important aspects of these salts is that they are a solid form of acid mine drainage that is stored until the next rainstorm event when the salts can quickly dissolve and be transported to a drainage system. Dagenhart (1980) demonstrated that the concentrations of copper, zinc, iron, and aluminum increase sharply during the rising limb of the discharge as rain dissolves and flushes efflorescent salts from oxidizing tailings into a receiving stream. This phenomenon is probably common at mined sites and may be an important factor in the association of fish kills during periods of high runoff, especially after a significant dry period.

### Less-soluble sulfates

Although there are a great many metal sulfate minerals of low solubility known to occur, the most common ones are barite, celestite, and anglesite (Table 6.11). These are likely to provide solubility controls for the concentrations of barium, strontium, and lead (see previous section on mineral solubilities, Fig. 6.4). Their low solubilities tend to immobilize these elements in the environment and make them less bioavailable than many of the other hazardous metals at mine sites. In particular, lead concentrations in acid mine drainage and tailings pore waters appear to be controlled at relatively low levels by anglesite solubility (e.g., Blowes and Jambor, 1990).

### Carbonates

Many carbonate minerals occur as either primary or secondary minerals in mine wastes. Examples are given in Table 6.12. Carbonates may originate as an accessory gangue mineral that accompanies the mineral deposit and mine waste (mine working residuum, waste piles, tailings), as an amended material for neutralization, or as a secondary product from weathering of wastes or amendments. Carbonate minerals are important as neutralizers of acid in mine drainage (Blowes and Ptacek, 1994). Siderite forms as a secondary phase in tailings impoundments where calcite reacts with Fe(II)-rich solutions (Ptacek and Blowes, 1994). The hydroxyl-bearing carbonates in Table 6.13 form as secondary minerals in the oxidation of Zn-Cu-Pb ores and related mine wastes.

### Supergene and diagenetic sulfides

The supergene enrichment process that affects primary sulfide ores may also be a factor in redistribution of metals in mine waste environments, particularly tailings impoundments. Supergene alteration of copper- and nickel-sulfide deposits has resulted in

## GEOCHEMISTRY OF ACID MINE WATERS

enrichment of ore grades by oxidation and leaching of metals in the unsaturated zone above the water table followed by transport of metals to a zone of more reducing conditions where secondary sulfide minerals are formed (Anderson, 1982; Alpers and Brimhall, 1989). A list of some supergene copper and nickel minerals is given in Table 6.13. The two compositions for djurleite are based on the investigation by Potter (1977). An example of active supergene enrichment in a tailings impoundment is the presence of secondary covellite near the depth of active oxidation at Waite Amulet, Ontario (Blowes and Jambor, 1990).

Diagenetic processes affect mine drainage geochemistry in areas where reducing conditions can lead to sulfate reduction and the formation of secondary sulfides. The sulfides are generally insoluble, so this represents a plausible geochemical mechanism for metal fixation in mine workings, anoxic wetlands, and lake bottoms, if reducing conditions are maintained. Iron is commonly the most abundant transition metal and therefore is the most likely metal to combine with  $H_2S$  to produce secondary sulfides in environments affected by mine drainage. Other divalent metals present will also tend to form secondary sulfides, as indicated in Table 6.13. The relative solubility of metal sulfides, starting from the most soluble, is:  $MnS > FeS > NiS \sim ZnS > CdS \sim PbS > CuS > HgS$  (DiToro et al., 1991).

#### A summary of mineralogic controls on metal concentrations

As a guide to the aqueous geochemistry for acid mine waters, we have compiled a list of minerals in Table 6.14 that might be important in governing metal concentrations. This list is drawn from our experience in modeling and interpreting mine water chemistry and is meant as a guide rather than a strict protocol. The two columns in Table 6.14 show those minerals most likely to have a solubility control and those less likely but possible.

### SUMMARY

Physical, chemical, and biological processes all play important roles in the production, release, mobility, and attenuation of contaminants in acid mine waters. Physical aspects include the geology (geomorphology, structure, petrology, geophysical features), the hydrology (water budget, porosity, permeability, flow direction, flow rate, dispersion, mixing, surface transport characteristics), and the effects of mining and mineral processing. The specific processes that have been studied and found to contribute to the overall phenomenon of acid mine water geochemistry are:

- 1) pyrite oxidation
- 2) oxidation of other sulfides
- 3) oxidation and hydrolysis of aqueous iron and other elements
- 4) neutralizing capacity of gangue minerals and country rock
- 5) neutralizing capacity of bicarbonate-buffered waters
- 6) oxygen transport
- 7) fluid transport of water and water vapor
- 8) form and location of permeable zones relative to flow paths
- 9) climatic variations (diel, storm events, seasonal)
- 10) evaporation, efflorescence, redissolution
- 11) heating by conduction and radiation (due to a variety of exothermic reactions including pyrite oxidation, dissolution of soluble salts, and dilution of concentrated acid)


- 12) temperature
- 13) microbial catalysis of reaction rates
- 14) microbial sorption and uptake of metals
- 15) mineral precipitation and dissolution during transport
- 16) adsorption and desorption of metals during transport
- 17) photoreduction of iron
- 18) organic complexing
- 19) microenvironmental processes (surface films, microbial films, mineral coatings)

TABLE 6.14—Minerals whose solubilities might control metal concentrations in mine waters.

Solubility equilibrium likely	Solubility equilibrium difficult but possible
alunogen	alunite
anglesite	ankerite
barite	antlerite
basaluminite (amorphous)	atacamite, paratacamite
calcite	azurite
cerussite	bronchantite
chalcantite	chrysocolla
epsomite	goethite
ferrhydrite	hemimorphite
gibbsite (amorphous to microcrystalline)	hematite
goslarite	hydrozincite
gypsum	jarosite
halotrichite-pickeringite	kaolinite
manganese oxides	kutnohorite
melanterite	malachite
otavite	natroalunite
rhodochrosite	natrojarosite
schwertmannite	plumbojarosite
scorodite	
siderite	
silica (microcrystalline)	
smithsonite	
witherite	

Many of these processes are represented schematically in Figure 6.7. Perhaps the most important factors affecting the production of acid mine waters are the amount, concentration, grain size, and distribution of pyrite present in a mine, tailings, or waste pile. The rate of oxidation can vary depending on the accessibility of air, moisture, and microbes to the pyrite surfaces and the neutralizing capacity of available buffering materials. These complex geochemical processes can be modeled with either equilibrium or kinetic principles to estimate the result of pyrite oxidation, carbonate buffering, and silicate hydrolysis (see Chapter 14 on geochemical modeling). Modeling calculations of this type have been done for pyritic rocks and waters of different initial compositions (e.g., Lichtner, 1994). Modeling calculations, however, are well-educated guesses. There will always be inadequate data and contentions ambiguities in the conclusions. The advantage of modeling is that it can take into account some of the complex interactions between hydrology, geochemistry, geology, and other site characteristics as well as performing database management. This advantage is a major step beyond various acid-base accounting, static, and kinetic tests for which comparison, evaluation, and agreement is lacking (White and Jeffers, 1994).

The geochemistry of acid mine waters is a complex subject that draws upon many technical disciplines. Although considerable

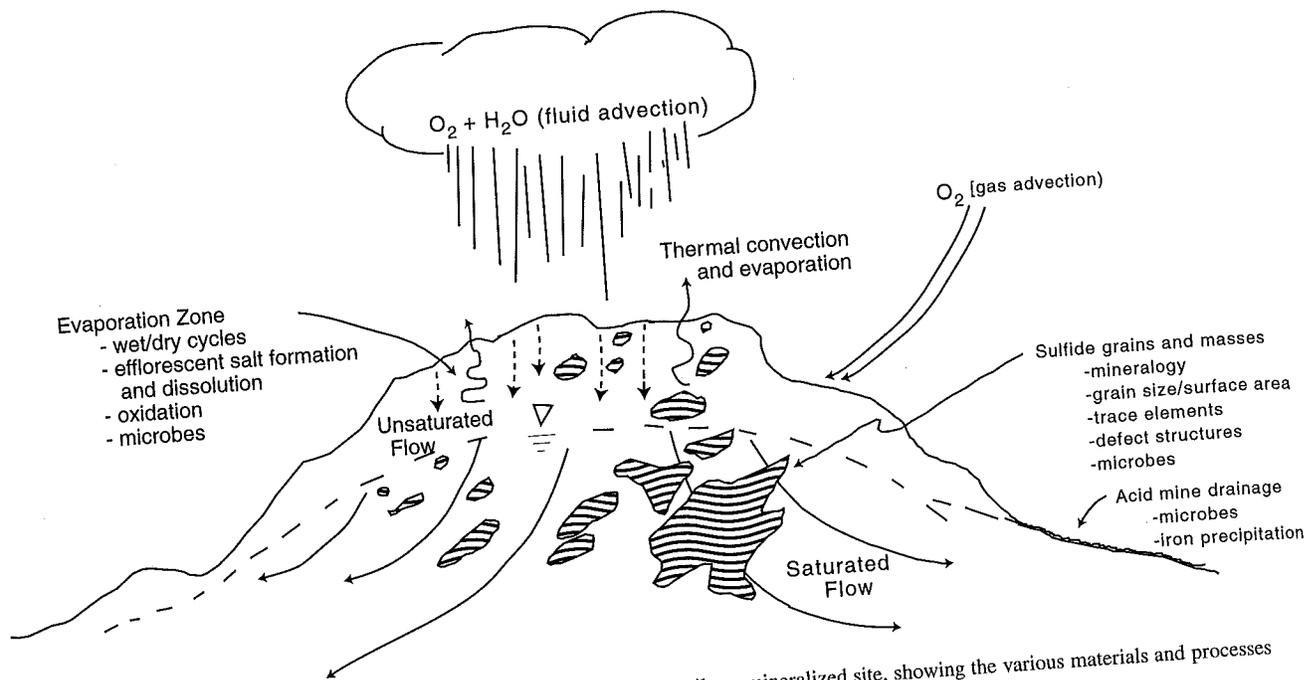

**FIGURE 6.7**—Schematic diagram depicting a hypothetical tailings or waste pile or mineralized site, showing the various materials and processes involving reaction and flow.

research has been accomplished on this subject, surprises and new challenges continue to appear. Inadequate recognition of the importance of the multi-disciplinary nature of the subject can result in inappropriate or even dangerous remediation measures. In this arena, as with many other environmental problems, the quick fixes are rare; complexity and heterogeneity of this environment along with high-cost, high-risk options are the rule. A cautious, phased, and iterative approach to both site characterization and remediation would seem most warranted.

**ACKNOWLEDGMENTS**—We are deeply indebted to Geoff Plumlee and the Society of Economic Geologists for inviting us to participate in this short course and for showing enormous patience with our unanticipated delays. The reviewers, David Blowes, Briant Kimball, Geoff Plumlee, Teresa Rogers, and Katie Walton-Day were most helpful in catching errors and mistakes and in asking for important points of clarification. Their comments led to significant improvements in the manuscript. Finally, we would like to acknowledge all the students and colleagues with whom we have shared both sweat and joy in attempting to demystify some of the secrets of mine water geochemistry.

## REFERENCES

- Adams, F. and Rawajfih, Z., 1977, Basaluminite and alunite—A possible cause of sulfate retention by acid soils: *Soil Science Society of America Journal*, v. 41, pp. 686–692.
- Agricola, G., 1546, *De Natura Fossilium* (Textbook of Mineralogy), translated by Bandy, M.C., and Bandy, J.A., 1955: Geological Society of America Spec. Pub. No. 63, 240 pp.
- Agricola, G., 1556, *De Re Metallica*, translated by Hoover, H.C., and Hoover, L.H., 1950: Dover Publications, New York, 638 pp.
- Alpers, C.N., and Brimhall, G.H., 1989, Paleohydrologic evolution and geochemical dynamics of cumulative supergene metal enrichment at La Escondida, Atacama Desert, northern Chile: *Economic Geology*, v. 84, pp. 229–255.
- Alpers, C.N., and Nordstrom, D.K., 1991, Geochemical evolution of extremely acid mine waters at Iron Mountain, California—Are there any lower limits to pH?; in *Proceedings, 2nd Internl Conference on the Abatement of Acidic Drainage*, Montreal, Quebec, Canada: CANMET, Ottawa, Sept. 16–18, 1991, v. 2, pp. 324–342.
- Alpers, C.N., and Nordstrom, D.K., 1999, Geochemical modeling of water-rock interactions in mining environments; in Plumlee, G.S., and Logsdon, M.J. (eds.), *The Environmental Geochemistry of Mineral Deposits, Part A. Processes, Techniques, and Health Issues*: Society of Economic Geologists, *Reviews in Economic Geology*, v. 6A, pp. 289–323.
- Alpers, C.N., Nordstrom, D.K., and Ball, J.W., 1989, Solubility of jarosite solid solutions precipitated from acid mine waters, Iron Mountain, California, U.S.A.: *Sciences Géologiques Bulletin*, v. 42, pp. 281–298.
- Alpers, C.N., Meinz, C., Nordstrom, D.K., Erd, R.C., and Thompson, J.M., 1991, Storage of metals and acidity by iron-sulfate minerals associated with extremely acidic mine waters from Iron Mountain, California [abs.]: *Geological Society of America Annual Meeting, Abstracts with Programs*, v. 23, no. 5, p. A383.
- Alpers, C.N., Rye, R.O., Nordstrom, D.K., White, L.D., and King, B.-S., 1992, Chemical, crystallographic, and isotopic properties of alunite and jarosite from acid hypersaline Australian lakes: *Chemical Geology*, v. 96, pp. 203–226.
- Alpers, C.N., Nordstrom, D.K., and Thompson, J.M., 1994a, Seasonal variations of Zn/Cu ratios in acid mine waters from Iron Mountain, California; in Alpers, C.N., and Blowes, D.W. (eds.), *Environmental Geochemistry of Sulfide Oxidation*: American Chemistry Society Symposium Series 550, Washington, D.C., pp. 324–344.
- Alpers, C.N., Blowes, D.W., Nordstrom, D.K., and Jambor, J.L., 1994b, Secondary minerals and acid mine-water chemistry; in Jambor, J.L., and Blowes, D.W. (eds.), *The Environmental Geochemistry of Sulfide Mine-Wastes*: Mineralogical Association of Canada, Nepean, Ontario, Short Course Handbook, v. 22, pp. 247–270.

- Anderson, J.A., 1982, Characteristics of leached capping and techniques of appraisal; in Titley, S.R. (ed.), *Advances in Geology of the Porphyry Copper Deposits, Southwestern North America*, Tucson: University of Arizona Press, Tucson, pp. 275-295.
- Anthony, J.W., and MacLean, W.J., 1976, Jurbanite, a new post-mine alunite mineral from San Manuel, Arizona: *American Mineralogist*, v. 61, pp. 1-4.
- Appalachian Regional Commission, 1969, Acid mine drainage in Appalachia: Report to the President, 126 pp.
- Ash, S.H., Felegy, E.W., Kennedy, D.O., and Miller, P.S., 1951, Acid mine drainage problems—Anthracite region of Pennsylvania: U.S. Bureau of Mines Bulletin 508, 72 pp.
- Ball, J.W., and Nordstrom, D.K., 1989, Final revised analyses of major and trace elements from acid mine waters in the Leviathan mine drainage basin, California and Nevada—October 1981 to October 1982: U.S. Geological Survey Water-Resources Investigations Report 89-4138, 46 pp.
- Ball, J.W., and Nordstrom, D.K., 1991, User's manual for WATEQ4F, with revised thermodynamic data base and test cases for calculating speciation of major, trace, and redox elements in natural waters: U.S. Geological Survey Open-File Report 91-183, 189 pp., plus diskette.
- Ball, J.W., and Nordstrom, D.K., 1994, A comparison of simultaneous plasma, atomic absorption, and iron colorimetric determinations of major and trace constituents in acid mine waters: U.S. Geological Survey Water-Resources Investigations Report 93-4122, 151 pp.
- Barton, P., 1978, The acid mine drainage; in Nriagu, J.O. (ed.), *Sulfur in the Environment, Part II. Ecological Impacts*: John Wiley and Sons, New York, pp. 313-358.
- Basolo, F., and Pearson, R.G., 1967, *Mechanisms of inorganic reactions—A study of metal complexes in solution*, 2nd ed.: John Wiley and Sons, New York, 701 pp.
- Beck, J.V., 1977, Chalcoite oxidation by concentrated cell suspensions of *Thiobacillus ferrooxidans*; in Schwartz, W. (ed.), *Conference Bacterial Leaching 1977*: GBF, Verlag Chemie, Weinheim, pp. 119-128.
- Bennett, J.C., and Tributsch, H., 1978, Bacteria leaching patterns on pyrite crystal surface: *Journal of Bacteriology*, v. 134, pp. 310-326.
- Bergholm, A., 1955, Oxidation of pyrite: *Jernkontorets Annalen*, v. 139, pp. 531-549.
- Berner, R.A., 1969, Goethite stability and the origin of red beds: *Geochimica et Cosmochimica Acta*, v. 33, pp. 267-273.
- Berner, R.A., 1971, *Principles of chemical sedimentology*: McGraw-Hill Book Company, New York, 240 pp.
- Berner, R.A., 1981, A new geochemical classification of sedimentary environments: *Journal of Sedimentary Petrology*, v. 51, pp. 359-365.
- Bertsch, P.M. and Parker, D.R., 1996, Aqueous polynuclear aluminum species; in Sposito, G., (ed.), *The Environmental Chemistry of Aluminum*, 2nd ed.: CRC Press/Lewis Publishers, Boca Raton, Fla., pp. 117-168.
- Biernacki, A., 1978, Fish kills caused by pollution—Fifteen year summary 1961-1975: U.S. Environmental Protection Agency Report EPA-440/4-78-011, 78 pp.
- Bigham, J.M., 1994, Mineralogy of ochre deposits formed by sulfide oxidation; in Jambor J.L., and Blowes, D.W., (eds.), *The Environmental Geochemistry of Sulfide Mine-Wastes: Mineralogical Association of Canada, Nepean, Ontario, Short Course Handbook*, v. 22, pp. 103-132.
- Canada, Nepean, Ontario, Short Course Handbook, v. 22, pp. 103-132.
- Bigham, J.M., Schwertmann, U., Carlson, L., and Murad, E., 1990, A poorly crystallized oxyhydroxysulfate of iron formed by bacterial oxidation of Fe(II) in acid mine waters: *Geochimica et Cosmochimica Acta*, v. 54, pp. 2743-2758.
- Blanchard, R., 1968, Interpretation of leached outcrops: *Nevada Bureau of Mines Bulletin*, v. 66, 196 pp.
- Blowes, D.W., 1990, The geochemistry, hydrogeology, and mineralogy of decommissioned sulfide tailings—A comparative study: Unpub. Ph.D. thesis, Univ. of Waterloo, Ontario, Canada, 635 pp.
- Blowes, D.W., and Jambor, J.L., 1990, The pore-water geochemistry and the mineralogy of the vadose zone of sulfide tailings, Waite Amulet, Quebec, Canada: *Applied Geochemistry*, v. 5, pp. 327-346.
- Blowes, D.W., and Ptacek, C.J., 1994, Acid-neutralization mechanisms in inactive mine tailings; in Jambor, J.L., and Blowes, D.W., (eds.), *The Environmental Geochemistry of Sulfide Mine-Wastes: Mineralogical Association of Canada, Nepean, Ontario, Short Course Handbook*, v. 22, pp. 271-292.
- Blowes, D.W., Reardon, E.J., Jambor, J.L., and Cherry, J.A., 1991, The formation and potential importance of cemented layers in inactive sulfide mine tailings: *Geochimica et Cosmochimica Acta*, v. 55, pp. 965-978.
- Blowes, D.W., Al, T., Lortie, L., Gould, W.D., and Jambor, J.L., 1995, Microbiological, chemical, and mineralogical characterization of the Kidd Creek mine tailings impoundment, Timmins area, Ontario: *Geomicrobiology Journal*, v. 13, pp. 13-31.
- Braeuning, E., 1977, Mine water development in the lead and zinc deposits of Bawdwin, Burma; in 2nd Internal Symposium on Water-Rock Interaction: Strasbourg, France, pp. 1237-1245.
- Braley, S.A., 1954, Summary of report of Commonwealth of Pennsylvania, No. 326-B: Department of Health, Industrial Fellowship, Mellon Institute, 279 pp.
- Bricker, O.P., 1982, Redox potential—Its measurement and importance in water systems; in Minear, R.A., and Keith, L.H. (eds.), *Water Analysis, v. 1, Inorganic Species, Part 1: Academic Press, New York*, pp. 55-83.
- Brierley, C.L., and Murr, L.E., 1973, Leaching—Use of a thermophilic and chemoautotrophic microbe: *Science*, v. 179, pp. 488-489.
- Brierley, J.A., and Le Roux, N.W., 1977, A facultative thermophilic *Thiobacillus*-like bacterium—Oxidation of iron and pyrite; in Schwartz, W. (ed.), *Conference Bacterial Leaching 1977*: GBF, Verlag Chemie, Weinheim, pp. 55-66.
- Brophy, G.P., and Sheridan, M.E., 1965, Sulfate studies IV. The jarosite-natrojarosite-hydronium jarosite solid solution series: *American Mineralogist*, v. 50, pp. 1595-1607.
- Brophy, G.P., Scott, E.S., and Snellgrove, R.A., 1962, Sulfate studies II. Solid solution between alunite and jarosite: *American Mineralogist*, v. 47, pp. 112-126.
- Brown, A.D., and Jurinak, J.J., 1989, Mechanisms of pyrite oxidation in aqueous mixtures: *Journal of Environmental Quality*, v. 18, pp. 545-550.
- Bryner, L.C., Beck, J.F., Davis, D.B., and Wilson, D.G., 1954, Microorganisms in leaching sulfide minerals: *Industrial and Engineering Chemistry*, v. 46, pp. 2587-2592.
- Burke, S.P., and Downs, W.R., 1938, Oxidation of pyrite sulfur in coal mines: *American Institute of Mining, Metallurgical, and Petroleum Engineering*, v. 130, pp. 425-444.
- Buurman, P., 1975, *In vitro* weathering products of pyrite: *Geologie en Mijnbouw*, v. 54, pp. 101-105.
- Burkhalter, J.E., McCarty, P., and Parks, G.A., 1975, Oxidation of cinnabar by Fe(III) in acid mine waters: *Environmental Science and Technology*, v. 9, p. 676-678.
- Carlson, L., and Schwertmann, U., 1981, Natural ferrihydrites in surface deposits from Finland and their association with silica: *Geochimica et Cosmochimica Acta*, v. 4, pp. 421-429.
- Carlson-Fosch, V., 1991, Rare earth element mobility in acid mine drainage, Ophir region, San Juan Mountains, Colorado: Unpub. M.S. thesis, Dartmouth College, Dartmouth, N.H., 71 pp.
- Carpenter, L.V., and Herndon, L.K., 1933, Acid mine drainage from bituminous coal mines: West Virginia University Engineering Exploration Station Research Bulletin No. 19, 38 pp.
- Carrucio, F.T., 1970, The quantification of reactive pyrite by grain size distribution—3rd Symposium on Coal Mine Drainage Research: National Coal Association/Bituminous Coal Research, pp. 123-131.
- Carrucio, F.T., Geidel, G., and Sewell, J. M., 1976, The character of drainage as a function of the occurrence of framboidal pyrite and ground water quality in eastern Kentucky—6th Symposium on Coal Mine Drainage Research: National Coal Association/Bituminous Coal Research, pp. 1-16.
- Carson, C.D., Fanning, D.S., and Dixon, J.B., 1982, Alfisols and ultisols with acid sulfate weathering features in Texas; in Kittrick, J.A., Fanning, D.S., and Hossner, L.R. (eds.), *Acid Sulfate Weathering: Soil Science Society of America Spec. Pub. No. 10, Madison, Wis.*, pp. 127-146.

- Cathles, L.M., 1994, Attempts to model the industrial-scale leaching of copper-bearing mine waste; in Alpers, C.N., and Blowes, D.W. (eds.), *Environmental Geochemistry of Sulfide Oxidation: American Chemical Society Symposium Series 550*, Washington, D.C., pp. 123-131.
- Cathles, L.M., and Apps, J.A., 1975, A model of the dump leaching process that incorporates oxygen balance, heat balance, and air convection: *Metallurgical Transactions B*, v. 6B, p. 617-624.
- Chen, K.Y., and Morris, J.C., 1971, Oxidation of aqueous sulfide by  $O_2$ , 1. General characteristics and catalytic influences: *Proceedings of the 5th Internat'l Water Pollution Research Conference*, III-32, pp. 1-17.
- Chen, K.Y., and Morris, J.C., 1972, Kinetics of oxidation of aqueous sulfide by  $O_2$ : *Environmental Science and Technology*, v. 6, pp. 529-537.
- Chukhrov, F., Zvijagin, B.B., Gorshkov, A.I., Erilova, L.P., and Balashova, V.V., 1973, Ferrihydrite: *Izvetzia Akadamiy Nauklady SSSR Series Geology*, v. 4, pp. 23-33.
- Clark, C.S., 1966, Oxidation of coal mine pyrite: *Journal of Sanitary Engineering Division, Proceedings of American Society of Civil Engineers*, v. 92, pp. 127-145.
- Clarke, F.W., 1916, The data of geochemistry, 3rd ed.: U.S. Geological Survey Bulletin 616, 821 pp.
- Colmer, A.R., and Hinkle, M.E., 1947, The role of microorganisms in acid mine drainage: *Science*, v. 106, pp. 253-256.
- Colmer, A.R., Temple, K.L., and Hinkle, M.E., 1950, An iron-oxidizing bacterium from the acid drainage of some bituminous coal mines: *Journal of Bacteriology*, v. 59, pp. 317-328.
- Cravotta, C.A. III, 1994, Secondary iron-sulfate minerals as sources of sulfate and acidity; in Alpers, C.N., and Blowes, D.W. (eds.), *Environmental Geochemistry of Sulfide Oxidation: American Chemical Society Symposium Series 550*, Washington, D.C., pp. 345-364.
- Dagenhart, T.V., Jr., 1980, The acid mine drainage of Contrary Creek, Louisa County, Virginia: Factors causing variations in stream water chemistry: Unpub. M.S. thesis, Univ. of Virginia, 215 pp.
- Devasia, P., Natarajan, K.A., Sathayanarayana, D.N., and Rao, G.R., 1993, Surface chemistry of *Thiobacillus ferrooxidans* relevant to adhesion on mineral surfaces: *Applied and Environmental Microbiology*, v. 59, pp. 4051-4055.
- DiToro, D.M., Mahony, J.D., Hanson, D.J., Scott, K.J., Hicks, M.B., Mayr, S.M., and Redmond, M.S., 1991, Toxicity of cadmium in sediments: The role of acid volatile sulfide: *Environmental and Toxicological-Chemistry*, v. 9, pp. 1487-1502.
- Dugan, P.R., 1972, Biochemistry of acid mine drainage; in *Biochemical Ecology of Water Pollution*: Plenum Press, New York, pp. 123-137.
- Dugan, P.R., MacMillan, C.B., and Pfister, R.M., 1970, Aerobic heterotrophic bacteria indigenous to pH 2.8 acid mine water, I. Microscopic examination of acid streamers, II. Predominant slime-producing bacteria in acid streamers: *Journal of Bacteriology*, v. 101, p. 973-988.
- Dutrizac, J.E., 1983, Factors affecting alkali jarosite precipitation: *Metallurgical Transactions B*, v. 14B, p. 531-539.
- Dutrizac, J.E., and Kaiman, S., 1976, Synthesis and properties of jarosite-type compounds: *Canadian Mineralogist*, v. 14, pp. 151-158.
- Dzombak, D.A., and Morel, F.F., 1990, Surface complexation modeling—Hydrous ferric oxide: John Wiley and Sons, New York, 545 pp.
- Ehrlich, H.L., 1963a, Bacterial action on orpiment: *Economic Geology*, v. 58, pp. 991-994.
- Ehrlich, H.L., 1963b, Microorganisms in acid drainage from a copper mine: *Journal of Bacteriology*, v. 86, pp. 350-352.
- Ehrlich, H.L., 1964, Bacterial oxidation of arsenopyrite and enargite: *Economic Geology*, v. 59, p. 1306-1308.
- Elberling, B., Nicholson, R.V., and David, D., 1993, Field evaluation of sulfide oxidation rates: *Nordic Hydrology*, v. 24, p. 323-338.
- Evangelou, V.P. (Bill), 1995, Pyrite oxidation and its control: CRC Press, Boca Raton, Fla., 285 pp.
- Eychaner, J.H., 1991, The Globe, Arizona research site—Contaminants related to copper mining in a hydrologically integrated environment; in Mallard, G.E., and Aronson, D.A., (eds.), *Proceedings, U.S. Geological Survey Toxic Substances Hydrology Program: U.S. Geological Survey Water-Resources Investigations Report 91-4034*, pp. 439-447.
- Federal Water Pollution Control Administration, 1968, Pollution caused by fish kills—1967: 8th Annual Report, Washington, D.C., 16 pp.
- Fox, L.E., 1988, The solubility of colloidal ferric hydroxide and its relevance to iron concentrations in river water: *Geochimica et Cosmochimica Acta*, v. 52, pp. 771-777.
- Garrels, R.M., 1954, Mineral species as functions of pH and oxidation potentials with special reference to the zone of oxidation and secondary enrichment of sulfide ore deposits: *Geochimica et Cosmochimica Acta*, v. 5, pp. 153-168.
- Garrels, R.M., and Christ, C.M., 1965, Solutions, minerals, and equilibria: Freeman and Cooper, New York, 450 pp.
- Garrels, R.M., and Thompson, M.E., 1960, Oxidation of pyrite by iron sulfate solutions: *American Journal of Science*, v. 258A, pp. 57-67.
- Goldberg, S., Davis, J.A., and Hem, J.D., 1995, The surface chemistry of aluminum oxides and hydroxides; in Sposito, G., (ed.), *The Environmental Chemistry of Aluminum*, 2nd ed.: CRC Press/Lewis Publishers, Boca Raton, Fla., pp. 271-332.
- Goldhaber, M.B., 1983, Experimental study of metastable sulfur oxyanion formation during pyrite oxidation at pH 6-9 and 30°C: *American Journal of Science*, v. 283, pp. 193-217.
- Goleva, G.A., 1977, Hydrogeochemistry of ore elements: Nedra, Moscow, 215 pp.
- Goleva, G.A., Polyakov, V.A., and Nechayeva, T.P., 1970, Distribution and migration of lead in ground waters: *Geochemistry International*, v. 7, pp. 256-268.
- Gould, W.D., Béchard, G., and Lortie, L., 1994, The nature and role of microorganisms in the tailings environment; in Jambor, J.L., and Blowes, D.W. (eds.), *The Environmental Geochemistry of Sulfide Mine-Wastes: Mineralogical Association of Canada, Short Course Handbook*, v. 22, pp. 185-200.
- Granger, H.C., and Warren, C.G., 1969, Unstable sulfur compounds and the origin of roll-type uranium deposits: *Economic Geology*, v. 64, pp. 160-171.
- Harries, J.R., and Ritchie, A.I.M., 1981, The use of temperature profiles to estimate the pyritic oxidation rate in a waste rock dump from an open-pit mine: *Water, Air, and Soil Pollution*, v. 15, pp. 405-423.
- Hem, J.D., 1961, Stability field diagrams as aids in iron chemistry studies: *Journal American Water Works Association*, Feb., 1961, pp. 211-232.
- Hem, J.D., 1978, Redox processes at surfaces of manganese oxide and their effects on aqueous metal ions: *Chemical Geology*, v. 21, pp. 199-218.
- Hem, J.D., 1980, Redox coprecipitation mechanisms of manganese oxide; in Kavanaugh, M.C., and Leckie, J.O. (eds.), *Particulates in Water: Advances in Chemistry Series 189*, American Chemical Society, Washington, D.C., pp. 45-72.
- Hem, J.D., 1985, Study and interpretation of the chemical characteristics of natural water, 3rd ed.: U.S. Geological Survey Water-Supply Paper 2254, 264 pp.
- Hem, J.D., and Lind, C., 1993, Chemical processes in manganese oxide and carbonate precipitation in Pinal Creek, Arizona; in Morganwalp, D.W., and Aronson, D.A., (eds.), U.S. Geological Survey Toxic Substances Hydrology Program with Abstracts: U.S. Geological Survey Open-File Report 93-454, pp. 163.
- Hem, J.D., and Roberson, C.E., 1990, Aluminum hydrolysis reaction and products in mildly acidic aqueous systems; in Melchior, D.C., and Bassett, R.L. (eds.), *Chemical Modeling of Aqueous Systems II: American Chemical Society Symposium Series 416*, Washington, D.C., pp. 430-446.
- Hem, J.D., Roberson, C.E., and Lind, C.E., 1985, Thermodynamic stability of  $CoOOH$  and its coprecipitation with manganese: *Geochimica et Cosmochimica Acta*, v. 49, pp. 801-810.
- Hem, J.D., Roberson, C.E., and Lind, C.E., 1987, Synthesis and stability of heterolite,  $ZnMn_2O_4$ , at 25°C: *Geochimica et Cosmochimica Acta*, v. 51, pp. 1539-1547.
- Hemingway, B.S., and Sposito, G., 1996, Inorganic aluminum-bearing solid phases; in Sposito, G. (ed.), *The Environmental Chemistry of*

## GEOCHEMISTRY OF ACID MINE WATERS

- Aluminum, 2nd ed.: CRC Press/Lewis Publishers, Boca Raton, Fla., pp. 81-116.
- Hostetler, J.D., 1984, Electrode electrons, aqueous electrons, and redox potentials in natural waters: *American Journal of Science*, v. 294, pp. 734-759.
- Joseph, J.M., 1953, Microbiological study of acid mine waters—Preliminary report: *Ohio Journal of Science*, v. 53, pp. 123-127.
- Kämpf, N., and Schwertmann, U., 1982, Goethite and hematite in a clino-sequence in southern Brazil and their application in classification of kaolinitic soils: *Geoderma*, v. 29, pp. 27-39.
- Kelly, D.P., Norris, P.R., and Brierly, C.L., 1979, Microbiological methods for extractions and recovery of metals: *Symposium on Microbial Technology*, Society of General Microbiology, v. 29, pp. 263-308.
- Khalid, A.M., and Ralph, B.J., 1977, The leaching behavior of various zinc sulphide minerals with three *Thiobacillus* species; in Schwartz, W. (ed.), *Conference Bacterial Leaching 1977*: GBF, Verlag Chemie, Weinheim, p. 165-173.
- Kimball, B.A., Broshears, R.A., McKnight, D.M., and Bencala, K.E., 1994, Effects of instream pH modification on transport of sulfide-oxidation products; in Alpers, C.N., and Blowes, D.W. (eds.), *Environmental Geochemistry of Sulfide Oxidation*: American Chemical Society Symposium Series 550, Washington, D.C., pp. 224-243.
- Kleinmann, R.L.P., 1989, Acid mine drainage in the United States—Controlling the impact on streams and rivers: 4th World Congress on the Conservation of the Built and Natural Environments, Univ. of Toronto, pp. 1-10.
- Konishi, Y., Asai, S., and Sakai, H.K., 1990, Bacterial dissolution of pyrite by *Thiobacillus ferrooxidans*: *Bioprocess Engineering*, v. 5, pp. 5-17.
- Krauskopf, K.B., 1957, Separation of iron and manganese in sedimentary processes: *Geochimica et Cosmochimica Acta*, v. 12, pp. 61-84.
- Krauskopf, K.B., 1967, *Introduction to geochemistry*, 1st ed.: McGraw-Hill Book Company, New York, 617 pp.
- Krauskopf, K.B. and Bird, D.K., 1995, *Introduction to geochemistry*, 3rd ed.: McGraw-Hill Book Company, New York, 647 pp.
- Krumbein, W.C., and Garrels, R.M., 1952, Origin and classification of chemical sediments in terms of pH and oxidation-reduction potentials: *Journal of Geology*, v. 60, pp. 1-33.
- Kubisz, J., 1960, Hydronium jarosite— $(\text{H}_3\text{O})\text{Fe}_3(\text{SO}_4)_2(\text{OH})_6$ : *Bulletin Academia Polonia, Science, Series Science Geology and Geography*, v. 8, no. 2, pp. 95-99.
- Kubisz, J., 1961, Natural hydronium jarosites: *Bulletin Academia Polonia, Science, Series Science Geology and Geography*, v. 9, no. 4, pp. 195-200.
- Kubisz, J., 1964, Minerals of the alunite-jarosite group: *Polonia Academia Nauk, Prace Geologia*, v. 22, pp. 1-93 (in Polish).
- Kubisz, J., 1970, Studies on synthetic alkali-hydronium jarosites. I. Synthesis of jarosite and natrojarosite: *Mineralogia Polonia*, v. 1, pp. 45-57.
- Kushner, D.J. (ed.), 1978, *Microbial life in extreme environments*: Academic Press, New York, 465 pp.
- Kwong, Y.T.J., 1995, Influence of galvanic sulfide oxidation on mine water chemistry; in Hynes, T.P., and Blanchette, M.C. (eds.), *Proceedings of Sudbury '95—Mining and the Environment*, v. 2, May 28-June 1, Sudbury, Ontario: CANMET, Ottawa, pp. 477-484.
- Lacey, D.T., and Lawson, F., 1977, Kinetics of the liquid-phase oxidation of acid ferrous sulfate by the bacterium *Thiobacillus ferrooxidans*: *Biotechnology and Bioengineering*, v. 12, pp. 29-50.
- Lackey, J.B., 1938, The flora and fauna of surface waters polluted by acid mine drainage: *Public Health Report* 53, pp. 1499-1507.
- Landesman, J., Duncan, D.W., and Walden, C.C., 1966, Oxidation of inorganic sulfur compounds by washed cell suspensions of *Thiobacillus ferrooxidans*: *Canadian Journal of Microbiology*, v. 12, pp. 957-964.
- Langmuir, D., 1969, The Gibbs free energies of substances in the system  $\text{Fe}-\text{O}_2-\text{H}_2\text{O}-\text{CO}_2$ : *U.S. Geological Survey Professional Paper* 650-B, pp. 180-184.
- Langmuir, D., 1971, Particle size effect on the reaction goethite = hematite + water: *American Journal of Science*, v. 271, pp. 147-156.
- Langmuir, D., 1972, Correction—Particle size effect on the reaction goethite = hematite + water: *American Journal of Science*, v. 272, pp. 972.
- Le Roux, N.W., and Marshall, V.M., 1977, Effect of light on *Thiobacilli*; in Schwartz, W., (ed.), *Conference Bacterial Leaching 1977*: GBF, Verlag Chemie, Weinheim, pp. 21-35.
- Lichtner, P.C., 1994, Time-space continuum formulation of supergene enrichment and weathering of sulfide-bearing ore deposits; in Alpers, C.N., and Blowes, D.W. (eds.), *Environmental Geochemistry of Sulfide Oxidation*: American Chemical Society Symposium Series 550, Washington, D.C., pp. 153-170.
- Lind, C., 1991, Manganese minerals and associated fine particulates in the Pinal Creek streambed; in Mallard, G.E., and Aronson, D.A. (eds.), *Proceedings, U.S. Geological Survey Toxic Substances Hydrology Program*: U.S. Geological Survey Water-Resources Investigations Report 91-4034, pp. 486-491.
- Lindberg, R.D., and Runnells, D.D., 1984, Ground water redox reactions—An analysis of equilibrium state applied to Eh measurements and geochemical modeling: *Science*, v. 225, pp. 925-927.
- Lindgren, W., 1928, *Mineral deposits*, 3rd ed.: McGraw-Hill, New York, 1049 pp.
- Locke, A., 1926, *Leached outcrops as guides to copper ores*: Williams and Wilkins Co., Baltimore, Md, 166 pp.
- Loghry, J.D., 1972, Characteristics of favorable cappings from several southwestern porphyry copper deposits: Unpub. M.S. thesis, Univ. of Arizona, Tucson, 112 pp.
- Lowry, R.T., 1982, Aqueous oxidation of pyrite by molecular oxygen: *Chemical Reviews*, v. 82, pp. 461-497.
- Lundgren, D.G., Anderson, K.J., Remson, C.C., and Mahoney, R.P., 1964, Culture, structure and physiology of the chemoautotroph *Ferrobacillus ferrooxidans*: *Developments in Industrial Microbiology*, v. 6, pp. 250-259.
- Luther, G.W., II, 1987, Pyrite oxidation and reduction—Molecular orbital theory considerations: *Geochimica et Cosmochimica Acta*, v. 51, pp. 3193-3199.
- Luther, G.W., II, 1990, The frontier-molecular-orbital theory approach in geochemical processes; in Stumm, W., (ed.), *Aquatic Chemical Kinetics*: John Wiley and Sons, Inc., New York, pp. 173-198.
- Lyon, J.S., Hilliard, T.J., and Bethell, T.N., 1993, Burden of gilt: Mineral Policy Center, Washington, D.C., 68 pp.
- Markosyan, G.E., 1972, A new iron-oxidizing bacterium *Leptospirillum ferrooxidans*: gen. et sp. nov. *Biol. Zh. Arm.* v. 25, p. 26 (in Russian).
- Martin, H.W., and Mills, W.R., Jr, 1976, Water pollution caused by inactive ore and mineral mines: USEPA Contract Report 68-03-2212, 184 pp.
- Mathews, C.T., and Robins, R.G., 1972, The oxidation of ferrous disulfide by ferric sulfate: *Australian Chemical Engineering*, v. 47, pp. 21-25.
- Mathews, C.T., and Robins, R.G., 1974, Aqueous oxidation of iron disulfide by molecular oxygen: *Australian Chemical Engineering*, v. 15, pp. 19-24.
- May, H.M., and Nordstrom, D.K., 1991, Assessing the solubilities and reactions kinetics of aluminous minerals in soils; in Ulrich, B., and Sumner, M.E. (eds.), *Soil Acidity*: Springer-Verlag, pp. 125-148.
- McKay, D.R., and Halpern, J., 1958, A kinetic study of the oxidation of pyrite in aqueous suspension: *Transactions of the Metallurgical Society AIME*, v. 121, pp. 301-309.
- McKibben, M.A., and Barnes, H.L., 1986, Oxidation of pyrite in low temperature acidic solutions—Rate laws and surface textures: *Geochimica et Cosmochimica Acta*, v. 50, pp. 1509-1520.
- McKnight, D., and Bencala, K.E., 1988, Diel variations in iron chemistry in an acidic stream in the Colorado Rocky Mountains, U.S.A.: *Arctic and Alpine Research*, v. 20, pp. 492-500.
- McKnight, D.M., and Bencala, K.E., 1989, Reactive iron transport in an acidic mountain stream in Summit County, Colorado—A hydrologic perspective: *Geochimica et Cosmochimica Acta*, v. 53, pp. 2225-2234.
- McKnight, D.M., Kimball, B.A., and Bencala, K.E., 1988, Iron photoreduction and oxidation in an acidic mountain stream: *Science*, v. 240, pp. 637-640.

- Mills, A.L., 1999, The role of bacteria in environmental geochemistry; in Plumlee, G.S., and Logsdon, M.J. (eds.), *The Environmental Geochemistry of Mineral Deposits, Part A. Processes, Techniques, and Health Issues*: Society of Economic Geologists, *Reviews in Economic Geology*, v. 6A, pp. 125-132.
- Moore, J.N., and Luoma, S.N., 1990, Hazardous wastes from large-scale metal extraction: *Environmental Science and Technology*, v. 24, p. 1278-1285.
- Moses, C.O., and Herman, J.S., 1991, Pyrite oxidation at circumneutral pH: *Geochimica et Cosmochimica Acta*, v. 55, pp. 471-482.
- Moses, C.O., Nordstrom, D.K., and Mills, A.L., 1984, Sampling and analyzing mixtures of sulphate, sulphite, thiosulfate, and polythionate: *Talanta*, v. 31, pp. 331-339.
- Moses, C.O., Nordstrom, D.K., Herman, J.S. and Mills, A.L., 1987, Aqueous pyrite oxidation by dissolved oxygen and by ferric iron: *Geochimica et Cosmochimica Acta*, v. 51, pp. 1561-1571.
- Murad, E., Schwertmann, U., Bigham, J.M., and Carlson, L., 1994, Mineralogical characteristics of poorly crystallized precipitates formed by oxidation of Fe<sup>2+</sup> in acid mine sulfate waters; in Alpers, C.N., and Blowes, D.W. (eds.), *Environmental Geochemistry of Sulfide Oxidation*: American Chemical Society Symposium Series 550, Washington, D.C., pp. 190-200.
- Nathansohn, A., 1902, Über eine neue Gruppe von Schwefelbakterien und ihren Stoffwechsel: *Mitt. Zool. Staatsmus. Neapel*, v. 15, pp. 655-680.
- Nicholson, R.V., 1994, Iron-sulfide oxidation mechanisms—Laboratory studies; in Jambor, J.L., and Blowes, D.W. (eds.), *The Environmental Geochemistry of Sulfide Mine-Wastes*: Mineralogical Association of Canada, *Short Course Handbook*, v. 22, pp. 163-183.
- Nicholson, R.V., and Scharer, J.M., 1994, Laboratory studies of pyrrhotite oxidation kinetics; in Alpers, C.N., and Blowes, D.W. (eds.), *Environmental Geochemistry of Sulfide Oxidation*: American Chemical Society Symposium Series 550, Washington, D.C., pp. 14-30.
- Nicholson, R.V., Gillham, R.W., and Reardon, E.J., 1988, Pyrite oxidation in carbonate-buffered solutions, 1. Experimental kinetics: *Geochimica et Cosmochimica Acta*, v. 52, pp. 1077-1085.
- Nor, Y.M., and Tabatai, M.A., 1976, Oxidation of elemental sulfur in soils: *Soil Science Society of America Journal*, v. 41, pp. 736-741.
- Nordstrom, D.K., 1982a, Aqueous pyrite oxidation and the consequent formation of secondary iron minerals; in Kittrick, J.A., Fanning, D.S., and Hossner, L.R., (eds.), *Acid Sulfate Weathering*: Soil Science Society of America Spec. Pub. No. 10, pp. 37-56.
- Nordstrom, D.K., 1982b, The effects of sulfate on aluminum concentrations in natural waters—Some stability relations in the system Al<sub>2</sub>O<sub>3</sub>-SO<sub>3</sub>-H<sub>2</sub>O at 298 K: *Geochimica et Cosmochimica Acta*, v. 46, pp. 681-692.
- Nordstrom, D.K., 1985, The rate of ferrous iron oxidation in a stream receiving acid mine effluent; in *Selected Papers in the Hydrological Sciences*: U.S. Geological Survey Water-Supply Paper 2270, pp. 113-119.
- Nordstrom, D.K., 1991, Chemical modeling of acid mine waters in the western United States; in Mallard, G.E., and Aronson, D.A. (eds.), *Proceedings, U.S. Geological Survey Toxic Substances Hydrology Program*: U.S. Geological Survey Water-Resources Investigations Report 91-4034, pp. 534-538.
- Nordstrom, D.K., and Alpers, C.N., 1999, Negative pH, efflorescent mineralogy, and consequences for environmental restoration at the Iron Mountain Superfund site, California: *Proceedings of the National Academy of Sciences*, v. 96, pp. 3455-3462.
- Nordstrom, D.K., and Ball, J.W., 1985, Toxic element composition of acid mine waters from sulfide ore deposits: 2nd Internatl Mine Water Symposium, Granada, Spain, pp. 749-758.
- Nordstrom, D.K., and Ball, J.W., 1986, The geochemical behavior of aluminum in acidified surface waters: *Science*, v. 232, pp. 54-56.
- Nordstrom, D.K., and May, H.M., 1996, Aqueous equilibrium data for mononuclear aluminum species; in Sposito, G. (ed.), *The Environmental Chemistry of Aluminum*, 2nd ed.: CRC Press/Lewis Publishers, Boca Raton, Fla., pp. 39-80.
- Nordstrom, D.K., and Munoz, J.L., 1994, *Geochemical thermodynamics*, 2nd ed.: Blackwell Science, 493 pp.
- Nordstrom, D.K., and Southam, G., 1997, Geomicrobiology of sulfide mineral oxidation; in Banfield, J.F., and Nealson, K.H. (eds.), *Geomicrobiology—Interactions Between Microbes and Minerals: Reviews in Mineralogy*, Mineralogical Society of America, Washington, D.C., v. 35, pp. 361-390.
- Nordstrom, D.K., Jenne, E.A., and Averett, R.C., 1977, Heavy metal discharges into Shasta Lake and Keswick Reservoir on the Upper Sacramento River, California—A reconnaissance during low flow: U.S. Geological Survey Open-File Report 76-49, pp. 25.
- Nordstrom, D.K., Jenne, E.A., and Ball, J.W., 1979, Redox equilibria of iron in acid mine waters; in Jenne, E.A., (ed.), *Chemical Modeling in Aqueous Systems*: American Chemical Society Symposium Series 93, Washington, D.C., pp. 51-80.
- Nordstrom, D.K., Ball, J.W., Roberson, C.E., and Hanshaw, B.B., 1984, The effect of sulfate on aluminum concentrations in natural waters, II. Field occurrences and identification of aluminum hydroxysulfate precipitates [abs.]: *Geological Society of America Abstracts with Programs*, v. 16, no. 6, pp. 611.
- Nordstrom, D.K., Alpers, C.N., and Ball, J.W., 1991, Measurement of negative pH and extremely high metal concentrations in acid mine water from Iron Mountain, California [abs.]: *Geological Society of America Annual Meeting, Abstract with Programs*, v. 23, no. 5, pp. A383.
- Nordstrom, D.K., McNutt, R.H., Puigdomènech, I., Smellie, J.A.T., and Wolf, M., 1992, Ground water chemistry and geochemical modeling of water-rock interactions at the Osamu Utsumi mine and Morro do Ferro analogue study sites, Poços de Caldas, Minas Gerais, Brazil: *Journal of Geochemical Exploration*, v. 45, pp. 249-287.
- Nordstrom, D.K., Carlson-Fosch, V., and Oreskes, N., 1995, Rare earth element (REE) fractionation during acidic weathering of San Juan tuff, Colorado [abs.]: *Geological Society of America Annual Meeting, Abstracts with Programs*, v. 27, no. 6, p. A-199.
- Olson, G.J., 1991, Rate of pyrite bioleaching by *Thiobacillus ferrooxidans*—Results of an interlaboratory comparison: *Applied and Environmental Microbiology*, v. 57, pp. 642-644.
- Pabst, A., 1940, Cryptocrystalline pyrite from Alpine County, California: *American Mineralogist*, v. 25, pp. 425-431.
- Parker, R.L., 1962, Isomorphous substitution in natural and synthetic alunite: *American Mineralogist*, v. 47, pp. 127-136.
- Parks, G.A., 1990, Surface energy and adsorption at mineral/water interfaces—An introduction; in Hochella, M.F., Jr., and White, A.F. (eds.), *Mineral-Water Interface Geochemistry: Reviews in Mineralogy*, Mineralogical Society of America, Washington, D.C., v. 23, pp. 133-175.
- Plumlee, G.S., Smith, K.S., Mosier, E.L., Ficklin, W.H., Montour, M., Briggs, P.H., and Meier, A.L., 1995, Geochemical processes controlling acid-drainage generation and cyanide degradation at Summitville; in Posey, H.H., Pendleton, J.A., and Van Zyl, D., (eds.), *Summitville Forum Proceedings*: Colorado Geological Survey Spec. Pub. No. 38, pp. 23-34.
- Ponnamperuma, F.N., Tianco, E.M., and Loy, T., 1967, Redox equilibria in flooded soils, I. The iron hydroxide systems: *Soil Science*, v. 103, pp. 374-382.
- Potter, R.W., II, 1977, An electrochemical investigation of the system copper-sulfur: *Economic Geology*, v. 72, pp. 1524-1542.
- Pourbaix, M., 1945, Thermodynamique des solutions aqueuses diluées—Representation graphique du pH et du potentiel: Ph.D. thesis, Delft, Beranger, Paris and Liege.
- Pourbaix, M., 1966, *Atlas of electrochemical equilibria in aqueous solutions*: Pergamon Press, New York, 670 pp.
- Pourbaix, M., and Pourbaix, A., 1992, Potential-pH equilibrium diagrams for the system S-H<sub>2</sub>O from 25 to 150°C—Influence of access of oxygen in sulfide solutions: *Geochimica et Cosmochimica Acta*, v. 56, pp. 3157-3178.
- Powell, A.R., and Parr, S.W., 1919, Forms in which sulfur occurs in coal: *Bulletin of the American Institute of Mining and Metallurgical Engineering*, pp. 2041-2049.

## GEOCHEMISTRY OF ACID MINE WATERS

- Platak, C.J., and Blowes, D.W., 1994, Influence of siderite on the geochemistry of inactive mine tailings impoundment; in Alpers, C.N., and Blowes, D.W. (eds.), Environmental Geochemistry of Sulfide Oxidation: American Chemical Society Symposium Series 550, Washington, D.C., pp. 172-189.
- Reardon, E.J., 1988, Ion interaction parameters for Al-SO<sub>4</sub> and application to the prediction of metal sulfate solubility in binary salt systems: Journal of Physical Chemistry, v. 42, pp. 6426-6431.
- Rickard, P.A., and Vanselow, D.G., 1978, Investigations into the kinetics and stoichiometry of bacterial oxidation of covellite (CuS) using a polarographic probe: Canadian Journal of Microbiology, v. 24, pp. 998-1003.
- Rimstidt, J.D., Chermak, J.A., and Gagen, P.M., 1994, Rates of reaction of galena, sphalerite, chalcopyrite, and arsenopyrite with Fe(III) in acidic solutions; in Alpers, C.N., and Blowes, D.W. (eds.), Environmental Geochemistry of Sulfide Oxidation: American Chemical Society Symposium Series 550, Washington, D.C., pp. 2-13.
- Ripmeester, J.A., Ratcliffe, C.I., Dutrizac, J.E. and Jambor, J.L., 1986, Hydronium ion in the alunite-jarosite group: Canadian Mineralogist, v. 24, pp. 435-447.
- Ritcey, G.M., 1989, Tailings management, problems and solutions in the mining industry: Elsevier Science Publishing Co. Inc., Amsterdam, 970 pp.
- Ritchie, A.I.M., 1994a, Sulfide oxidation mechanisms—Control and rates of oxygen transport; in Jambor, J.L., and Blowes, D.W. (eds.), The Environmental Geochemistry of Sulfide Mine-Wastes: Mineralogical Association of Canada, Short Course Handbook, v. 22, pp. 201-245.
- Ritchie, A.I.M., 1994b, Rates of mechanisms that govern pollutant generation from pyritic wastes; in Alpers, C.N., and Blowes, D.W. (eds.), Environmental Geochemistry of Sulfide Oxidation: American Chemical Society Symposium Series 550, Washington, D.C., pp. 108-122.
- Runnells, D.D., Shepard, T.A., and Angino, E.E., 1992, Metals in water—Determining natural background concentrations in mineralized areas: Environmental Science and Technology, v. 26, pp. 2316-2322.
- Russell, J.D., 1979, Infrared spectroscopy of ferrihydrite—Evidence for the presence of structural hydroxyl groups: Clay Minerals, v. 14, pp. 109-113.
- Sakaguchi, H., Torma, A.E., and Silver, M., 1976, Microbiological oxidation of synthetic chalcocite and covellite by *Thiobacillus ferrooxidans*: Applied and Environmental Microbiology, v. 31, pp. 7-10.
- Sand, W., Rhode, K., and Zenneck, C., 1992, Evaluation of *Leptospirillum ferrooxidans* for leaching: Applied and Environmental Microbiology, v. 58, pp. 85-92.
- Sato, M., 1992, Persistence-field Eh-pH diagrams for sulfides and their application to supergene oxidation and enrichment of sulfide ore bodies: Geochimica et Cosmochimica Acta, v. 56, pp. 3133-3156.
- Scala, G., Mills, A.L., Moses, C.O., and Nordstrom, D.K., 1982, Distribution of autotrophic Fe and sulfur-oxidizing bacteria in mine drainage from sulfide deposits measured with the FAINT assay [abs.]: American Society of Microbiology Annual Meeting.
- Schwertmann, U., 1985a, The effect of pedogenic environments on iron oxide minerals, in Stewart, B.A. (ed.), Advances in Soil Science, v. 1: Springer-Verlag, New York, pp. 171-200.
- Schwertmann, U., 1985b, Occurrence and formation of iron oxides in various pedoenvironments; in Stucki, F.W., Goodman, B.A. and Schwertmann, U. (eds.), Iron in Soils and Clay Minerals: D. Reidel Pub. Co., Boston, Mass., NATO Advanced Study Institute Series C, v. 217, pp. 267-308.
- Schwertmann, U., and Cornell, R.M., 1991, Iron oxides in the laboratory—Preparation and characterization: Verlag Chemie, Weinheim, Germany, 137 pp.
- Schwertmann, U., and Murad, E., 1983, The effect of pH on the formation of goethite and hematite from ferrihydrite: Clays and Clay Minerals, v. 31, pp. 277-284.
- Scott, K.D., 1987, Solid solution in, and classification of, gossan-derived members of the alunite-jarosite family, Northwest Queensland, Australia: American Mineralogist, v. 72, pp. 178-187.
- Silverman, M.P., 1967, Mechanism of bacterial pyrite oxidation: Journal of Bacteriology, v. 94, pp. 1046-1051.
- Silverman, M.P., and Lundgren, D.G., 1959, Studies on the chemotrophic iron bacterium *Ferrobacillus ferrooxidans*, I. An improved medium and a harvesting procedure for securing high cell yields: Journal of Bacteriology, v. 77, pp. 642-647.
- Silverman, M.P., Rogoff, M.H., and Wender, I., 1961, Bacterial oxidation of pyritic materials in coal: Applied and Environmental Microbiology, v. 9, pp. 491-496.
- Singer, P.C., and Stumm, W., 1968, Kinetics of the oxidation of ferrous iron, 2nd Symposium on Coal Mine Drainage Research: National Coal Association/Bituminous Coal Research, pp. 12-34.
- Singer, P.C., and Stumm, W., 1970a, Acid mine drainage—The rate-determining step: Science, v. 167, pp. 1121-1123.
- Singer, P.C., and Stumm, W., 1970b, Oxygenation of ferrous iron: Federal Water Quality Administration Report 14010-06/69, 198 pp.
- Smith, E.E., and Shumate, K.S., 1970, Sulfide to sulfate reaction mechanism: Federal Water Pollution Control Federation Report, 115 pp.
- Smith, K.S., 1999, Metal sorption on mineral surfaces—An overview with examples relating to mineral deposits; in Plumlee, G.S., and Logsdon, M.J. (eds.), The Environmental Geochemistry of Mineral Deposits, Part A. Processes, Techniques, and Health Issues: Society of Economic Geologists, Reviews in Economic Geology, v. 6A, pp. 161-182.
- Sokolova, G.A., and Karavaiko, G.I., 1968, Physiology and geochemical activity of *Thiobacilli*: Izdatelstvo "Nauka," Moscow, 283 pp.
- Southam, G., and Beveridge, T.J., 1992, Enumeration of *Thiobacilli* within pH-neutral and acidic mine tailings and their role in the development of secondary mineral soil: Applied and Environmental Microbiology, v. 58, pp. 1904-1912.
- Steger, H.F., and Desjardins, L.E., 1978, Oxidation of sulfide minerals, IV. Pyrite, chalcopyrite, and pyrrotite: Chemical Geology, v. 23, pp. 225-237.
- Stoffregen, R.E., and Alpers, C.N., 1987, Woodhouseite and svanbergite in hydrothermal ore deposits—Products of apatite destruction during advanced argillic alteration: Canadian Mineralogist, v. 45, pp. 201-211.
- Stoffregen, R.E., and Alpers, C.N., 1992, Observations on the unit-cell dimensions, H<sub>2</sub>O contents, and  $\delta D$  values of natural and synthetic alunite: American Mineralogist, v. 77, pp. 1092-1098.
- Stokes, H.N., 1901, On pyrite and marcasite: U.S. Geological Survey Bulletin 186, 50 pp.
- Stumm, W., and Morgan, J.J., 1981, Aquatic chemistry, 2nd ed.: Wiley-Interscience, New York, 770 pp.
- Sveshnikov, G.B., and Dobyichin, S.L., 1956, Electrochemical solution of sulfides and dispersion aureoles of heavy metals: Geokhimiya, no. 4, pp. 413-419.
- Sveshnikov, G.B., and Ryss, Yu.S., 1964, Electrochemical processes in sulfide deposits and their geochemical significance: Geokhimiya, v. 3, pp. 208-218.
- Tardy, Y., and Nahon, D., 1985, Geochemistry of laterites, stability of Al-goethite, Al-hematite, and Fe<sup>3+</sup>-kaolinite in bauxites and ferricretes: American Journal of Science, v. 285, pp. 865-903.
- Temple, K.L., and Colmer, A.R., 1951, The autotrophic oxidation of iron by a new bacterium—*Thiobacillus ferrooxidans*: Journal of Bacteriology, v. 62, pp. 605-611.
- Temple, K.L., and Delchamps, E.W., 1953, Autotrophic bacteria and the formation of acid in bituminous coal mines: Applied Microbiology, v. 1, pp. 255-258.
- Tervari, P.H., and Campbell, A.B., 1976, Dissolution of iron sulfide (troilite) in aqueous sulfuric acid: Journal of Physical Chemistry, v. 80, pp. 1844-1848.
- Thorber, M.R., 1975, Supergene alteration of sulfides, II. A chemical study of the Kambalda nickel deposits: Chemical Geology, v. 15, pp. 117-144.
- Thorstensen, D.C., 1984, The concept of electron activity and its relation to redox potentials in aqueous geochemical systems: U.S. Geological Survey Open-File Report 84-072, 45 pp.
- To, B.T., Nordstrom, D.K., Cunningham, K.M., Ball, J.W., and

- McCleskey, R.B., 1999, New method for the direct determination of dissolved Fe(III) concentration in acid mine waters: *Environmental Science and Technology*, v. 33, pp. 807-813.
- Torma, A.E., and Habashi, F., 1972, Oxidation of copper (II) selenide by *Thiobacillus ferrooxidans*: *Canadian Journal of Microbiology*, v. 18, pp. 1780-1781.
- Torma, A.E., and Subramanian, K.N., 1974, Selective bacterial leaching of a lead sulphide concentrate: *International Journal of Mineral Processing*, v. 1, pp. 125-134.
- Torma, A.E., Walden, C.C., Duncan, D.W., and Branion, R.M., 1972, The effect of carbon dioxide and particle surface area on the microbiological leaching of a zinc sulfide concentrate: *Biotechnology and Bioengineering*, v. 15, pp. 777-786.
- Torma, A.E., Legault, G., Kougiomoutzakos, D., and Ouellet, R., 1974, Kinetics of bio-oxidation of metal sulfides: *Canadian Journal of Chemical Engineering*, v. 52, pp. 515-517.
- Torma, A.E., Gabra, G.G., Guay, R., and Silver, M., 1976, Effects of surface active agents on the oxidation of chalcopyrite by *Thiobacillus ferrooxidans*: *Hydrometallurgy*, v. 1, pp. 301-309.
- Torrent, J., and Guzman, R., 1982, Crystallization of Fe(III)-oxides from ferrihydrite in salt solutions—Osmotic and specific ion effects: *Clays and Clay Minerals*, v. 17, pp. 463-469.
- Towe, K.M., and Bradley, W.F., 1967, Mineralogical constituents of colloidal "hydrous ferric oxides": *Journal of Colloid and Interface Science*, v. 24, pp. 384-392.
- Tunell, G., 1930, The oxidation of disseminated copper ores in altered porphyry: Unpub. Ph.D. thesis, Harvard Univ., 104 pp.
- Tuovinen, O.H., Niemela, S.I., and Gyllenberg, H.G., 1971, Tolerance of *Thiobacillus ferrooxidans* to some metals: *Antonie van Leeuwenhoek*, v. 37, pp. 489-496.
- Turner, A.W., 1949, Bacterial oxidation of arsenite: *Nature*, v. 164, pp. 76-77.
- U.S. Environmental Protection Agency, 1985, Wastes from the extraction and beneficiation of metallic ores, phosphate rock, asbestos, overburden from uranium mining, and oil shale: Report to Congress, EPA/530-SW-85-033.
- Vairavamurthy, A., Manowitz, B., Zhou, W., and Jeon, Y., 1994, Determination of hydrogen sulfide oxidation products by sulfur K-edge X-ray absorption near-edge structure spectroscopy; in Alpers, C.N., and Blowes, D.W. (eds.), *Environmental Geochemistry of Sulfide Oxidation*: American Chemical Society Symposium Series 550, Washington, D.C., pp. 412-430.
- Vranesh, G., 1979, Mine drainage—The common enemy; in Argal, G.O., Jr., and Brawner, C.O. (eds.), *Proceedings, 1st Internatl Mine Drainage Symposium*: Miller Freeman Publications, pp. 54-97.
- Waite, T.D., and Morel, F.M.M., 1984, Photoreductive dissolution of colloidal iron oxides in natural waters: *Environmental Science and Technology*, v. 18, pp. 860-868.
- Wakao, N., Sakurai, Y., and Shiota, H., 1977, Microbial oxidation of ferrous iron in acid mine water at sulfur and iron-sulfide mine: *Soil Science and Plant Nutrition*, v. 23, pp. 207-216.
- Wakao, N., Mishina, M., Sakurai, Y., and Shiota, H., 1982, Bacterial pyrite oxidation, I. The effect of pure and mixed cultures of *Thiobacillus ferrooxidans* and *Thiobacillus thiooxidans* on release of iron: *Journal of General and Applied Microbiology*, v. 28, pp. 331-343.
- Wakao, N., Mishina, M., Sakurai, Y., and Shiota, H., 1984, Bacterial pyrite oxidation, III. Adsorption of *Thiobacillus ferrooxidans* cells on solid surfaces and its effect on iron release from pyrite: *Journal of General and Applied Microbiology*, v. 30, pp. 63-77.
- Wakao, N., Koyatsu, H., Komai, Y., Shimokawara, H., Sakurai, Y., and Shiota, H., 1988, Microbial oxidation of arsenite and occurrence of arsenite-oxidizing bacteria in acid mine water from a sulfur-pyrite mine: *Geomicrobiology Journal*, v. 6, pp. 11-24.
- Waksman, S.A., and Jaffe, J.S., 1921, Acid production by a new sulfur-oxidizing bacterium: *Science*, v. 53, pp. 216.
- Waksman, S.A., and Jaffe, J.S., 1922, Microorganisms concerned in the oxidation of sulphur in the soil, II. *Thiobacillus thiooxidans*, a new sulphur-oxidizing organism isolated from the soil: *Journal of Bacteriology*, v. 7, pp. 239-256.
- Walker, T.R., 1967, Formation of red beds in modern and ancient deserts: *Geological Society of America Bulletin*, v. 78, pp. 353-368.
- Walker, T.R., 1974, Formation of red beds in moist tropical climates—A hypothesis: *Geological Society of America Bulletin*, v. 84, pp. 633-638.
- Walker, T.R., 1976, Diagenetic origin of continental red beds; in Falke, H. (ed.), *The Continental Permian in Central, West, and South Europe*: D. Reidel Publishing Co., pp. 241-282.
- Walsh, A.W., and Rimstidt, J.D., 1986, Rates of reaction of covellite and blaubleibender covellite with ferric iron at pH 2.0: *Canadian Mineralogist*, v. 24, pp. 35-44.
- White, A.F., and Brantley, S.L., 1995, Chemical weathering rates of silicate minerals: *Reviews in Mineralogy*, Mineralogical Society of America, Washington, D.C., v. 31, 583 pp.
- White, W.W., III, and Jeffers, T.H., 1994, Chemical predictive modeling of acid mine drainage from metallic sulfide-bearing waste rock; in Alpers, C.N., and Blowes, D.W. (eds.), *Environmental Geochemistry of Sulfide Oxidation*: American Chemical Society Symposium Series 550, Washington, D.C., pp. 608-630.
- Wieder, R.K., 1994, Diel changes in iron(III)/iron(II) in effluent from constructed acid mine drainage treatment wetlands: *Journal of Environmental Quality*, v. 23, no. 4, pp. 730-738.
- Wiersma, C.L., and Rimstidt, J.D., 1984, Rates of reactions of pyrite and marcasite with ferric iron at pH 2: *Geochimica et Cosmochimica Acta*, v. 48, pp. 85-92.
- Wilber, C.G., 1969, *The biological aspects of water pollution*: C.C. Thomas, New York, 296 pp.
- Williams, E.G., Rose, A.W., Parizek, R.R., and Waters, S.A., 1982, Factors controlling the generation of acid mine drainage: Pennsylvania State University Report to the U.S. Bureau of Mines, 265 pp.
- Williamson, M.A., and Rimstidt, J.D., 1993, The rate of decomposition of the ferric-thiosulfate complex in acidic aqueous solutions: *Geochimica et Cosmochimica Acta*, v. 57, pp. 3555-3561.
- Yakhontova, L. K., Zeman, I., and Nesterovich, L.G., 1980, Oxidation of tetrahydrite: *Doklady, Earth Sciences Section, Akademia Nauk SSSR*, v. 253, pp. 461-464.
- Yapp, C.J., 1983, Stable hydrogen isotopes in iron oxides—Isotope effects associated with the dehydration of a natural goethite: *Geochimica et Cosmochimica Acta*, v. 47, pp. 1277-1287.
- Zhang, J., and Millero, F.J., 1994, Kinetics of oxidation of hydrogen sulfide in natural waters; in Alpers, C.N., and Blowes, D.W. (eds.), *Environmental Geochemistry of Sulfide Oxidation*: American Chemical Society Symposium Series 550, Washington, D.C., pp. 393-409.
- Zodrov, E.L., and McCandlish, K., 1978a, Hydrated sulphates in the Sydney Coalfield, Cape Breton, Nova Scotia: *Canadian Mineralogist*, v. 16, pp. 17-22.
- Zodrov, E.L., and McCandlish, K., 1978b, Roof weakness—Fossilization and (cyclic) regenerative hydrated sulphates, Discussion: *Canadian Institute of Mining and Metallurgy Bulletin*, v. 71, pp. 90-91.
- Zodrov, E.L., Wiltshire, J., and McCandlish, E., 1979, Hydrated sulphates in the Sydney Coalfield, Cape Breton, Nova Scotia, II. Pyrite and its alteration products: *Canadian Mineralogist*, v. 17, pp. 63-70.
- Zverev, V.P., Dol'nikov, V.A., Khutorskoy, M.D., Dobrovol'skiy, Ye.V., Lyal'ko, V.I., Mitnik, M.M. and Fotogdinov, R.A., 1983, Sulfide oxidation kinetics and heat effects: *Geochemistry International*, v. 20, pp. 82-90.